
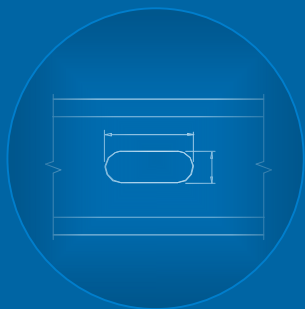
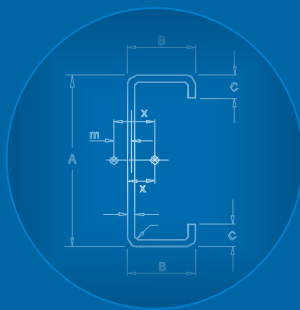


# LIGHTWEIGHT STEEL FRAMING

## Member Selection Tables (Imperial)

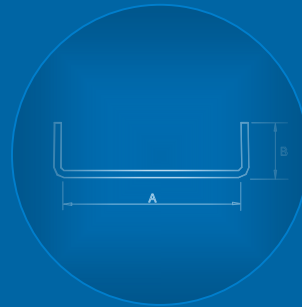

## LIGHTWEIGHT STEEL FRAMING MEMBER SELECTION TABLES

**58-2018**  
**June 2018**

**Prepared for:**  
CANADIAN SHEET STEEL BUILDING INSTITUTE

**Prepared by:**  
Prof. R.M. Schuster, P.Eng.  
Distinguished Professor Emeritus, University of Waterloo

**Copyright © June 2018**  
All rights reserved. This publication, nor any part thereof, may be reproduced in any form  
without the written permission of the publisher.

### PREFACE

The material presented has been prepared for the general information of the reader. While the material is believed to be technically correct and in accordance with recognized good practice at the time of publication it should not be used without first securing competent advice with respect to its suitability for any specific application. Neither the *Canadian Sheet Steel Building Institute*, its Members, nor Prof. Schuster warrant or assume any liability for the suitability of the material for any general or particular application.

## TABLE OF CONTENTS

### **General Notes**

Introduction .....	4
Product Designator .....	4
Manufacturer Certification and Product Marking .....	4
Section Geometries .....	5
Section Properties .....	6
Symbols .....	7
Design Examples .....	8

### **Section Properties**

Stud Section Properties .....	12
Joist Section Properties .....	14
Track Section Properties .....	16
<b>Curtain Wall Limiting Height Tables – Single and Double Spans</b> .....	<b>19</b>
<b>Combined Axial and Lateral Load Tables</b> .....	<b>36</b>
<b>Floor Joist Load Tables</b> .....	<b>69</b>
<b>Header Load Tables</b> .....	<b>78</b>
<b>Web Crippling Data</b> .....	<b>83</b>
<b>S-Section Ceiling Span Tables</b> .....	<b>86</b>
<b>U-Channel Section Properties</b> .....	<b>87</b>
<b>U-Channel Ceiling Span Tables</b> .....	<b>88</b>
<b>Furring Channel Section Properties</b> .....	<b>89</b>
<b>Furring Channel Ceiling Span Tables</b> .....	<b>90</b>

## GENERAL NOTES


### 1. INTRODUCTION

The technical data in this publication is intended as an aid to the design professional and should not be used to replace the judgement of a qualified Engineer or Architect.

### 2. PRODUCT DESIGNATOR

Lightweight steel framing manufacturers in Canada use a common designator method for identifying their products. The designator is a four-part code that identifies depth, flange width, member type and material thickness. This designator (based on Imperial units) is used for both SI metric and Imperial units.

**Example:** 600S162-54

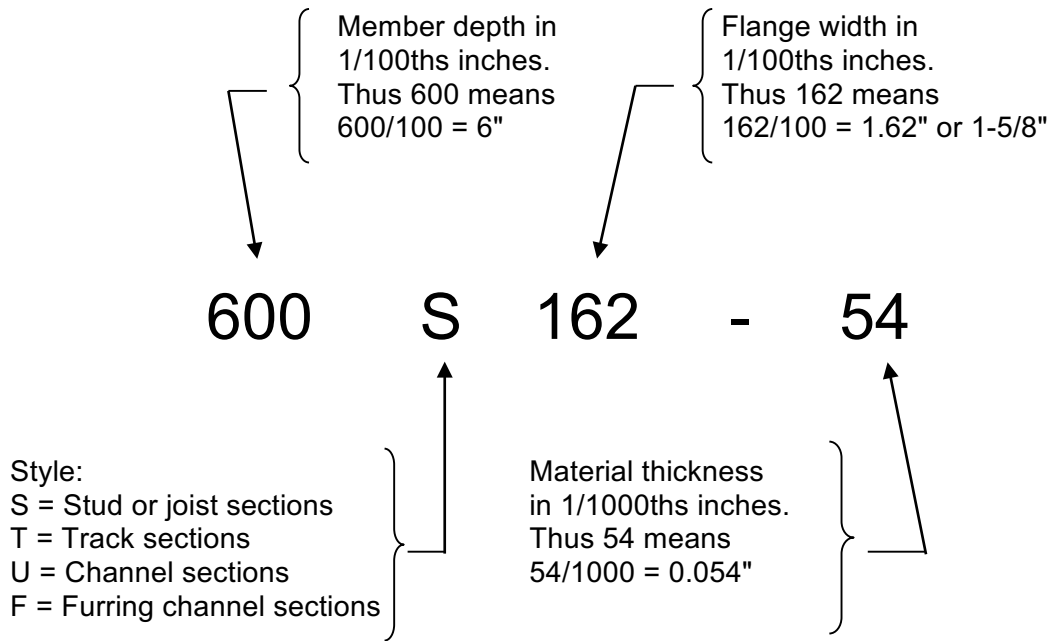

### 3. MANUFACTURER CERTIFICATION AND PRODUCT MARKING

- 3.1 **Lightweight steel framing manufacturers who are members of the CSSBI and adhere to the CSSBI Manufacturer Certification Requirements for Cold Formed Steel Framing Members are the only companies that have authorization from the CSSBI to utilize these tables.**

Under the *CSSBI Manufacturer Certification Program*, a participating manufacturer certifies that the designated structural and non-structural cold formed steel (CFS) framing members it produces meet or exceed the relevant ASTM International (ASTM), Canadian Standards Association (CSA) and American Iron and Steel Institute (AISI) standard requirements. The manufacturer's products are validated through an independent 3<sup>rd</sup> party review of the products and production practices, by appropriate testing and inspection.

### 3.2 Marking:

Individual products shall have a legible label, stencil, or embossment on the member with the following minimum information:

- (a) Initials “CSSBI”;
- (b) Manufacturer’s identification (2 or 3 letters);
- (c) Designation steel thickness (in mils) exclusive of protective coatings; and,
- (d) A reference number identifying the source coil.

*Example:* “CSSBI-XYZ-33 ABCD” would be a 33 mil thick product manufactured by XYZ company who is a CSSBI Manufacturer Member from a coil that can be traced through the reference number “ABCD”.

Additional information may also be included at the discretion of the manufacturer.

## 4. SECTION GEOMETRIES

4.1 Section geometries are identified by the product designator method described in Section 2.

4.2 Stud, joist, track and U-channel members shall be cold formed to shape from sheet steel with a minimum base steel thickness and inside bend radius as follows:


Designation Thickness (mil)	Minimum Base Steel Thickness (in.)	Base Steel Design Thickness (in.)	Inside Bend Radius (in.)
18	0.0179	0.0188	0.0843
33	0.0329	0.0346	0.0764
43	0.0428	0.0451	0.0712
54	0.0538	0.0566	0.0849
68	0.0677	0.0713	0.1069
97	0.0966	0.1017	0.1525

4.3 Stud and joist lip lengths based on the flange width are as follows:

Section	Flange Width (in.)	Lip Length (in.)
S125	1.250	0.1875
S162	1.625	0.500
S200	2.000	0.625
S250	2.500	0.625
S300	3.000	0.625

## 5. SECTION PROPERTIES

- 5.1 Structural properties are based on Limit States Design (LSD) of the CSA Standard S136-16, *North American Specification for the Design of Cold-Formed Steel Structural Members*, 2016 edition (S136-16).
- 5.2 Steel shall conform to the requirements of S136-16, AISI S220-15 *North American Standard for Cold-Formed Steel Framing - Nonstructural Members* and AISI S240-15 *North American Standard for Cold-Formed Steel Structural Framing*. Products with a design thicknesses less than or equal to 0.0451" shall have a minimum yield strength of 33 ksi and products with a design thicknesses equal to or greater than 0.0566" shall have a minimum yield strength of 50 ksi.
- 5.3 Section properties are computed for the base steel design thicknesses (exclusive of coating) shown in the tables.
- 5.4 When provided, factory punchouts shall be located along the centreline of the webs of the members and shall have a minimum centre-to-centre spacing of 24". Punchouts for members greater than 2.5" deep are a maximum of 1.5" wide by 4.5" in length. Any configuration or combination of holes that fit within the punchout width and length limitations stated above shall be permitted; other punchout configurations and locations not in compliance with the stated limitations must be approved by a design professional.

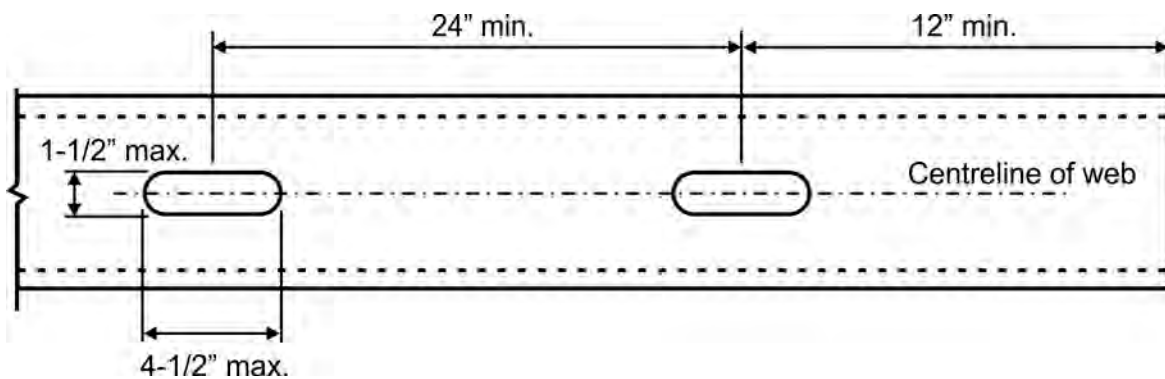

- 5.5 Increase in yield strength from cold work of forming has been included whenever applicable.
- 5.6 The effective moment of inertia for deflection,  $I_{xd}$ , is based on local buckling at an assumed specified live load stress of  $0.6F_y$ . This moment of inertia is only appropriate for checking serviceability limit states.

## 6. SYMBOLS

### Gross Properties


$I_x$	Moment of inertia about x-axis
$I_y$	Moment of inertia about y-axis
$r_x$	Radius of gyration about x-axis
$r_y$	Radius of gyration about y-axis
$V_{rg}$	Factored shear resistance along y-axis of unperforated section

### Effective Properties

$I_{xd}$	Moment of inertia about x-axis for deflection calculations
$M_{rx}$	Factored moment resistance for track, U-channel and furring channel sections based on local buckling
$M_{rxDB}$	Factored moment resistance about x-axis based on distortional buckling, assuming $K_\phi = 0$
$M_{rxLB}$	Factored moment resistance about x-axis based on local buckling
$M_{ryDB}$	Factored moment resistance about y-axis based on distortional buckling with lip in compression
$M_{ryLB}$	Factored moment resistance about y-axis based on local buckling with web/lip in compression
$S_{xe}$	Effective section modulus about x-axis
$V_m$	Factored shear resistance along y-axis of perforated section

### Torsional and other Properties

$\beta$	$1 - (x_o/r_o)^2$
$C_w$	Torsional warping constant
$J$	Saint-Venant torsion constant. The values shown in the tables have been multiplied by 1,000. To obtain the actual values, divide table values by 1,000
$L_u$	Limiting unbraced length below which lateral-torsional buckling is not considered
$m$	Distance from shear centre to mid-plane of web
$r_o$	Polar radius of gyration about shear centre
$x_o$	Distance from shear centre to centroid along principle x-axis

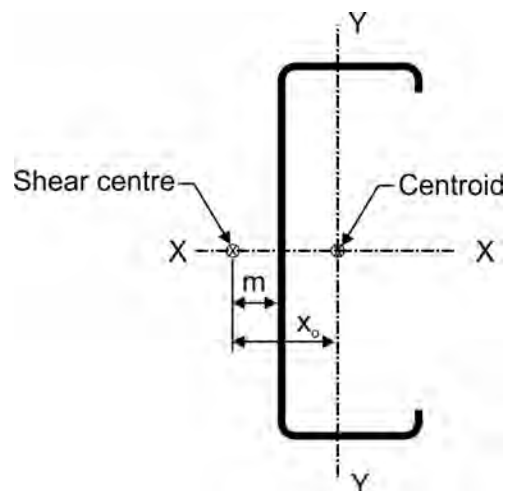

## Web Depth to Thickness Ratio (h/t)

Designation Thickness (mil)	18		33		43		54		68		97	
Design Thickness (in.)	0.0188		0.0346		0.0451		0.0566		0.0713		0.1017	
Section Depth (in.)	h(in.)	h/t	h(in.)	h/t	h(in.)	h/t	h(in.)	h/t	h(in.)	h/t	h(in.)	h/t
1.625	1.42	75.5										
2.50	2.29	122										
3.625	3.42	182	3.40	98.3	3.39	75.2	3.34	59.0	3.27	45.8	3.12	30.6
4	3.79	202 <sup>1</sup>	3.78	109	3.77	83.5	3.72	65.7	3.64	51.1	3.49	34.3
6	5.79	*	5.78	167	5.77	128	5.72	101	5.64	79.2	5.49	54.0
8			7.78	225 <sup>1</sup>	7.77	172	7.72	136	7.64	107	7.49	73.7
10			9.78	*	9.77	217 <sup>1</sup>	9.72	172	9.64	135	9.49	93.3
12			11.8	*	11.8	*	11.7	207 <sup>1</sup>	11.6	163	11.5	113
14			13.8	*	13.8	*	13.7	242 <sup>1</sup>	13.6	191	13.5	133

<sup>1</sup> h/t exceeds 200; \* h/t exceeds 260

## 7. DESIGN EXAMPLES

### 7.1 LOAD BEARING WALL STUDS – Concentric load only

**Given:**

Specified (unfactored) Loads: Axial live load (L) = 4.8 kips/stud  
 Axial dead load (D) = 2.0 kips/stud

Stud height = 14'-0"

Stud spacing = 16" o.c.

Assume studs are braced by bridging only

Select a stud section

**Solution:**

Factored load combination = 1.25D + 1.5L

$C_f = 1.25(2.0) + 1.5(4.8) = 9.70 \text{ kips/stud}$

Try 600S162-68 studs at 16" o.c.

From Combined Axial and Lateral Load table, the limiting factored compressive resistance for 0 psf factored lateral load

$C_r = 10.4 \text{ kips/stud}$

Since  $C_r = 10.4 \text{ kips/stud} > C_f = 9.70 \text{ kips/stud} \therefore \text{OK}$

**Conclusion:**

Use **600S162-68** section spaced at 16" o.c. with 3 bridging lines arranged so that the maximum spacing does not exceed 48" o.c.



## 7.2 LOAD BEARING WALL STUDS – Combined loading

### Given:

Specified (unfactored) Loads:	Axial live load (L)	= 3.6 kips/stud
	Axial dead load (D)	= 1.8 kips/stud
	Wind load (W)	= 25 psf

Stud height = 10'-0"

Stud spacing = 16" o.c.

Deflection limit = L/600

Assume studs are braced by bridging only

Select a stud section

### Solution:

Try 600S162-54 studs at 16" o.c.

#### 1) Dead load only

$$\text{Factored load combination} = 1.4D$$

$$C_f (\text{factored axial load}) = 1.4D = 1.4(1.8) = \underline{2.52 \text{ kips/stud}}$$

From Combined Axial and Lateral Load table, the limiting factored compressive resistance for 0 psf factored lateral load

$$C_r = \underline{8.24 \text{ kips/stud}}$$

$$\text{Since } C_r = \underline{8.24 \text{ kips/stud}} > C_f = \underline{2.52 \text{ kips/stud}} \therefore \text{OK}$$

#### 2) Dead + Wind + Live Load

$$\text{a) Factored load combination \# 1} = 1.25D + 1.5L + 0.4W$$

$$\begin{aligned} W_f (\text{factored wind load}) &= 0.4W \\ &= 0.4(25) = \underline{10.0 \text{ psf}} \\ C_f (\text{factored axial load}) &= 1.25D + 1.5L \\ &= 1.25(1.8) + 1.5(3.6) \\ &= \underline{7.65 \text{ kips/stud}} \end{aligned}$$

From Combined Axial and Lateral Load table, the limiting factored compressive resistance for 10 psf factored lateral load

$$C_r = \underline{7.67 \text{ kips/stud}}$$

$$\text{Since } C_r = \underline{7.67 \text{ kips/stud}} > C_f = \underline{7.65 \text{ kips/stud}} \therefore \text{OK}$$

$$\text{b) Factored load combination \# 2} = 1.25D + 0.5L + 1.4W$$

$$\begin{aligned} W_f (\text{factored wind load}) &= 1.4W \\ &= 1.4(25) = \underline{35.0 \text{ psf}} \\ C_f (\text{factored axial load}) &= 1.25D + 0.5L \\ &= 1.25(1.8) + 0.5(3.6) \\ &= \underline{4.05 \text{ kips/stud}} \end{aligned}$$

From Combined Axial and Lateral Load table, the limiting factored compressive resistance for 30 and 40 psf factored lateral load

$$C_r = \underline{6.57 \text{ kips/stud}} \text{ (for 30 psf)}$$

$$C_r = \underline{6.04 \text{ kips/stud}} \text{ (for 40 psf)}$$

$$\text{By interpolation for 35 psf, } C_r = \underline{6.31 \text{ kips/stud}} > \underline{4.05 \text{ kips/stud}} \therefore \text{OK}$$

#### 3) Web crippling check

From Single Span Curtain Wall Limiting Heights table for a 25 psf specified wind load, web crippling does not control.

**4) Deflection check (L/600)**

From Single Span Curtain Wall Limiting Heights table, the limiting stud height for a specified wind load of 25 psf and a deflection limit of L/600 is 14'-4".

Since 14'-4" > 10'-0" ∴ **OK**

**Conclusion:**

Use **600S162-54** section spaced at 16" o.c. with 2 bridging lines arranged so that the maximum spacing does not exceed 48" o.c.

**7.3 FLOOR JOIST – Single span****Given:**

Specified (unfactored) Loads:	Live load (L)	= 40 psf
	Dead load (D)	= 15 psf

Single span length = 16'-0"

Joist spacing = 16" o.c.

Deflection limit = L/360

Select a joist section

**Solution:**Strength

Factored load combination = 1.25D + 1.5L

$P_f = 1.25(15) + 1.5(40) = 78.8$  psf

Try 800S162-54 joists at 16" o.c.

From Floor Joist Load table, the factored uniformly distributed single span

Strength Resistance = 91 psf

Since 91 psf > 78.8 psf ∴ **OK**

Deflection

From Floor Joist Load table, the specified uniformly distributed single span L/360 deflection load is 44 psf

Since 44 psf > 40 psf ∴ **OK**

**Conclusion:**

Use **800S162-54** section spaced at 16" o.c. Web stiffeners are not required based on an end bearing length of 3.5". If end bearing length is less than 3.5", web crippling must be checked.

**7.4 CURTAIN WALL – Single span****Given:**

Specified (unfactored) wind load = 30 psf

Stud height = 12'-0"

Stud spacing = 24" o.c.

Deflection limit = L/360

Select a stud section

**Solution:**

Try 600S162-43 studs at 24" o.c.

From Single Span Curtain Wall Limiting Heights table under 30 psf specified wind load, the limiting stud height is 12'-4"

Since 12'-4" > 12'-0" ∴ **OK**

**Conclusion:**

Use **600S162-43** section spaced at 24" o.c. Web stiffeners are not required.

**7.5 CURTAIN WALL – Double span**

**Given:**

Specified (unfactored) wind load = 50 psf

Stud height = 10'-0"

Stud spacing = 24" o.c.

Deflection limit = L/360

Select a stud section

**Solution:**

Try 800S162-43 studs at 24" o.c.

From Double Span Curtain Wall Limiting Heights table under 50 psf specified wind load, the limiting stud height is 10'-3"

Since 10'-3" > 10'-0" ∴ **OK**

**Conclusion:**

Use **800S162-43** section spaced at 24" o.c. Web stiffeners are required at end and interior supports.

**7.6 USE OF WEB CRIPPLING DATA TABLE – Single Web Member**

**Given:**

Single web C-section

Depth = 8 in.

Designation thickness = 54 mil; Base Design Thickness, t = 0.0566 in.

Bearing length, N = 3 in.

*Determine the factored end-one-flange (EOF) web crippling resistance.*

**Solution:**

From the Factored Web Crippling Data table for Single Web Members

$$P_{eo1} = 305 \text{ lb}; P_{eo2} = 107 \text{ lb}$$

$$P_{rEOF} = P_{eo1} + P_{eo2} \sqrt{\frac{N}{t}} = 305 + 107 \sqrt{\frac{3}{0.0566}} = \underline{1,084 \text{ lb}}$$

**Conclusion:**

The factored end-one-flange (EOF) web crippling resistance,  $P_{rEOF} = \underline{1,084 \text{ lb}}$ .



Stud Designation	Lip (in.)	Base Design Thickness (in.)	F <sub>y</sub> (ksi)	GROSS							PERFORATED EFFECTIVE									TORSIONAL						L <sub>u</sub> (in.)
				Weight (lb/ft)	Area (in. <sup>2</sup> )	I <sub>x</sub> (in. <sup>4</sup> )	r <sub>x</sub> (in.)	I <sub>y</sub> (in. <sup>4</sup> )	r <sub>y</sub> (in.)	V <sub>rg</sub> (kip)	I <sub>xd</sub> (in. <sup>4</sup> )	S <sub>xe</sub> (in. <sup>3</sup> )	M <sub>rxLB</sub> (k-in.)	M <sub>rxDB</sub> (k-in.)	V <sub>rn</sub> (kip)	M <sub>ryLB</sub> web comp. (k-in.)	M <sub>ryLB</sub> lip comp. (k-in.)	M <sub>ryDB</sub> lip comp. (k-in.)	Jx1000 (in. <sup>4</sup> )	C <sub>w</sub> (in. <sup>6</sup> )	x <sub>o</sub> (in.)	m (in.)	r <sub>o</sub> (in.)	β (in.)		
600S125-33	0.188	0.0346	33	1.01	0.297	1.41	2.18	0.0416	0.375	0.815	1.34	0.369	11.0	8.60	0.815	1.06	1.18	1.13	0.118	0.300	0.608	0.399	2.29	0.930	27.5	
600S125-43	0.188	0.0451	33	1.31	0.385	1.82	2.17	0.0526	0.370	1.81	1.79	0.554	16.5	12.7	1.58	1.39	1.49	1.53	0.261	0.378	0.598	0.393	2.28	0.931	27.3	
600S125-54	0.188	0.0566	50	1.63	0.479	2.24	2.16	0.0626	0.362	3.61	2.22	0.672	30.3	22.9	2.49	2.52	2.69	2.76	0.511	0.457	0.586	0.386	2.27	0.933	21.9	
600S162-33	0.500	0.0346	33	1.17	0.344	1.79	2.28	0.116	0.581	0.815	1.79	0.577	17.1	13.7	0.815	2.41	2.77	2.85	0.137	0.861	1.07	0.677	2.59	0.828	41.1	
600S162-43	0.500	0.0451	33	1.52	0.447	2.32	2.28	0.148	0.576	1.81	2.32	0.767	25.1*	19.5	1.58	3.21	3.54	3.64	0.303	1.10	1.06	0.670	2.58	0.830	38.9	
600S162-54	0.500	0.0566	50	1.89	0.556	2.86	2.27	0.181	0.570	3.61	2.86	0.915	45.6*	34.6	2.49	5.93	6.53	6.70	0.594	1.34	1.05	0.663	2.56	0.833	31.3	
600S162-68	0.500	0.0713	50	2.36	0.693	3.53	2.26	0.218	0.561	6.84	3.52	1.16	59.3*	46.7	3.68	7.40	7.86	8.09	1.17	1.63	1.03	0.655	2.54	0.835	30.8	
600S162-97	0.500	0.1017	50	3.29	0.966	4.80	2.23	0.283	0.542	13.4	4.80	1.60	85.3*	71.4	4.87	10.0	10.2	10.5	3.33	2.15	1.00	0.636	2.50	0.841	29.7	
600S200-33	0.625	0.0346	33	1.29	0.379	2.08	2.34	0.209	0.743	0.815	2.04	0.621	18.4	15.7	0.815	3.63	4.06	3.97	0.151	1.59	1.46	0.901	2.86	0.740	51.6	
600S200-43	0.625	0.0451	33	1.67	0.492	2.68	2.34	0.268	0.739	1.81	2.68	0.872	25.9	22.3	1.58	4.84	5.43	5.54	0.334	2.03	1.45	0.894	2.84	0.742	51.4	
600S200-54	0.625	0.0566	50	2.09	0.613	3.32	2.33	0.329	0.732	3.61	3.32	1.01	45.7	39.5	2.49	9.01	10.1	9.87	0.655	2.49	1.43	0.887	2.83	0.744	41.5	
600S200-68	0.625	0.0713	50	2.60	0.764	4.10	2.32	0.400	0.723	6.84	4.10	1.32	65.7*	53.3	3.68	11.4	12.2	12.6	1.30	3.05	1.42	0.878	2.81	0.746	39.3	
600S200-97	0.625	0.1017	50	3.63	1.07	5.61	2.29	0.530	0.705	13.4	5.61	1.87	97.0*	82.6	4.87	15.7	16.2	16.7	3.68	4.08	1.38	0.859	2.77	0.752	38.3	
600S250-33	0.625	0.0346	33	1.41	0.414	2.38	2.40	0.356	0.928	0.815	2.26	0.649	19.3	16.4	0.815	5.00	5.67	4.84	0.165	2.67	1.89	1.14	3.19	0.651	62.5	
600S250-43	0.625	0.0451	33	1.83	0.537	3.08	2.40	0.458	0.923	1.81	3.06	0.918	27.3	23.6	1.58	6.67	7.56	6.87	0.364	3.41	1.87	1.14	3.18	0.652	62.3	
600S250-54	0.625	0.0566	50	2.28	0.670	3.82	2.39	0.562	0.917	3.61	3.66	1.07	48.1	41.5	2.49	12.5	14.1	12.2	0.715	4.19	1.86	1.13	3.16	0.654	50.4	
600S250-68	0.625	0.0713	50	2.84	0.836	4.73	2.38	0.688	0.908	6.84	4.67	1.39	62.3	56.3	3.68	15.8	17.2	16.3	1.42	5.15	1.84	1.12	3.14	0.657	50.3	
600S250-97	0.625	0.1017	50	3.98	1.17	6.50	2.36	0.923	0.889	13.4	6.50	2.06	104*	88.7	4.87	22.2	23.0	23.8	4.03	6.95	1.80	1.10	3.10	0.661	47.2	
600S300-33	0.625	0.0346	33	1.53	0.448	2.69	2.45	0.552	1.11	0.815	2.45	0.663	19.7	16.8	0.815	6.53	7.48	5.67	0.179	4.09	2.33	1.39	3.56	0.572	73.0	
600S300-43	0.625	0.0451	33	1.98	0.582	3.48	2.45	0.711	1.11	1.81	3.30	0.944	28.0	24.4	1.58	8.73	10.0	8.13	0.395	5.24	2.31	1.38	3.54	0.574	72.8	
600S300-54	0.625	0.0566	50	2.47	0.726	4.32	2.44	0.875	1.10	3.61	3.94	1.11	49.8	42.9	2.49	16.4	18.6	14.3	0.775	6.45	2.30	1.37	3.53	0.575	59.0	
600S300-68	0.625	0.0713	50	3.09	0.907	5.35	2.43	1.08	1.09	6.84	5.06	1.45	65.0	58.5	3.68	20.8	22.8	19.4	1.54	7.94	2.28	1.36	3.51	0.577	58.9	
600S300-97	0.625	0.1017	50	4.32	1.27	7.38	2.41	1.45	1.07	13.4	7.25	2.25	101	93.2	4.87	29.6	30.7	30.3	4.38	10.8	2.24	1.34	3.46	0.581	58.8	
800S162-43	0.500	0.0451	33	1.83	0.537	4.63	2.94	0.160	0.546	1.34	4.48	1.02	30.3	26.5	1.34	3.23	3.66	3.72	0.364	2.08	0.926	0.601	3.13	0.912	39.8	
800S162-54	0.500	0.0566	50	2.28	0.670	5.74	2.93	0.194	0.539	2.67	5.57	1.23	55.3	47.1	2.67	5.97	6.75	6.85	0.715	2.54	0.914	0.594	3.11	0.914	32.1	
800S162-68	0.500	0.0713	50	2.84	0.836	7.09	2.91	0.235	0.530	5.39	7.05	1.66	74.8	64.5	4.30	7.47	8.14	8.27	1.42	3.09	0.898	0.586	3.09	0.916	31.8	
800S162-97	0.500	0.1017	50	3.98	1.17	9.72	2.88	0.305	0.511	13.9	9.71	2.43	109	103	7.60	10.2	10.6	10.8	4.03	4.11	0.866	0.568	3.05	0.920	31.3	
800S200-43	0.625	0.0451	33	1.98	0.582	5.30	3.02	0.292	0.708	1.34	5.30	1.29	38.4	30.5	1.34	4.87	5.63	5.72	0.395	3.80	1.28	0.811	3.30	0.855	50.3	
800S200-54	0.625	0.0566	50	2.47	0.726	6.57	3.01	0.357	0.701	2.67	6.57	1.50	67.4	54.1	2.67	9.06	10.4	10.2	0.775	4.66	1.27	0.804	3.34	0.856	40.6	
800S200-68	0.625	0.0713	50	3.09	0.907	8.14	3.00	0.435	0.692	5.39	8.14	1.96	98.0*	73.8	4.30	11.4	12.7	12.9	1.54	5.71	1.25	0.796	3.32	0.859	38.4	
800S200-97	0.625	0.1017	50	4.32	1.27	11.2	2.97	0.576	0.674	13.9	11.2	2.80	145*	117	7.60	16.0	16.8	17.1	4.38	7.68	1.21	0.777	3.28	0.863	37.2	
800S250-43	0.625	0.0451	33	2.13	0.627	6.02	3.10	0.500	0.893	1.34	5.98	1.31	39.0	32.1	1.34	6.71	7.88	7.09	0.425	6.37	1.68	1.04	3.63	0.787	61.5	
800S250-54	0.625	0.0566	50	2.66	0.783	7.47	3.09	0.614	0.886	2.67	7.17	1.52	68.6	56.7	2.67	12.5	14.7	12.6	0.836	7.85	1.66	1.04	3.62	0.789	49.7	
800S250-68	0.625	0.0713	50	3.33	0.978	9.26	3.08	0.752	0.877	5.39	9.14	2.06	92.6	77.7	4.30	15.9	17.9	16.8	1.66	9.65	1.64	1.03	3.60	0.791	49.5	
800S250-97	0.625	0.1017	50	4.67	1.37	12.8	3.05	1.01	0.857	13.9	12.8	3.05	154*	125	7.60	22.6	24.0	24.5	4.73	13.1	1.61	1.01	3.56	0.796	46.3	
800S300-43	0.625	0.0451	33	2.29	0.672	6.73	3.16	0.779	1.08	1.34	6.40	1.31	39.0	33.0	1.34	8.77	10.4	8.33	0.456	9.79	2.09	1.28	3.94	0.719	72.3	
800S300-54	0.625	0.0566	50	2.86	0.839	8.36	3.16	0.959	1.07	2.67	7.66	1.53	69.0	58.3	2.67	16.5	19.4	14.7	0.896	12.1	2.07	1.27	3.92	0.721	58.5	
800S300-68	0.625	0.0713	50	3.57	1.05	10.4	3.15	1.18	1.06	5.39	9.84	2.14	96.5	80.3	4.30	21.0	23.9	20.0	1.78	14.9	2.06	1.26	3.90	0.723	58.3	
800S300-97	0.625	0.1017	50	5.02	1.47	14.4	3.12	1.60	1.04	13.9	14.1	3.30	149	130	7.60	30.0	32.2	31.3	5.08	20.3	2.02	1.24	3.86	0.727	58.0	

\* Cold work of forming applies

# Joist Section Properties

## Table Notes

- 1 Inside bend radius values are shown in the General Notes.
- 2 Gross section properties are based on the full-unreduced cross section of the joist sections, away from the punchouts.
- 3 The factored moment resistance for design is based on the lesser of local and distortional buckling. Distortional buckling is based on an assumed rotational stiffness of  $K_\phi = 0$ .

Joist Designation	Lip (in.)	Base Design Thickness (in.)	F <sub>y</sub> (ksi)	GROSS							PERFORATED EFFECTIVE							TORSIONAL						L <sub>u</sub> (in.)	
				Weight (lb/ft)	Area (in. <sup>2</sup> )	I <sub>x</sub> (in. <sup>4</sup> )	r <sub>x</sub> (in.)	I <sub>y</sub> (in. <sup>4</sup> )	r <sub>y</sub> (in.)	V <sub>rg</sub> (kip)	I <sub>xd</sub> (in. <sup>4</sup> )	S <sub>xe</sub> (in. <sup>3</sup> )	M <sub>rxLB</sub> (k-in.)	M <sub>rxDB</sub> (k-in.)	V <sub>rn</sub> (kip)	M <sub>ryLB</sub> web comp. (k-in.)	M <sub>ryLB</sub> lip comp. (k-in.)	M <sub>ryDB</sub> lip comp. (k-in.)	Jx1000 (in. <sup>4</sup> )	C <sub>w</sub> (in. <sup>6</sup> )	x <sub>o</sub> (in.)	m (in.)	r <sub>o</sub> (in.)		β
600S162-43	0.500	0.0451	33	1.52	0.447	2.32	2.28	0.148	0.576	1.81	2.32	0.767	25.1*	19.5	1.58	3.21	3.54	3.64	0.303	1.10	1.06	0.670	2.58	0.830	39.0
600S162-54	0.500	0.0566	50	1.89	0.556	2.86	2.27	0.181	0.570	3.61	2.86	0.915	45.6*	34.6	2.49	5.93	6.53	6.70	0.594	1.34	1.05	0.663	2.56	0.833	31.4
600S162-68	0.500	0.0713	50	2.36	0.693	3.53	2.26	0.218	0.561	6.84	3.53	1.16	59.3*	46.7	3.68	7.40	7.86	8.09	1.17	1.63	1.03	0.655	2.54	0.835	30.8
600S162-97	0.500	0.1017	50	3.29	0.966	4.80	2.23	0.283	0.542	13.4	4.80	1.60	85.3*	71.4	4.87	10.0	10.2	10.5	3.33	2.15	1.00	0.636	2.50	0.841	29.8
600S200-43	0.625	0.0451	33	1.67	0.492	2.68	2.34	0.268	0.739	1.81	2.68	0.872	25.9	22.3	1.58	4.84	5.43	5.54	0.334	2.03	1.45	0.894	2.84	0.742	51.4
600S200-54	0.625	0.0566	50	2.09	0.613	3.32	2.33	0.329	0.732	3.61	3.32	1.02	45.7	39.5	2.49	9.01	10.1	9.87	0.655	2.49	1.43	0.887	2.83	0.744	41.6
600S200-68	0.625	0.0713	50	2.60	0.764	4.10	2.32	0.400	0.723	6.84	4.10	1.32	65.7*	53.3	3.68	11.4	12.2	12.6	1.30	3.05	1.42	0.878	2.81	0.746	39.3
600S200-97	0.625	0.1017	50	3.63	1.07	5.61	2.29	0.530	0.705	13.4	5.61	1.87	97.0*	82.6	4.87	15.8	16.2	16.7	3.68	4.08	1.38	0.859	2.77	0.752	38.3
600S250-43	0.625	0.0451	33	1.83	0.537	3.08	2.40	0.458	0.923	1.81	3.06	0.918	27.3	23.6	1.58	6.67	7.56	6.87	0.364	3.41	1.87	1.14	3.18	0.652	62.3
600S250-54	0.625	0.0566	50	2.28	0.670	3.82	2.39	0.562	0.917	3.61	3.66	1.07	48.1	41.5	2.49	12.5	14.1	12.2	0.715	4.19	1.86	1.13	3.16	0.654	50.4
600S250-68	0.625	0.0713	50	2.84	0.836	4.73	2.38	0.688	0.908	6.84	4.67	1.39	62.3	56.3	3.68	15.8	17.2	16.3	1.42	5.15	1.84	1.12	3.14	0.657	50.3
600S250-97	0.625	0.1017	50	3.98	1.17	6.50	2.36	0.923	0.889	13.4	6.50	2.06	104*	88.7	4.87	22.2	23.0	23.8	4.03	6.95	1.80	1.10	3.10	0.661	47.2
600S300-43	0.625	0.0451	33	1.98	0.582	3.48	2.45	0.711	1.11	1.81	3.30	0.944	28.0	24.4	1.58	8.73	10.0	8.13	0.395	5.24	2.31	1.38	3.54	0.574	72.8
600S300-54	0.625	0.0566	50	2.47	0.726	4.32	2.44	0.875	1.10	3.61	3.94	1.11	49.8	42.9	2.49	16.4	18.6	14.3	0.775	6.45	2.30	1.37	3.53	0.575	59.0
600S300-68	0.625	0.0713	50	3.09	0.907	5.35	2.43	1.08	1.09	6.84	5.06	1.45	65.0	58.5	3.68	20.8	22.8	19.4	1.54	7.94	2.28	1.36	3.51	0.577	58.9
600S300-97	0.625	0.1017	50	4.32	1.27	7.38	2.41	1.45	1.07	13.4	7.25	2.25	101	93.2	4.87	29.6	30.7	30.3	4.38	10.8	2.24	1.34	3.46	0.581	58.8
800S162-43	0.500	0.0451	33	1.83	0.537	4.64	2.94	0.160	0.546	1.34	4.48	1.02	30.3	26.5	1.34	3.23	3.66	3.72	0.364	2.08	0.926	0.601	3.13	0.912	39.8
800S162-54	0.500	0.0566	50	2.28	0.670	5.74	2.93	0.194	0.539	2.67	5.57	1.23	55.3	47.1	2.67	5.97	6.75	6.85	0.715	2.54	0.914	0.594	3.11	0.914	32.1
800S162-68	0.500	0.0713	50	2.84	0.836	7.09	2.91	0.235	0.530	5.39	7.05	1.66	74.8	64.5	4.30	7.47	8.14	8.27	1.42	3.09	0.898	0.586	3.09	0.916	31.9
800S162-97	0.500	0.1017	50	3.98	1.17	9.72	2.88	0.305	0.511	13.9	9.71	2.43	109	103	7.60	10.2	10.6	10.8	4.03	4.11	0.866	0.568	3.05	0.920	31.4
800S200-43	0.625	0.0451	33	1.98	0.582	5.30	3.02	0.292	0.708	1.34	5.30	1.29	38.4	30.5	1.34	4.87	5.63	5.72	0.395	3.80	1.28	0.811	3.35	0.855	50.3
800S200-54	0.625	0.0566	50	2.47	0.726	6.57	3.01	0.357	0.701	2.67	6.57	1.50	67.4	54.1	2.67	9.06	10.4	10.2	0.775	4.66	1.27	0.804	3.34	0.856	40.7
800S200-68	0.625	0.0713	50	3.09	0.907	8.14	3.00	0.435	0.692	5.39	8.14	1.96	98.0*	73.8	4.30	11.5	12.7	12.9	1.54	5.71	1.25	0.796	3.32	0.859	38.4
800S200-97	0.625	0.1017	50	4.32	1.27	11.2	2.97	0.576	0.674	13.9	11.2	2.80	145*	117	7.60	16.0	16.8	17.1	4.38	7.68	1.21	0.777	3.28	0.863	37.2
800S250-43	0.625	0.0451	33	2.13	0.627	6.02	3.10	0.500	0.893	1.34	5.98	1.31	39.0	32.1	1.34	6.71	7.88	7.09	0.425	6.37	1.68	1.04	3.63	0.787	61.5
800S250-54	0.625	0.0566	50	2.66	0.783	7.47	3.09	0.614	0.886	2.67	7.17	1.52	68.6	56.7	2.67	12.5	14.7	12.6	0.836	7.85	1.66	1.04	3.62	0.789	49.8
800S250-68	0.625	0.0713	50	3.33	0.978	9.26	3.08	0.752	0.877	5.39	9.14	2.06	92.6	77.7	4.30	15.9	17.9	16.8	1.66	9.65	1.64	1.03	3.60	0.791	49.6
800S250-97	0.625	0.1017	50	4.67	1.37	12.8	3.05	1.01	0.857	13.9	12.8	3.05	154*	125	7.60	22.6	24.0	24.5	4.73	13.1	1.61	1.01	3.56	0.796	46.4
800S300-43	0.625	0.0451	33	2.29	0.672	6.73	3.16	0.779	1.08	1.34	6.40	1.31	39.0	33.0	1.34	8.77	10.4	8.33	0.456	9.79	2.09	1.28	3.94	0.719	72.3
800S300-54	0.625	0.0566	50	2.86	0.839	8.36	3.16	0.959	1.07	2.67	7.66	1.53	69.0	58.3	2.67	16.5	19.4	14.7	0.896	12.1	2.07	1.27	3.92	0.721	58.5
800S300-68	0.625	0.0713	50	3.57	1.05	10.4	3.15	1.18	1.06	5.39	9.84	2.14	96.5	80.3	4.30	21.0	23.9	20.0	1.78	14.9	2.06	1.26	3.90	0.723	58.3
800S300-97	0.625	0.1017	50	5.02	1.47	14.4	3.12	1.60	1.04	13.9	14.1	3.30	149	130	7.60	30.0	32.2	31.3	5.08	20.3	2.02	1.24	3.86	0.727	58.0

\* Cold work of forming applies

Bailey Metal Products, Dass Metal Products, DCI Metal Corp., EB Metal Inc., Imperial Building Products, Managresse, Groupe UP, Trebor Building Products Ltd.

Joist Designation	Lip (in.)	Base Design Thickness (in.)	F <sub>y</sub> (ksi)	GROSS							PERFORATED EFFECTIVE									TORSIONAL						L <sub>u</sub> (in.)
				Weight (lb/ft)	Area (in. <sup>2</sup> )	I <sub>x</sub> (in. <sup>4</sup> )	r <sub>x</sub> (in.)	I <sub>y</sub> (in. <sup>4</sup> )	r <sub>y</sub> (in.)	V <sub>rg</sub> (kip)	I <sub>xd</sub> (in. <sup>4</sup> )	S <sub>xe</sub> (in. <sup>3</sup> )	M <sub>rxLB</sub> (k-in.)	M <sub>rxDB</sub> (k-in.)	V <sub>m</sub> (kip)	M <sub>ryLB</sub> web comp. (k-in.)	M <sub>ryLB</sub> lip comp. (k-in.)	M <sub>ryDB</sub> lip comp. (k-in.)	Jx1000 (in. <sup>4</sup> )	C <sub>w</sub> (in. <sup>9</sup> )	x <sub>o</sub> (in.)	m (in.)	r <sub>o</sub> (in.)	β		
1000S162-54	0.500	0.0566	50	2.66	0.783	9.95	3.57	0.204	0.511	2.12	9.31	1.57	71	58.2	2.12	5.99	6.88	6.95	0.836	4.20	0.812	0.538	3.69	0.952	31.3	
1000S162-68	0.500	0.0713	50	3.33	0.978	12.3	3.55	0.247	0.502	4.27	11.9	2.15	96.9	80.9	4.27	7.50	8.31	8.39	1.66	5.12	0.798	0.531	3.67	0.953	31.0	
1000S162-97	0.500	0.1017	50	4.67	1.37	17.0	3.52	0.320	0.483	12.6	17.0	3.27	147	132	9.17	10.2	10.8	10.9	4.73	6.83	0.768	0.514	3.63	0.955	30.4	
1000S200-54	0.625	0.0566	50	2.86	0.839	11.3	3.67	0.378	0.671	2.12	10.6	1.70	76.7	67.7	2.12	9.09	10.7	10.4	0.896	7.67	1.14	0.737	3.90	0.915	39.8	
1000S200-68	0.625	0.0713	50	3.57	1.05	14.0	3.65	0.460	0.662	4.27	13.6	2.42	109	93.5	4.27	11.5	13.0	13.2	1.78	9.40	1.12	0.729	3.88	0.917	39.6	
1000S200-97	0.625	0.1017	50	5.02	1.47	19.3	3.62	0.610	0.643	12.6	19.3	3.74	168	151	9.17	16.1	17.2	17.4	5.08	12.7	1.09	0.711	3.84	0.920	39.0	
1000S250-54	0.625	0.0566	50	3.05	0.896	12.7	3.76	0.653	0.854	2.12	12.2	1.88	84.5	71.5	2.12	12.6	15.1	12.9	0.957	12.9	1.51	0.958	4.14	0.868	49.1	
1000S250-68	0.625	0.0713	50	3.81	1.12	15.8	3.75	0.799	0.844	4.27	15.6	2.77	124	98.8	4.27	16.0	18.4	17.2	1.90	15.9	1.49	0.950	4.12	0.870	48.8	
1000S250-97	0.625	0.1017	50	5.36	1.58	21.8	3.72	1.07	0.825	12.6	21.8	4.18	211*	161	9.17	22.7	24.7	25.0	5.43	21.6	1.45	0.932	4.08	0.873	45.6	
1000S300-54	0.625	0.0566	50	3.24	0.953	14.1	3.85	1.02	1.04	2.12	12.8	1.90	85.5	73.6	2.12	16.5	20.0	15.1	1.02	19.9	1.89	1.19	4.41	0.816	58.0	
1000S300-68	0.625	0.0713	50	4.06	1.19	17.5	3.83	1.26	1.03	4.27	16.6	2.80	126	102	4.27	21.1	24.6	20.5	2.02	24.6	1.87	1.18	4.39	0.818	57.8	
1000S300-97	0.625	0.1017	50	5.71	1.68	24.3	3.81	1.70	1.01	12.6	23.9	4.50	202	167	9.17	30.2	33.2	32.1	5.78	33.6	1.84	1.16	4.35	0.821	57.4	
1200S162-68	0.500	0.0713	50	3.81	1.12	19.5	4.17	0.255	0.477	3.54	18.3	2.64	119	95.2	3.54	7.52	8.42	8.48	1.90	7.74	0.719	0.485	4.26	0.972	30.2	
1200S162-97	0.500	0.1017	50	5.36	1.58	27.0	4.14	0.332	0.459	10.4	26.6	4.09	184	159	9.47	10.3	11.0	11.0	5.43	10.3	0.691	0.470	4.22	0.973	29.5	
1200S200-68	0.625	0.0713	50	4.06	1.19	22.0	4.29	0.479	0.634	3.54	20.7	2.96	133	111	3.54	11.5	13.2	13.3	2.02	14.2	1.02	0.673	4.46	0.948	38.7	
1200S200-97	0.625	0.1017	50	5.71	1.68	30.4	4.26	0.635	0.615	10.4	30.1	4.66	210	184	9.47	16.1	17.5	17.7	5.78	19.1	0.987	0.656	4.42	0.950	38.1	
1200S250-68	0.625	0.0713	50	4.30	1.26	24.5	4.40	0.836	0.813	3.54	22.9	3.01	135	119	3.54	16.0	18.8	17.5	2.14	24.0	1.36	0.884	4.68	0.915	48.1	
1200S250-97	0.625	0.1017	50	6.05	1.78	34.0	4.37	1.12	0.794	10.4	33.7	5.04	227	196	9.47	22.8	25.2	25.4	6.13	32.7	1.33	0.867	4.64	0.918	47.5	
1200S300-68	0.625	0.0713	50	4.54	1.33	27.0	4.50	1.32	0.994	3.54	25.7	3.32	149	123	3.54	21.1	25.1	20.9	2.26	37.1	1.73	1.10	4.92	0.877	57.2	
1200S300-97	0.625	0.1017	50	6.40	1.88	37.6	4.47	1.79	0.975	10.4	37.0	5.83	262	205	9.47	30.3	33.9	32.7	6.48	50.9	1.69	1.09	4.88	0.880	56.7	
1400S162-68	0.500	0.0713	50	4.30	1.26	29.0	4.79	0.262	0.456	3.02	26.1	3.13	141	107	3.02	7.53	8.49	8.54	2.14	11.0	0.654	0.447	4.85	0.982	29.4	
1400S162-97	0.500	0.1017	50	6.05	1.78	40.1	4.75	0.341	0.438	8.86	38.6	4.91	221	183	8.86	10.3	11.1	11.1	6.13	14.7	0.628	0.433	4.81	0.983	28.7	
1400S200-68	0.625	0.0713	50	4.54	1.33	32.3	4.92	0.494	0.608	3.02	29.5	3.50	158	127	3.02	11.5	13.3	13.4	2.26	20.1	0.932	0.625	5.04	0.966	37.9	
1400S200-97	0.625	0.1017	50	6.40	1.88	44.9	4.88	0.655	0.590	8.86	43.4	5.58	251	213	8.86	16.2	17.7	17.8	6.48	27.2	0.904	0.609	5.00	0.967	37.3	
1400S250-68	0.625	0.0713	50	4.78	1.41	35.8	5.04	0.865	0.784	3.02	32.5	3.55	160	137	3.02	16.1	19.0	17.6	2.38	34.1	1.26	0.827	5.26	0.943	47.3	
1400S250-97	0.625	0.1017	50	6.75	1.98	49.8	5.01	1.16	0.765	8.86	48.3	6.01	270	229	8.86	22.9	25.5	25.7	6.83	46.5	1.23	0.811	5.22	0.945	46.7	
1400S300-68	0.625	0.0713	50	5.03	1.48	39.2	5.15	1.37	0.963	3.02	34.3	3.65	164	143	3.02	21.2	25.5	21.2	2.50	52.8	1.60	1.04	5.48	0.915	56.5	
1400S300-97	0.625	0.1017	50	7.09	2.08	54.7	5.12	1.85	0.943	8.86	52.2	6.37	287	240	8.86	30.4	34.4	33.1	7.19	72.4	1.57	1.02	5.44	0.917	55.9	

\* Cold work of forming applies

## Track Section Properties

### Table Notes

- 1 Track web depths are equal to the nominal stud depth plus two times the design thickness plus the inside bend radius.
- 2 If present, hems are ignored.

Track Designation	Base Design Thickness (in.)	F <sub>y</sub> (ksi)	GROSS							EFFECTIVE			TORSIONAL						
			Weight (lb/ft)	Area (in. <sup>2</sup> )	I <sub>x</sub> (in. <sup>4</sup> )	r <sub>x</sub> (in.)	I <sub>y</sub> (in. <sup>4</sup> )	r <sub>y</sub> (in.)	V <sub>rg</sub> (kip)	I <sub>xd</sub> (in. <sup>4</sup> )	S <sub>xe</sub> (in. <sup>3</sup> )	M <sub>rx</sub> (k-in.)	Jx1000 (in. <sup>4</sup> )	C <sub>w</sub> (in. <sup>6</sup> )	x <sub>o</sub> (in.)	m (in.)	r <sub>o</sub> (in.)	β	L <sub>u</sub> (in.)
162T125-18	0.0188	33	0.264	0.0776	0.0417	0.733	0.0131	0.411	0.386	0.0292	0.0252	0.747	0.00915	0.00699	0.876	0.503	1.21	0.479	25.4
250T125-18	0.0188	33	0.320	0.0941	0.104	1.05	0.0150	0.400	0.313	0.0766	0.0443	1.32	0.0111	0.0180	0.767	0.460	1.36	0.682	25.7
362T125-18	0.0188	33	0.392	0.115	0.238	1.44	0.0167	0.380	0.213	0.176	0.0636	1.89	0.0136	0.0416	0.665	0.413	1.63	0.833	25.7
362T125-33	0.0346	33	0.721	0.212	0.438	1.44	0.0301	0.377	1.31	0.381	0.174	5.17	0.0845	0.0756	0.658	0.409	1.63	0.836	25.7
362T125-43	0.0451	33	0.939	0.276	0.571	1.44	0.0388	0.375	2.22	0.525	0.245	7.27	0.187	0.0978	0.654	0.407	1.62	0.838	25.7
362T125-54	0.0566	50	1.18	0.346	0.723	1.45	0.0481	0.373	4.31	0.671	0.312	14.0	0.369	0.123	0.648	0.404	1.63	0.841	20.9
362T125-68	0.0713	50	1.48	0.436	0.921	1.45	0.0597	0.370	6.02	0.901	0.427	19.2	0.738	0.156	0.641	0.399	1.63	0.846	21.0
362T125-97	0.1017	50	2.11	0.621	1.34	1.47	0.0822	0.364	8.48	1.34	0.675	30.4	2.14	0.226	0.626	0.390	1.64	0.854	21.4
362T150-33	0.0346	33	0.780	0.229	0.499	1.48	0.0499	0.467	1.31	0.409	0.180	5.36	0.0914	0.124	0.854	0.522	1.77	0.766	30.9
362T150-43	0.0451	33	1.02	0.298	0.650	1.48	0.0644	0.465	2.23	0.568	0.255	7.58	0.202	0.160	0.850	0.519	1.77	0.768	31.0
362T150-54	0.0566	50	1.27	0.374	0.823	1.48	0.0801	0.463	4.32	0.726	0.325	14.7	0.400	0.202	0.844	0.516	1.77	0.772	25.2
362T150-68	0.0713	50	1.60	0.471	1.05	1.49	0.100	0.460	6.02	0.982	0.449	20.2	0.799	0.257	0.836	0.511	1.77	0.777	25.3
362T150-97	0.1017	50	2.29	0.672	1.54	1.51	0.138	0.453	8.48	1.54	0.733	33.0	2.32	0.374	0.820	0.501	1.78	0.787	25.8
362T200-33	0.0346	33	0.897	0.264	0.619	1.53	0.110	0.645	1.31	0.458	0.190	5.65	0.105	0.269	1.27	0.754	2.09	0.631	41.0
362T200-43	0.0451	33	1.17	0.343	0.808	1.53	0.142	0.643	2.23	0.640	0.270	8.03	0.233	0.350	1.27	0.752	2.09	0.633	41.1
362T200-54	0.0566	50	1.47	0.431	1.02	1.54	0.177	0.641	4.32	0.820	0.345	15.5	0.460	0.442	1.26	0.748	2.09	0.638	33.4
362T200-68	0.0713	50	1.85	0.543	1.31	1.55	0.221	0.638	6.02	1.12	0.480	21.6	0.919	0.564	1.25	0.743	2.09	0.643	33.6
362T200-97	0.1017	50	2.63	0.773	1.92	1.58	0.308	0.632	8.48	1.82	0.804	36.2	2.67	0.825	1.23	0.732	2.10	0.655	34.3
362T300-33	0.0346	33	1.13	0.333	0.861	1.61	0.327	0.992	1.31	0.534	0.197	5.85	0.133	0.811	2.16	1.23	2.87	0.434	60.1
362T300-43	0.0451	33	1.48	0.434	1.12	1.61	0.425	0.990	2.22	0.753	0.290	8.61	0.294	1.05	2.15	1.23	2.86	0.435	60.4
362T300-54	0.0566	50	1.85	0.544	1.43	1.62	0.531	0.988	4.31	0.966	0.371	16.7	0.581	1.34	2.15	1.23	2.86	0.439	49.1
362T300-68	0.0713	50	2.33	0.685	1.82	1.63	0.665	0.985	6.02	1.34	0.519	23.4	1.16	1.71	2.14	1.22	2.86	0.443	49.5
362T300-97	0.1017	50	3.32	0.977	2.68	1.66	0.937	0.979	8.48	2.22	0.886	39.9	3.37	2.52	2.12	1.21	2.86	0.453	50.4
400T125-18	0.0188	33	0.416	0.122	0.298	1.56	0.0171	0.374	0.193	0.216	0.0701	2.08	0.0144	0.0520	0.637	0.400	1.73	0.864	25.6
400T125-33	0.0346	33	0.765	0.225	0.549	1.56	0.0309	0.371	1.20	0.480	0.201	5.97	0.0897	0.0946	0.630	0.396	1.73	0.867	25.6
400T125-43	0.0451	33	1.00	0.293	0.716	1.56	0.0398	0.369	2.22	0.660	0.282	8.37	0.198	0.122	0.626	0.394	1.72	0.868	25.6
400T125-54	0.0566	50	1.25	0.367	0.904	1.57	0.0493	0.367	4.31	0.842	0.359	16.1	0.392	0.154	0.621	0.390	1.73	0.871	20.8
400T125-68	0.0713	50	1.57	0.462	1.15	1.58	0.0611	0.364	6.66	1.13	0.488	22.0	0.783	0.194	0.614	0.386	1.73	0.874	20.9
400T125-97	0.1017	50	2.24	0.659	1.67	1.59	0.0842	0.358	9.39	1.67	0.768	34.6	2.27	0.280	0.600	0.377	1.74	0.881	21.1
400T150-33	0.0346	33	0.824	0.242	0.622	1.60	0.0513	0.460	1.20	0.514	0.208	6.19	0.0966	0.155	0.821	0.507	1.86	0.805	30.8
400T150-43	0.0451	33	1.07	0.315	0.811	1.60	0.0662	0.458	2.23	0.711	0.293	8.71	0.214	0.200	0.817	0.504	1.86	0.807	30.9
400T150-54	0.0566	50	1.35	0.396	1.03	1.61	0.0822	0.456	4.32	0.909	0.374	16.8	0.422	0.252	0.811	0.501	1.86	0.810	25.1
400T150-68	0.0713	50	1.70	0.498	1.31	1.62	0.102	0.453	6.66	1.23	0.513	23.1	0.844	0.320	0.804	0.496	1.86	0.814	25.2
400T150-97	0.1017	50	2.42	0.710	1.90	1.64	0.142	0.447	9.39	1.90	0.832	37.5	2.45	0.463	0.788	0.487	1.87	0.823	25.6



Track Designation	Base Design Thickness (in.)	F <sub>y</sub> (ksi)	GROSS							EFFECTIVE			TORSIONAL						L <sub>u</sub> (in.)
			Weight (lb/ft)	Area (in. <sup>2</sup> )	I <sub>x</sub> (in. <sup>4</sup> )	r <sub>x</sub> (in.)	I <sub>y</sub> (in. <sup>4</sup> )	r <sub>y</sub> (in.)	V <sub>rg</sub> (kip)	I <sub>xd</sub> (in. <sup>4</sup> )	S <sub>xe</sub> (in. <sup>3</sup> )	M <sub>rx</sub> (k-in.)	Jx1000 (in. <sup>4</sup> )	C <sub>w</sub> (in. <sup>6</sup> )	x <sub>o</sub> (in.)	m (in.)	r <sub>o</sub> (in.)	β	
400T200-33	0.0346	33	0.941	0.277	0.768	1.67	0.113	0.639	1.20	0.574	0.220	6.53	0.110	0.336	1.23	0.737	2.17	0.678	41.0
400T200-43	0.0451	33	1.23	0.360	1.00	1.67	0.146	0.637	2.23	0.800	0.311	9.23	0.244	0.437	1.22	0.734	2.16	0.680	41.1
400T200-54	0.0566	50	1.54	0.452	1.27	1.68	0.182	0.635	4.32	1.02	0.397	17.9	0.483	0.551	1.22	0.730	2.17	0.684	33.4
400T200-68	0.0713	50	1.94	0.569	1.62	1.69	0.227	0.632	6.66	1.39	0.549	24.7	0.965	0.702	1.21	0.725	2.17	0.689	33.6
400T200-97	0.1017	50	2.76	0.811	2.36	1.71	0.318	0.626	9.39	2.24	0.911	41.0	2.80	1.02	1.19	0.715	2.17	0.699	34.1
400T300-33	0.0346	33	1.18	0.346	1.06	1.75	0.338	0.989	1.20	0.670	0.218	6.48	0.138	1.01	2.10	1.21	2.91	0.478	60.4
400T300-43	0.0451	33	1.53	0.451	1.38	1.75	0.439	0.987	2.22	0.939	0.334	9.91	0.306	1.31	2.10	1.21	2.91	0.479	60.6
400T300-54	0.0566	50	1.92	0.565	1.75	1.76	0.548	0.985	4.31	1.20	0.426	19.2	0.604	1.66	2.09	1.21	2.91	0.482	49.3
400T300-68	0.0713	50	2.42	0.712	2.24	1.77	0.686	0.982	6.66	1.66	0.594	26.7	1.21	2.12	2.08	1.20	2.90	0.487	49.6
400T300-97	0.1017	50	3.45	1.01	3.28	1.80	0.967	0.976	9.39	2.73	1.00	45.2	3.50	3.11	2.06	1.19	2.90	0.497	50.4
600T125-18	0.0188	33	0.544	0.160	0.776	2.20	0.0187	0.342	0.128	0.493	0.103	3.06	0.0188	0.131	0.522	0.341	2.29	0.948	24.9
600T125-33	0.0346	33	1.00	0.294	1.43	2.20	0.0338	0.339	0.795	1.20	0.297	8.82	0.117	0.238	0.516	0.337	2.29	0.949	24.8
600T125-43	0.0451	33	1.30	0.383	1.86	2.21	0.0435	0.337	1.76	1.72	0.461	13.7	0.260	0.307	0.513	0.335	2.29	0.950	24.7
600T125-54	0.0566	50	1.64	0.480	2.34	2.21	0.0539	0.335	3.49	2.19	0.592	26.6	0.513	0.384	0.508	0.332	2.29	0.951	20.1
600T125-68	0.0713	50	2.06	0.605	2.97	2.22	0.0668	0.332	6.84	2.92	0.858	38.6	1.03	0.483	0.503	0.329	2.30	0.952	20.0
600T125-97	0.1017	50	2.93	0.862	4.28	2.23	0.0919	0.327	13.9	4.28	1.35	60.6	2.97	0.685	0.491	0.321	2.31	0.955	20.1
600T150-33	0.0346	33	1.06	0.311	1.59	2.26	0.0566	0.426	0.800	1.27	0.303	9.00	0.124	0.390	0.684	0.439	2.40	0.919	30.2
600T150-43	0.0451	33	1.38	0.405	2.07	2.26	0.0730	0.424	1.76	1.83	0.474	14.1	0.275	0.504	0.680	0.437	2.40	0.920	30.2
600T150-54	0.0566	50	1.73	0.509	2.61	2.27	0.0907	0.422	3.49	2.33	0.609	27.4	0.543	0.633	0.675	0.434	2.40	0.921	24.5
600T150-68	0.0713	50	2.18	0.641	3.31	2.27	0.113	0.419	6.85	3.13	0.891	40.1	1.09	0.797	0.669	0.430	2.41	0.923	24.5
600T150-97	0.1017	50	3.11	0.913	4.78	2.29	0.156	0.414	13.9	4.78	1.44	65.0	3.15	1.14	0.656	0.421	2.42	0.926	24.6
600T200-33	0.0346	33	1.18	0.346	1.91	2.35	0.126	0.604	0.800	1.50	0.333	9.90	0.138	0.847	1.05	0.655	2.64	0.843	40.9
600T200-43	0.0451	33	1.53	0.451	2.49	2.35	0.163	0.602	1.76	2.06	0.565	16.8	0.306	1.10	1.04	0.652	2.64	0.844	40.9
600T200-54	0.0566	50	1.92	0.565	3.15	2.36	0.204	0.600	3.49	2.62	0.717	32.3	0.604	1.38	1.04	0.649	2.65	0.846	33.2
600T200-68	0.0713	50	2.42	0.712	3.99	2.37	0.254	0.597	6.85	3.51	0.973	43.8	1.21	1.75	1.03	0.644	2.65	0.849	33.3
600T200-97	0.1017	50	3.45	1.02	5.77	2.39	0.355	0.591	13.9	5.51	1.57	70.6	3.50	2.51	1.02	0.635	2.66	0.854	33.4
600T300-33	0.0346	33	1.41	0.415	2.56	2.48	0.384	0.962	0.795	1.63	0.331	9.82	0.166	2.52	1.85	1.11	3.24	0.674	61.3
600T300-43	0.0451	33	1.84	0.541	3.34	2.48	0.498	0.960	1.76	2.39	0.555	16.5	0.367	3.28	1.85	1.11	3.24	0.675	61.4
600T300-54	0.0566	50	2.31	0.679	4.21	2.49	0.622	0.957	3.49	3.05	0.721	32.5	0.725	4.13	1.84	1.11	3.24	0.677	49.9
600T300-68	0.0713	50	2.91	0.855	5.35	2.50	0.779	0.954	6.84	4.11	1.05	47.4	1.45	5.24	1.83	1.10	3.25	0.681	50.0
600T300-97	0.1017	50	4.15	1.22	7.76	2.52	1.10	0.949	13.9	6.59	1.72	77.6	4.20	7.58	1.82	1.09	3.25	0.688	50.4
800T125-43	0.0451	33	1.61	0.473	3.77	2.82	0.0458	0.311	1.32	3.34	0.640	19.0	0.321	0.589	0.436	0.292	2.87	0.977	23.8
800T125-54	0.0566	50	2.02	0.594	4.75	2.83	0.0568	0.309	2.61	4.26	0.824	37.1	0.634	0.735	0.432	0.289	2.88	0.977	19.3
800T125-68	0.0713	50	2.54	0.748	6.00	2.83	0.0703	0.307	5.23	5.83	1.22	54.7	1.27	0.920	0.427	0.286	2.88	0.978	19.2
800T125-97	0.1017	50	3.63	1.07	8.61	2.84	0.0967	0.301	13.9	8.61	2.06	92.8	3.67	1.30	0.417	0.279	2.89	0.979	19.1

Track Designation	Base Design Thickness (in.)	F <sub>y</sub> (ksi)	GROSS							EFFECTIVE			TORSIONAL						L <sub>u</sub> (in.)
			Weight (lb/ft)	Area (in. <sup>2</sup> )	I <sub>x</sub> (in. <sup>4</sup> )	r <sub>x</sub> (in.)	I <sub>y</sub> (in. <sup>4</sup> )	r <sub>y</sub> (in.)	V <sub>rg</sub> (kip)	I <sub>xd</sub> (in. <sup>4</sup> )	S <sub>xe</sub> (in. <sup>3</sup> )	M <sub>rx</sub> (k-in.)	Jx1000 (in. <sup>4</sup> )	C <sub>w</sub> (in. <sup>6</sup> )	x <sub>o</sub> (in.)	m (in.)	r <sub>o</sub> (in.)	β	
800T150-43	0.0451	33	1.69	0.496	4.14	2.89	0.0774	0.395	1.32	3.52	0.655	19.5	0.336	0.972	0.584	0.386	2.98	0.961	29.3
800T150-54	0.0566	50	2.12	0.622	5.21	2.90	0.0961	0.393	2.61	4.49	0.844	38.0	0.664	1.22	0.580	0.383	2.98	0.962	23.8
800T150-68	0.0713	50	2.67	0.783	6.59	2.90	0.119	0.390	5.23	6.20	1.26	56.5	1.33	1.53	0.575	0.379	2.98	0.963	23.7
800T150-97	0.1017	50	3.80	1.12	9.48	2.91	0.165	0.385	13.9	9.48	2.19	98.6	3.85	2.16	0.564	0.372	2.99	0.965	23.7
800T200-43	0.0451	33	1.84	0.541	4.89	3.01	0.175	0.569	1.32	3.82	0.676	20.1	0.367	2.12	0.913	0.587	3.19	0.918	40.3
800T200-54	0.0566	50	2.31	0.679	6.15	3.01	0.218	0.567	2.61	4.89	0.872	39.2	0.725	2.66	0.908	0.584	3.20	0.919	32.7
800T200-68	0.0713	50	2.91	0.854	7.79	3.02	0.272	0.564	5.23	6.81	1.31	59.0	1.45	3.36	0.902	0.580	3.20	0.921	32.7
800T200-97	0.1017	50	4.15	1.22	11.2	3.03	0.379	0.558	13.9	10.8	2.35	106	4.20	4.79	0.889	0.571	3.21	0.923	32.7
800T300-43	0.0451	33	2.15	0.631	6.37	3.18	0.540	0.925	1.32	4.60	0.736	21.9	0.428	6.33	1.66	1.02	3.70	0.800	61.4
800T300-54	0.0566	50	2.69	0.792	8.03	3.18	0.675	0.923	2.60	5.92	0.955	43.0	0.845	7.96	1.65	1.02	3.70	0.801	49.9
800T300-68	0.0713	50	3.39	1.00	10.2	3.19	0.844	0.920	5.22	8.05	1.55	69.6	1.69	10.1	1.64	1.02	3.71	0.803	49.9
800T300-97	0.1017	50	4.84	1.42	14.7	3.21	1.19	0.914	13.9	12.7	2.59	116	4.90	14.5	1.63	1.01	3.72	0.808	50.1
1000T125-54	0.0566	50	2.41	0.707	8.33	3.43	0.0587	0.288	2.08	7.13	1.06	47.5	0.755	1.21	0.376	0.256	3.47	0.988	18.5
1000T125-68	0.0713	50	3.03	0.890	10.5	3.44	0.0727	0.286	4.17	9.86	1.58	70.9	1.51	1.51	0.372	0.253	3.47	0.989	18.4
1000T125-97	0.1017	50	4.32	1.27	15.1	3.45	0.100	0.281	12.2	15.1	2.75	124	4.38	2.12	0.363	0.247	3.48	0.989	18.3
1000T150-54	0.0566	50	2.50	0.735	9.06	3.51	0.100	0.368	2.08	7.47	1.08	48.5	0.785	2.01	0.509	0.342	3.57	0.980	23.0
1000T150-68	0.0713	50	3.15	0.926	11.4	3.52	0.124	0.366	4.17	10.4	1.62	73.0	1.57	2.52	0.505	0.339	3.57	0.980	23.0
1000T150-97	0.1017	50	4.49	1.32	16.4	3.53	0.172	0.361	12.2	16.4	2.90	131	4.55	3.56	0.495	0.332	3.58	0.981	22.9
1000T200-54	0.0566	50	2.69	0.792	10.5	3.65	0.228	0.537	2.08	8.04	1.11	50.0	0.845	4.43	0.809	0.531	3.77	0.954	32.0
1000T200-68	0.0713	50	3.39	1.00	13.3	3.65	0.284	0.534	4.17	11.3	1.68	75.8	1.69	5.58	0.803	0.527	3.78	0.955	32.0
1000T200-97	0.1017	50	4.84	1.42	19.1	3.66	0.397	0.528	12.2	18.4	3.08	139	4.90	7.92	0.791	0.519	3.79	0.956	31.9
1000T300-54	0.0566	50	3.08	0.905	13.4	3.85	0.714	0.888	2.08	9.36	1.19	53.6	0.966	13.3	1.50	0.947	4.23	0.874	49.6
1000T300-68	0.0713	50	3.88	1.14	17.0	3.86	0.894	0.885	4.17	13.7	1.90	85.6	1.93	16.8	1.49	0.943	4.23	0.876	49.6
1000T300-97	0.1017	50	5.53	1.63	24.4	3.88	1.26	0.880	12.1	21.4	3.59	161	5.60	24.0	1.48	0.934	4.24	0.879	49.6
1200T125-68	0.0713	50	3.51	1.03	16.8	4.04	0.0744	0.268	3.47	15.1	1.93	87.0	1.75	2.27	0.329	0.227	4.06	0.993	17.7
1200T125-97	0.1017	50	5.01	1.47	24.1	4.04	0.102	0.264	10.1	23.6	3.44	155	5.08	3.17	0.322	0.222	4.07	0.994	17.6
1200T150-68	0.0713	50	3.64	1.07	18.1	4.12	0.127	0.345	3.47	15.9	1.99	89.4	1.81	3.79	0.450	0.307	4.16	0.988	22.2
1200T150-97	0.1017	50	5.18	1.52	26.0	4.13	0.176	0.340	10.1	25.5	3.62	163	5.25	5.33	0.441	0.301	4.17	0.989	22.1
1200T200-68	0.0713	50	3.88	1.14	20.8	4.27	0.294	0.508	3.47	17.1	2.06	92.6	1.93	8.43	0.725	0.483	4.36	0.972	31.2
1200T200-97	0.1017	50	5.53	1.63	29.8	4.28	0.410	0.502	10.1	28.2	3.82	172	5.60	11.9	0.714	0.476	4.37	0.973	31.1
1200T300-68	0.0713	50	4.36	1.28	26.1	4.51	0.932	0.852	3.47	19.0	2.14	96.2	2.17	25.5	1.37	0.880	4.79	0.918	49.0
1200T300-97	0.1017	50	6.22	1.83	37.4	4.53	1.31	0.847	10.1	32.1	4.05	182	6.30	36.4	1.36	0.871	4.80	0.920	49.0
1400T125-68	0.0713	50	4.00	1.18	25.2	4.63	0.0757	0.254	2.97	21.6	2.29	103	1.99	3.19	0.296	0.206	4.65	0.996	17.1
1400T125-97	0.1017	50	5.70	1.68	36.0	4.64	0.104	0.249	8.65	34.2	4.13	186	5.78	4.44	0.289	0.201	4.65	0.996	16.9
1400T150-68	0.0713	50	4.12	1.21	27.0	4.72	0.130	0.328	2.97	22.6	2.35	106	2.05	5.35	0.407	0.280	4.75	0.993	21.5
1400T150-97	0.1017	50	5.88	1.73	38.6	4.73	0.180	0.323	8.65	36.8	4.33	195	5.95	7.50	0.399	0.275	4.76	0.993	21.3
1400T200-68	0.0713	50	4.36	1.28	30.6	4.88	0.301	0.485	2.97	24.2	2.43	109	2.17	11.9	0.661	0.446	4.95	0.982	30.5
1400T200-97	0.1017	50	6.22	1.83	43.8	4.89	0.420	0.479	8.65	40.4	4.56	205	6.30	16.9	0.651	0.439	4.96	0.983	30.3
1400T300-68	0.0713	50	4.85	1.42	37.7	5.15	0.963	0.822	2.97	26.7	2.52	113	2.41	36.3	1.27	0.825	5.36	0.944	48.4
1400T300-97	0.1017	50	6.91	2.03	54.1	5.16	1.35	0.816	8.64	45.5	4.81	217	7.00	51.6	1.25	0.817	5.37	0.946	48.3

## Curtain Wall Limiting Height Tables - Single and Double Spans

### Table Notes

- 1 For wind load deflection calculations, the SLS importance factor,  $I_w = 0.75$  is incorporated in the load tables.
- 2 Studs must be braced against rotation and lateral displacement at all supports.
- 3 Studs are assumed to be adequately braced at a maximum spacing of  $L_u$  to develop the full factored moment resistance
- 4 Web crippling check is based on 1.25" of bearing at end supports and 3" of bearing at interior supports.
- 5 Shear and web crippling resistance at end supports have not been reduced for punchouts. At interior supports, the shear and web crippling resistance has been reduced for the presence of punchout adjacent to the support.
- 6 Combined bending and shear check at interior support is based on the unreinforced web as per S136-16 (Eq. H2-1). Shear resistance and combined bending and shear checks at interior supports have been reduced for the presence of punchouts adjacent to the support.
- 7 In the "Double Span" tables, the listed span is the distance from either end to the centre of the interior support with the stud continuous past the interior support.



**SINGLE SPAN CURTAIN WALL LIMITING HEIGHTS (ft-in.) continued**

SPECIFIED LOADS			5 psf			10 psf			15 psf			20 psf			25 psf			30 psf		
Stud Member	F <sub>y</sub> (ksi)	Spacing (in.) o.c.	L/120	L/240	L/360	L/240	L/360	L/600	L/240	L/360	L/600	L/240	L/360	L/600	L/240	L/360	L/600	L/240	L/360	L/600
			Example row for 400S125-33 (Actual content is truncated for brevity, following the pattern in the image)																	

**NOTES:**

- 1)  $\rho = I_w \{q C_c C_p C_e\}$ ;  $I_w$  of 0.75 has been incorporated in the deflection values of the table.  
The parameters in the bracket { } must be determined by the design professional in accordance with the NBCC.
- 2) "e" web stiffeners required at ends.

Bailey Metal Products, Dacs Metal Products, DCM Metal Corp., EB Metal Inc., Imperial Building Products, Manuypasse, Groupe UP, Trebor Building Products Ltd.



SINGLE SPAN CURTAIN WALL LIMITING HEIGHTS (ft-in.) continued

SPECIFIED LOADS			5 psf			10 psf			15 psf			20 psf			25 psf			30 psf		
Stud Member	F <sub>y</sub> (ksi)	Spacing (in.) o.c.	L/120	L/240	L/360	L/240	L/360	L/600	L/240	L/360	L/600	L/240	L/360	L/600	L/240	L/360	L/600	L/240	L/360	L/600
800S162-43	33	12	50' 2"	42' 9"	37' 4"	33' 10"	29' 8"	25' 0"	29' 0"	25' 10"	21' 9"	25' 1'e	23' 6"	19' 9"	22' 6'e	21' 9'e	18' 4"	20' 6'e	20' 6'e	17' 3'e
	33	16	43' 6"	38' 10"	33' 10"	30' 9"	26' 10"	22' 8"	25' 1'e	23' 6"	19' 9"	21' 8'e	21' 4'e	18' 0"	19' 6'e	19' 6'e	16' 8'e	17' 9'e	17' 9'e	15' 9'e
	33	24	35' 6"	33' 10"	29' 8"	25' 1'e	23' 6"	19' 9"	20' 6'e	20' 6'e	17' 3'e	17' 9'e	17' 9'e	15' 9'e	15' 10'e	15' 10'e	14' 7'e	14' 6'e	14' 6'e	13' 9'e
800S162-54	50	12	57' 10"	46' 0"	40' 2"	36' 6"	31' 10"	26' 10"	31' 10"	27' 9"	23' 6"	29' 0"	25' 3"	21' 3"	26' 10"	23' 6"	19' 9"	25' 3"	22' 1"	18' 7"
	50	16	52' 7"	41' 9"	36' 6"	33' 1"	29' 0"	24' 4"	29' 0"	25' 3"	21' 3"	26' 3"	23' 0"	19' 4"	24' 4"	21' 3"	18' 0"	23' 0"	20' 1"	16' 10"
800S162-68	50	12	62' 8"	49' 8"	43' 4"	39' 6"	34' 6"	29' 1"	34' 6"	30' 1"	25' 4"	31' 3"	27' 4"	23' 1"	29' 1"	25' 4"	21' 4"	27' 4"	23' 10"	20' 2"
	50	16	56' 10"	45' 2"	39' 6"	35' 10"	31' 3"	26' 4"	31' 3"	27' 4"	23' 1"	28' 6"	24' 10"	21' 0"	26' 4"	23' 1"	19' 6"	24' 10"	21' 8"	18' 3"
800S162-97	50	12	69' 8"	55' 3"	48' 3"	43' 10"	38' 4"	32' 4"	38' 4"	33' 6"	28' 3"	34' 10"	30' 6"	25' 8"	32' 4"	28' 3"	23' 9"	30' 6"	26' 7"	22' 4"
	50	16	63' 3"	50' 3"	43' 10"	39' 10"	34' 10"	29' 4"	34' 10"	30' 6"	25' 8"	31' 8"	27' 8"	23' 3"	29' 4"	25' 8"	21' 8"	27' 8"	24' 2"	20' 4"
800S200-43	33	12	53' 10"	45' 2"	39' 6"	35' 10"	31' 4"	26' 4"	31' 1"	27' 4"	23' 1"	27' 0'e	24' 10'e	21' 0"	24' 1'e	23' 1'e	19' 6"	22' 0'e	21' 8'e	18' 3'e
	33	16	46' 8"	41' 1"	35' 10"	32' 7"	28' 6"	24' 0"	27' 0'e	24' 10'e	21' 0"	23' 4'e	22' 7'e	19' 1'e	20' 10'e	20' 10'e	17' 8'e	19' 1'e	19' 1'e	16' 8'e
	33	24	38' 1"	35' 10"	31' 4"	27' 0'e	24' 10'e	21' 0"	22' 0'e	21' 8'e	18' 3'e	19' 1'e	19' 1'e	16' 8'e	17' 1'e	17' 1'e	15' 6'e	15' 7'e	15' 7'e	14' 7'e
800S200-54	50	12	61' 2"	48' 7"	42' 4"	38' 7"	33' 8"	28' 4"	33' 8"	29' 4"	24' 9"	30' 7"	26' 8"	22' 7"	28' 4"	24' 9"	20' 10"	26' 8"	23' 4"	19' 8"
	50	16	55' 7"	44' 1"	38' 7"	35' 0"	30' 7"	25' 9"	30' 7"	26' 8"	22' 7"	27' 9"	24' 3"	20' 6"	25' 9"	22' 7"	19' 0"	24' 3"	21' 2"	17' 10"
800S200-68	50	12	65' 8"	52' 2"	45' 7"	41' 4"	36' 2"	30' 6"	36' 2"	31' 7"	26' 8"	32' 10"	28' 8"	24' 2"	30' 6"	26' 8"	22' 6"	28' 8"	25' 1"	21' 2"
	50	16	59' 8"	47' 4"	41' 4"	37' 7"	32' 10"	27' 8"	32' 10"	28' 8"	24' 2"	29' 10"	26' 1"	22' 0"	27' 8"	24' 2"	20' 4"	26' 1"	22' 9"	19' 2"
800S200-97	50	12	73' 1"	58' 0"	50' 8"	46' 1"	40' 2"	33' 10"	40' 2"	35' 2"	29' 7"	36' 7"	31' 10"	26' 10"	33' 10"	29' 7"	25' 0"	31' 10"	27' 10"	23' 6"
	50	16	66' 4"	52' 8"	46' 1"	41' 10"	36' 7"	30' 9"	36' 7"	31' 10"	26' 10"	33' 2"	29' 0"	24' 6"	30' 9"	26' 10"	22' 8"	29' 0"	25' 3"	21' 4"
800S250-43	33	12	55' 3"	47' 1"	41' 1"	37' 4"	32' 7"	27' 6"	31' 10"	28' 6"	24' 0"	27' 7'e	25' 10'e	21' 9"	24' 8'e	24' 0'e	20' 3'e	22' 7'e	22' 7'e	19' 1'e
	33	16	47' 10"	42' 9"	37' 4"	33' 10"	29' 8"	25' 0"	27' 7'e	25' 10'e	21' 9"	23' 10'e	23' 6'e	19' 10'e	21' 4'e	21' 4'e	18' 4'e	19' 6'e	19' 6'e	17' 3'e
	33	24	39' 1"	37' 4"	32' 7"	27' 7'e	25' 10'e	21' 9"	22' 7'e	22' 7'e	19' 1'e	19' 6'e	19' 6'e	17' 3'e	17' 6'e	17' 6'e	16' 1'e	16' 0'e	16' 0'e	15' 1'e
800S250-54	50	12	63' 0"	50' 0"	43' 8"	39' 8"	34' 8"	29' 2"	34' 8"	30' 3"	25' 6"	31' 6"	27' 6"	23' 2"	29' 2"	25' 6"	21' 6"	27' 6"	24' 0"	20' 3"
	50	16	57' 2"	45' 4"	39' 8"	36' 1"	31' 6"	26' 7"	31' 6"	27' 6"	23' 2"	28' 7"	25' 0"	21' 1"	26' 7"	23' 2"	19' 7"	25' 0"	21' 9"	18' 4"
800S250-68	50	12	68' 3"	54' 2"	47' 4"	43' 0"	37' 7"	31' 8"	37' 7"	32' 9"	27' 8"	34' 2"	29' 9"	25' 2"	31' 8"	27' 8"	23' 4"	29' 9"	26' 1"	22' 0"
	50	16	62' 1"	49' 3"	43' 0"	39' 1"	34' 2"	28' 9"	34' 2"	29' 9"	25' 2"	31' 0"	27' 1"	22' 10"	28' 9"	25' 2"	21' 2"	27' 1"	23' 8"	20' 0"
800S250-97	50	12	76' 4"	60' 8"	53' 0"	48' 1"	42' 1"	35' 6"	42' 1"	36' 8"	31' 0"	38' 2"	33' 4"	28' 2"	35' 6"	31' 0"	26' 1"	33' 4"	29' 2"	24' 7"
	50	16	69' 4"	55' 1"	48' 1"	43' 8"	38' 2"	32' 2"	38' 2"	33' 4"	28' 2"	34' 8"	30' 3"	25' 7"	32' 2"	28' 2"	23' 8"	30' 3"	26' 6"	22' 3"
800S300-43	33	12	56' 1"	48' 1"	42' 1"	38' 2"	33' 4"	28' 2"	32' 4"	29' 2"	24' 7"	28' 0'e	26' 6'e	22' 3"	25' 1'e	24' 7'e	20' 8'e	22' 10'e	22' 10'e	19' 6'e
	33	16	48' 7"	43' 8"	38' 2"	34' 3"	30' 3"	25' 7"	28' 0'e	26' 6'e	22' 3"	24' 3'e	24' 1'e	20' 3'e	21' 8'e	21' 8'e	18' 9'e	19' 9'e	19' 9'e	17' 8'e
	33	24	39' 7"	38' 2"	33' 4"	28' 0'e	26' 6'e	22' 3"	22' 10'e	22' 10'e	19' 6'e	19' 9'e	19' 9'e	17' 8'e	17' 8'e	17' 8'e	16' 6'e	16' 2'e	16' 2'e	15' 6'e
800S300-54	50	12	64' 4"	51' 1"	44' 8"	40' 7"	35' 6"	29' 10"	35' 6"	31' 0"	26' 1"	32' 2"	28' 1"	23' 8"	29' 10"	26' 1"	22' 0"	28' 1"	24' 7"	20' 8"
	50	16	58' 6"	46' 6"	40' 7"	36' 10"	32' 2"	27' 2"	32' 2"	28' 1"	23' 8"	29' 3"	25' 7"	21' 7"	27' 2"	23' 8"	20' 0"	25' 7"	22' 3"	18' 9"
800S300-68	50	12	70' 0"	55' 7"	48' 7"	44' 1"	38' 6"	32' 6"	38' 6"	33' 8"	28' 4"	35' 0"	30' 7"	25' 9"	32' 6"	28' 4"	23' 10"	30' 7"	26' 8"	22' 6"
	50	16	63' 7"	50' 6"	44' 1"	40' 1"	35' 0"	29' 6"	35' 0"	30' 7"	25' 9"	31' 9"	27' 9"	23' 4"	29' 6"	25' 9"	21' 9"	27' 9"	24' 3"	20' 6"
800S300-97	50	12	79' 0"	62' 8"	54' 9"	49' 9"	43' 6"	36' 8"	43' 6"	38' 0"	32' 0"	39' 6"	34' 6"	29' 1"	36' 8"	32' 0"	27' 0"	34' 6"	30' 1"	25' 4"
	50	16	71' 9"	57' 0"	49' 9"	45' 2"	39' 6"	33' 3"	39' 6"	34' 6"	29' 1"	35' 10"	31' 3"	26' 4"	33' 3"	29' 1"	24' 6"	31' 3"	27' 4"	23' 1"
50	24	62' 8"	49' 9"	43' 6"	39' 6"	34' 6"	29' 1"	34' 6"	30' 1"	25' 4"	31' 3"	27' 4"	23' 1"	29' 1"	25' 4"	21' 4"	27' 4"	23' 10"	20' 2"	

NOTES:

- 1)  $p = I_w \{ qC_s C_p \}$ ;  $I_w$  of 0.75 has been incorporated in the deflection values of the table. The parameters in the bracket { } must be determined by the design professional in accordance with the NBCC.
- 2) "e" web stiffeners required at ends.















DOUBLE SPAN CURTAIN WALL LIMITING HEIGHTS (ft-in.) continued

SPECIFIED LOADS		5 psf			10 psf			15 psf			20 psf			25 psf			30 psf			
Stud Member	F <sub>y</sub> (ksi)	Spacing (in.) o.c.	L/120	L/240	L/360	L/240	L/360	L/600	L/240	L/360	L/600	L/240	L/360	L/600	L/240	L/360	L/600	L/240	L/360	L/600
			600S125-33	33	12	28' 7"	28' 7"	28' 7"	20' 2"	20' 2"	20' 2"	16' 6"	16' 6"	16' 6"	14' 3"	14' 3"	14' 3"	12' 9"	12' 9"	12' 9"

NOTES:

- $p = l_w \{qC_c C_p\}$ ;  $l_w$  of 0.75 has been incorporated in the deflection values of the table.  
The parameters in the bracket { } must be determined by the design professional in accordance with the NBCC.
- "e" web stiffeners required at ends; "i" web stiffeners required at interior support; "a" web stiffeners required at ends and interior supports.

### DOUBLE SPAN CURTAIN WALL LIMITING HEIGHTS (ft-in.) continued

SPECIFIED LOADS			5 psf			10 psf			15 psf			20 psf			25 psf			30 psf		
Stud Member	F <sub>y</sub> (ksi)	Spacing (in.) o.c.	L/120	L/240	L/360	L/240	L/360	L/600	L/240	L/360	L/600	L/240	L/360	L/600	L/240	L/360	L/600	L/240	L/360	L/600
			This area contains the main data rows for the table, which are extremely dense. Representative rows are shown here to illustrate the format, with some cells containing alphanumeric codes like 'a', 'i', 'e' for web stiffeners.																	
800S162-43	33	12	50' 2"	50' 2"	49' 10"	35' 6"	35' 6"	33' 4"	29' 0"	29' 0"	29' 0"	25' 1"	25' 1"	25' 1"	22' 6"	22' 6"	22' 6"	20' 6"	20' 6"	20' 6"
	33	16	43' 6"	43' 6"	43' 6"	30' 9"	30' 9"	30' 3"	25' 1"	25' 1"	25' 1"	21' 8"	21' 8"	21' 8"	19' 6"	19' 6"	19' 6"	17' 9"	17' 9"	17' 9"

**NOTES:**

- 1)  $p = I_w \{qC_e C_g C_p\}$ ;  $I_w$  of 0.75 has been incorporated in the deflection values of the table.
- The parameters in the bracket { } must be determined by the design professional in accordance with the NBC.
- 2) "e" web stiffeners required at ends; "i" web stiffeners required at interior support; "a" web stiffeners required at ends and interior supports.











## Combined Axial and Lateral Load Tables

### Table Notes

- 1 Limiting factored axial compressive resistances are based on a simple one span condition and are given in kip based on the assumption that the axial load passes through the centroid of the effective section.
- 2 Limiting axial resistances are based on 4'-0" on centre bracing. The ends of the studs are also assumed to be laterally and torsionally restrained. Design bridging for the accumulated torsion between bridging lines in combination with the discrete bracing requirements. Provide periodic anchorage for the bridging as required structurally.
- 3 Wind loads shown are factored and uniformly distributed over the surface of the wall. Axial loads are factored and are per stud. Seismic loads are not considered.
- 4 For wind load deflection calculations,  $p = I_w \{qC_eC_gC_p\}$ .  $I_w$  of 0.75 has been incorporated in the deflection values of the table. The parameters in the bracket { } must be determined by the design professional in accordance with the NBCC.
- 5 End supports are not checked for web crippling. See web crippling data on page 83.

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 0 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	362S162					362S200					362S250					362S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	3.03	4.15	6.28	8.06	11.7	3.59	5.09	7.81	9.95	14.1	3.87	5.75	8.74	11.5	16.2	4.02	5.86	8.78	12.1	17.8
	16	3.03	4.15	6.28	8.06	11.7	3.59	5.09	7.81	9.95	14.1	3.87	5.75	8.74	11.5	16.2	4.02	5.86	8.78	12.1	17.8
	24	3.03	4.15	6.28	8.06	11.7	3.59	5.09	7.81	9.95	14.1	3.87	5.75	8.74	11.5	16.2	4.02	5.86	8.78	12.1	17.8
9	12	2.93	4.01	5.94	7.57	10.9	3.48	4.90	7.35	9.30	13.1	3.75	5.58	8.34	10.8	15.1	3.90	5.71	8.40	11.5	17.0
	16	2.93	4.01	5.94	7.57	10.9	3.48	4.90	7.35	9.30	13.1	3.75	5.58	8.34	10.8	15.1	3.90	5.70	8.40	11.5	17.0
	24	2.93	4.00	5.94	7.57	10.9	3.47	4.89	7.35	9.30	13.1	3.75	5.58	8.34	10.8	15.1	3.90	5.70	8.40	11.5	17.0
10	12	2.81	3.84	5.56	7.03	10.1	3.35	4.67	6.84	8.60	12.1	3.62	5.39	7.92	9.99	14.0	3.77	5.53	7.98	10.7	15.8
	16	2.81	3.84	5.56	7.03	10.1	3.35	4.67	6.84	8.60	12.1	3.62	5.39	7.92	9.99	14.0	3.77	5.53	7.98	10.7	15.8
	24	2.81	3.84	5.56	7.03	10.1	3.35	4.67	6.84	8.60	12.1	3.62	5.39	7.92	9.99	14.0	3.77	5.53	7.98	10.7	15.8
12	12	2.53	3.45	4.65	5.82	8.22	3.05	4.17	5.69	7.08	9.87	3.31	4.85	6.66	8.27	11.5	3.47	5.11	7.14	9.22	13.1
	16	2.53	3.45	4.65	5.82	8.22	3.05	4.17	5.69	7.08	9.87	3.31	4.85	6.66	8.27	11.5	3.47	5.11	7.14	9.22	13.1
	24	2.53	3.45	4.65	5.82	8.22	3.05	4.17	5.69	7.08	9.87	3.31	4.85	6.66	8.27	11.5	3.47	5.11	7.14	9.22	13.1
14	12	2.21	3.00	3.81	4.74	6.59	2.69	3.62	4.63	5.73	7.92	2.97	4.23	5.43	6.72	9.29	3.14	4.64	6.13	7.69	10.6
	16	2.21	3.00	3.81	4.74	6.59	2.68	3.62	4.63	5.73	7.92	2.97	4.23	5.43	6.72	9.29	3.14	4.64	6.13	7.69	10.6
	24	2.20	3.00	3.81	4.74	6.59	2.68	3.62	4.63	5.73	7.92	2.97	4.23	5.43	6.72	9.29	3.13	4.64	6.13	7.69	10.6
16	12	1.87	2.53	3.13	3.87	5.33	2.27	3.06	3.79	4.68	6.43	2.61	3.59	4.45	5.51	7.58	2.78	4.11	5.11	6.33	8.72
	16	1.87	2.53	3.13	3.87	5.33	2.27	3.06	3.79	4.68	6.43	2.61	3.59	4.45	5.51	7.58	2.78	4.11	5.11	6.33	8.72
	24	1.87	2.53	3.13	3.87	5.33	2.27	3.06	3.79	4.68	6.42	2.60	3.59	4.45	5.51	7.58	2.77	4.11	5.11	6.32	8.71
18	12	1.58	2.10	2.59	3.20	4.37	1.91	2.54	3.13	3.86	5.28	2.25	2.99	3.69	4.56	6.26	2.43	3.44	4.25	5.26	7.23
	16	1.58	2.10	2.59	3.20	4.37	1.91	2.54	3.13	3.86	5.28	2.25	2.99	3.69	4.56	6.26	2.43	3.43	4.25	5.26	7.23
	24	1.58	2.10	2.59	3.20	4.37	1.91	2.53	3.13	3.86	5.28	2.25	2.99	3.69	4.56	6.26	2.42	3.43	4.25	5.26	7.22
20	12	1.35	1.76	2.17	2.67	3.63	1.62	2.12	2.62	3.23	4.40	1.92	2.51	3.10	3.83	5.23	2.13	2.89	3.57	4.42	6.06
	16	1.35	1.76	2.17	2.67	3.63	1.62	2.12	2.62	3.23	4.40	1.91	2.51	3.10	3.82	5.23	2.13	2.89	3.57	4.42	6.06
	24	1.34	1.76	2.17	2.67	3.63	1.62	2.12	2.62	3.23	4.40	1.91	2.51	3.10	3.82	5.23	2.13	2.89	3.57	4.42	6.06

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 10 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	362S162					362S200					362S250					362S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	2.58	3.69	5.85	7.63	11.3	3.10	4.60	7.34	9.49	13.7	3.38	5.22	8.24	11.0	15.8	3.55	5.36	8.32	11.6	17.4
	16	2.43	3.54	5.72	7.49	11.1	2.94	4.44	7.18	9.34	13.5	3.23	5.06	8.08	10.9	15.6	3.39	5.19	8.16	11.5	17.2
	24	2.15	3.26	5.45	7.23	10.9	2.64	4.13	6.88	9.04	13.3	2.92	4.73	7.77	10.6	15.3	3.09	4.87	7.87	11.1	16.9
9	12	2.35	3.42	5.40	7.03	10.4	2.85	4.26	6.74	8.72	12.6	3.13	4.90	7.70	10.2	14.5	3.30	5.05	7.80	10.9	16.4
	16	2.18	3.24	5.23	6.86	10.2	2.66	4.06	6.55	8.53	12.4	2.94	4.69	7.49	9.95	14.4	3.11	4.84	7.61	10.7	16.2
	24	1.84	2.89	4.90	6.53	9.92	2.29	3.68	6.19	8.17	12.1	2.57	4.28	7.10	9.55	14.0	2.74	4.44	7.24	10.3	15.8
10	12	2.11	3.12	4.90	6.37	9.45	2.58	3.89	6.10	7.89	11.4	2.86	4.54	7.11	9.21	13.3	3.02	4.71	7.24	9.96	15.0
	16	1.90	2.90	4.70	6.17	9.25	2.35	3.66	5.88	7.66	11.2	2.63	4.28	6.87	8.96	13.0	2.80	4.45	7.00	9.71	14.8
	24	1.52	2.49	4.32	5.78	8.88	1.93	3.22	5.45	7.24	10.8	2.19	3.80	6.39	8.50	12.6	2.36	3.97	6.56	9.24	14.3
12	12	1.59	2.46	3.80	4.97	7.42	2.00	3.11	4.75	6.16	9.03	2.26	3.68	5.60	7.25	10.5	2.44	3.94	6.08	8.15	12.1
	16	1.34 <sup>4</sup>	2.20	3.56	4.73	7.18	1.72	2.81	4.48	5.90	8.78	1.98	3.35	5.30	6.95	10.3	2.14	3.60	5.77	7.83	11.8
	24	0.90 <sup>3</sup>	1.71 <sup>4</sup>	3.12	4.28	6.74	1.22 <sup>3</sup>	2.28 <sup>4</sup>	3.99	5.40	8.31	1.45 <sup>4</sup>	2.76	4.75	6.40	9.71	1.61 <sup>4</sup>	2.99	5.19	7.24	11.2
14	12	1.11 <sup>3</sup>	1.83	2.85	3.78	5.69	1.44 <sup>4</sup>	2.34	3.56	4.69	6.97	1.69	2.80	4.23	5.56	8.19	1.85	3.13	4.82	6.41	9.45
	16	0.85 <sup>3</sup>	1.54 <sup>3</sup>	2.60 <sup>4</sup>	3.52	5.43	1.14 <sup>3</sup>	2.03 <sup>4</sup>	3.28	4.41	6.69	1.37 <sup>3</sup>	2.45	3.91	5.24	7.87	1.52 <sup>4</sup>	2.75	4.47	6.05	9.11
	24	0.39 <sup>2</sup>	1.04 <sup>3</sup>	2.15 <sup>3</sup>	3.06 <sup>3</sup>	4.97	0.62 <sup>2</sup>	1.47 <sup>3</sup>	2.79 <sup>3</sup>	3.90 <sup>4</sup>	6.20	0.81 <sup>3</sup>	1.82 <sup>3</sup>	3.35 <sup>4</sup>	4.67	7.30	0.94 <sup>3</sup>	2.07 <sup>3</sup>	3.85 <sup>4</sup>	5.42	8.48
16	12	0.72 <sup>3</sup>	1.29 <sup>3</sup>	2.12 <sup>4</sup>	2.86	4.37	0.96 <sup>3</sup>	1.69 <sup>3</sup>	2.67	3.58	5.40	1.18 <sup>3</sup>	2.05 <sup>4</sup>	3.19	4.26	6.39	1.32 <sup>3</sup>	2.37	3.69	4.94	7.42
	16	0.46 <sup>2</sup>	1.01 <sup>3</sup>	1.87 <sup>3</sup>	2.60 <sup>3</sup>	4.12	0.67 <sup>2</sup>	1.38 <sup>3</sup>	2.39 <sup>3</sup>	3.30 <sup>4</sup>	5.13	0.86 <sup>3</sup>	1.69 <sup>3</sup>	2.87 <sup>4</sup>	3.94	6.06	0.98 <sup>3</sup>	1.97 <sup>3</sup>	3.34 <sup>4</sup>	4.58	7.06
	24	0.02 <sup>1</sup>	0.52 <sup>2</sup>	1.44 <sup>2</sup>	2.15 <sup>3</sup>	3.67 <sup>3</sup>	0.17 <sup>1</sup>	0.84 <sup>2</sup>	1.91 <sup>3</sup>	2.80 <sup>3</sup>	4.63 <sup>4</sup>	0.30 <sup>2</sup>	1.09 <sup>2</sup>	2.33 <sup>3</sup>	3.38 <sup>3</sup>	5.49	0.39 <sup>2</sup>	1.29 <sup>3</sup>	2.72 <sup>3</sup>	3.95 <sup>3</sup>	6.43
18	12	0.42 <sup>2</sup>	0.87 <sup>2</sup>	1.57 <sup>3</sup>	2.17 <sup>3</sup>	3.39	0.60 <sup>2</sup>	1.18 <sup>3</sup>	2.00 <sup>3</sup>	2.74 <sup>4</sup>	4.23	0.77 <sup>2</sup>	1.45 <sup>3</sup>	2.40 <sup>3</sup>	3.28	5.02	0.89 <sup>3</sup>	1.69 <sup>3</sup>	2.80 <sup>4</sup>	3.82	5.86
	16	0.18 <sup>1</sup>	0.60 <sup>2</sup>	1.34 <sup>2</sup>	1.92 <sup>3</sup>	3.15 <sup>3</sup>	0.32 <sup>2</sup>	0.88 <sup>2</sup>	1.74 <sup>3</sup>	2.47 <sup>3</sup>	3.96 <sup>4</sup>	0.46 <sup>2</sup>	1.11 <sup>3</sup>	2.11 <sup>3</sup>	2.97 <sup>3</sup>	4.70	0.56 <sup>2</sup>	1.31 <sup>3</sup>	2.46 <sup>3</sup>	3.48 <sup>4</sup>	5.51
	24		0.15 <sup>1</sup>	0.93 <sup>1</sup>	1.50 <sup>2</sup>	2.72 <sup>3</sup>		0.38 <sup>1</sup>	1.29 <sup>2</sup>	2.00 <sup>2</sup>	3.48 <sup>3</sup>		0.54 <sup>2</sup>	1.59 <sup>2</sup>	2.44 <sup>3</sup>	4.14 <sup>3</sup>		0.66 <sup>2</sup>	1.87 <sup>2</sup>	2.87 <sup>3</sup>	4.89 <sup>3</sup>
20	12	0.21 <sup>1</sup>	0.56 <sup>2</sup>	1.16 <sup>2</sup>	1.65 <sup>3</sup>	2.66 <sup>3</sup>	0.34 <sup>1</sup>	0.80 <sup>2</sup>	1.50 <sup>3</sup>	2.11 <sup>3</sup>	3.34 <sup>4</sup>	0.46 <sup>2</sup>	1.00 <sup>2</sup>	1.82 <sup>3</sup>	2.54 <sup>3</sup>	3.98	0.56 <sup>2</sup>	1.18 <sup>3</sup>	2.12 <sup>3</sup>	2.98 <sup>3</sup>	4.67
	16		0.31 <sup>1</sup>	0.94 <sup>1</sup>	1.42 <sup>2</sup>	2.42 <sup>3</sup>	0.08 <sup>1</sup>	0.53 <sup>1</sup>	1.26 <sup>2</sup>	1.85 <sup>2</sup>	3.08 <sup>3</sup>	0.17 <sup>1</sup>	0.69 <sup>2</sup>	1.54 <sup>2</sup>	2.25 <sup>3</sup>	3.67 <sup>3</sup>	0.24 <sup>1</sup>	0.82 <sup>2</sup>	1.80 <sup>2</sup>	2.64 <sup>3</sup>	4.33 <sup>4</sup>
	24			0.56 <sup>1</sup>	1.02 <sup>1</sup>	2.02 <sup>2</sup>		0.06 <sup>1</sup>	0.83 <sup>1</sup>	1.41 <sup>1</sup>	2.63 <sup>2</sup>		0.16 <sup>1</sup>	1.05 <sup>1</sup>	1.74 <sup>2</sup>	3.14 <sup>3</sup>		0.22 <sup>1</sup>	1.25 <sup>1</sup>	2.07 <sup>2</sup>	3.74 <sup>3</sup>

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

Bally Metal Products, Dass Metal Products, DCI Metal Corp., EB Metal Inc., Imperial Building Products, Managypse, Groupe UP, Trebor Building Products Ltd.

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 20 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	362S162					362S200					362S250					362S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	2.15	3.26	5.45	7.23	10.9	2.64	4.13	6.88	9.04	13.3	2.92	4.73	7.77	10.6	15.3	3.09	4.87	7.87	11.1	16.9
	16	1.89	2.98	5.19	6.96	10.6	2.35	3.83	6.59	8.76	13.0	2.63	4.41	7.46	10.2	15.0	2.80	4.55	7.57	10.8	16.6
	24	1.38	2.46	4.69	6.46	10.2	1.80	3.26	6.04	8.20	12.5	2.07	3.80	6.87	9.62	14.4	2.24	3.95	7.01	10.2	16.0
9	12	1.84	2.89	4.90	6.53	9.92	2.29	3.68	6.19	8.17	12.1	2.57	4.28	7.10	9.55	14.0	2.74	4.44	7.24	10.3	15.8
	16	1.52	2.56	4.59	6.21	9.62	1.95	3.32	5.84	7.82	11.8	2.22	3.89	6.72	9.16	13.6	2.38	4.05	6.88	9.86	15.4
	24	0.94 <sup>3</sup>	1.94 <sup>4</sup>	4.00	5.61	9.03	1.31 <sup>4</sup>	2.65	5.18	7.16	11.2	1.56 <sup>4</sup>	3.16	6.01	8.43	12.9	1.72	3.32	6.19	9.12	14.6
10	12	1.52	2.49	4.32	5.78	8.88	1.93	3.22	5.45	7.24	10.8	2.19	3.80	6.39	8.50	12.6	2.36	3.97	6.56	9.24	14.3
	16	1.16 <sup>4</sup>	2.12	3.96	5.42	8.52	1.54 <sup>4</sup>	2.80	5.05	6.84	10.5	1.79	3.34	5.95	8.05	12.1	1.95	3.52	6.13	8.79	13.9
	24	0.52 <sup>3</sup>	1.43 <sup>3</sup>	3.30 <sup>4</sup>	4.74	7.86	0.83 <sup>3</sup>	2.05 <sup>4</sup>	4.32	6.10	9.75	1.06 <sup>3</sup>	2.51 <sup>4</sup>	5.13	7.23	11.3	1.20 <sup>3</sup>	2.68	5.34	7.94	13.0
12	12	0.90 <sup>3</sup>	1.71 <sup>4</sup>	3.12	4.28	6.74	1.22 <sup>3</sup>	2.28 <sup>4</sup>	3.99	5.40	8.31	1.45 <sup>4</sup>	2.76	4.75	6.40	9.71	1.61 <sup>4</sup>	2.99	5.19	7.24	11.2
	16	0.51 <sup>2</sup>	1.28 <sup>3</sup>	2.73 <sup>3</sup>	3.87 <sup>4</sup>	6.33	0.78 <sup>3</sup>	1.81 <sup>3</sup>	3.54 <sup>4</sup>	4.95	7.87	0.99 <sup>3</sup>	2.23 <sup>4</sup>	4.25	5.90	9.21	1.13 <sup>3</sup>	2.44 <sup>4</sup>	4.67	6.70	10.6
	24		0.53 <sup>2</sup>	2.03 <sup>3</sup>	3.14 <sup>3</sup>	5.59 <sup>4</sup>	0.01 <sup>2</sup>	0.98 <sup>2</sup>	2.76 <sup>3</sup>	4.15 <sup>3</sup>	7.07	0.17 <sup>2</sup>	1.29 <sup>3</sup>	3.36 <sup>3</sup>	4.99 <sup>4</sup>	8.28	0.27 <sup>2</sup>	1.45 <sup>3</sup>	3.73 <sup>3</sup>	5.71 <sup>4</sup>	9.63
14	12	0.39 <sup>2</sup>	1.04 <sup>3</sup>	2.15 <sup>3</sup>	3.06 <sup>3</sup>	4.97	0.62 <sup>2</sup>	1.47 <sup>3</sup>	2.79 <sup>3</sup>	3.90 <sup>4</sup>	6.20	0.81 <sup>3</sup>	1.82 <sup>3</sup>	3.35 <sup>4</sup>	4.67	7.30	0.94 <sup>3</sup>	2.07 <sup>3</sup>	3.85 <sup>4</sup>	5.42	8.48
	16		0.60 <sup>2</sup>	1.76 <sup>2</sup>	2.65 <sup>3</sup>	4.56 <sup>3</sup>	0.17 <sup>2</sup>	0.99 <sup>2</sup>	2.35 <sup>3</sup>	3.45 <sup>3</sup>	5.75 <sup>4</sup>	0.32 <sup>2</sup>	1.28 <sup>3</sup>	2.85 <sup>3</sup>	4.15 <sup>3</sup>	6.77	0.42 <sup>2</sup>	1.47 <sup>3</sup>	3.29 <sup>3</sup>	4.84 <sup>4</sup>	7.90
	24			1.08 <sup>1</sup>	1.93 <sup>2</sup>	3.82 <sup>3</sup>		0.16 <sup>1</sup>	1.59 <sup>2</sup>	2.66 <sup>2</sup>	4.94 <sup>3</sup>		0.34 <sup>2</sup>	1.98 <sup>2</sup>	3.25 <sup>3</sup>	5.84 <sup>3</sup>		0.44 <sup>2</sup>	2.33 <sup>2</sup>	3.84 <sup>3</sup>	6.88 <sup>4</sup>
16	12	0.02 <sup>1</sup>	0.52 <sup>2</sup>	1.44 <sup>2</sup>	2.15 <sup>3</sup>	3.67 <sup>3</sup>	0.17 <sup>1</sup>	0.84 <sup>2</sup>	1.91 <sup>3</sup>	2.80 <sup>3</sup>	4.63 <sup>4</sup>	0.30 <sup>2</sup>	1.09 <sup>2</sup>	2.33 <sup>3</sup>	3.38 <sup>3</sup>	5.49	0.39 <sup>2</sup>	1.29 <sup>3</sup>	2.72 <sup>3</sup>	3.95 <sup>3</sup>	6.43
	16		0.11 <sup>1</sup>	1.07 <sup>1</sup>	1.76 <sup>2</sup>	3.27 <sup>3</sup>		0.38 <sup>1</sup>	1.50 <sup>2</sup>	2.37 <sup>2</sup>	4.19 <sup>3</sup>		0.56 <sup>2</sup>	1.85 <sup>2</sup>	2.88 <sup>3</sup>	4.97 <sup>3</sup>		0.69 <sup>2</sup>	2.18 <sup>2</sup>	3.40 <sup>3</sup>	5.86 <sup>4</sup>
	24			0.43 <sup>1</sup>	1.08 <sup>1</sup>	2.57 <sup>2</sup>			0.78 <sup>1</sup>	1.62 <sup>1</sup>	3.42 <sup>2</sup>			1.03 <sup>1</sup>	2.03 <sup>2</sup>	4.07 <sup>3</sup>			1.26 <sup>1</sup>	2.43 <sup>2</sup>	4.86 <sup>3</sup>
18	12		0.15 <sup>1</sup>	0.93 <sup>1</sup>	1.50 <sup>2</sup>	2.72 <sup>3</sup>		0.38 <sup>1</sup>	1.29 <sup>2</sup>	2.00 <sup>2</sup>	3.48 <sup>3</sup>		0.54 <sup>2</sup>	1.59 <sup>2</sup>	2.44 <sup>3</sup>	4.14 <sup>3</sup>		0.66 <sup>2</sup>	1.87 <sup>2</sup>	2.87 <sup>3</sup>	4.89 <sup>3</sup>
	16			0.58 <sup>1</sup>	1.13 <sup>1</sup>	2.34 <sup>2</sup>			0.90 <sup>1</sup>	1.59 <sup>1</sup>	3.06 <sup>2</sup>		0.06 <sup>1</sup>	1.14 <sup>1</sup>	1.97 <sup>2</sup>	3.65 <sup>3</sup>		0.11 <sup>1</sup>	1.37 <sup>1</sup>	2.34 <sup>2</sup>	4.34 <sup>3</sup>
	24				0.50 <sup>1</sup>	1.68 <sup>1</sup>			0.23 <sup>1</sup>	0.89 <sup>1</sup>	2.34 <sup>1</sup>			0.38 <sup>1</sup>	1.17 <sup>1</sup>	2.80 <sup>2</sup>			0.50 <sup>1</sup>	1.44 <sup>1</sup>	3.40 <sup>2</sup>
20	12			0.56 <sup>1</sup>	1.02 <sup>1</sup>	2.02 <sup>2</sup>		0.06 <sup>1</sup>	0.83 <sup>1</sup>	1.41 <sup>1</sup>	2.63 <sup>2</sup>		0.16 <sup>1</sup>	1.05 <sup>1</sup>	1.74 <sup>2</sup>	3.14 <sup>3</sup>		0.22 <sup>1</sup>	1.25 <sup>1</sup>	2.07 <sup>2</sup>	3.74 <sup>3</sup>
	16			0.24 <sup>1</sup>	0.68 <sup>1</sup>	1.66 <sup>1</sup>			0.47 <sup>1</sup>	1.03 <sup>1</sup>	2.24 <sup>1</sup>			0.64 <sup>1</sup>	1.30 <sup>1</sup>	2.68 <sup>2</sup>			0.78 <sup>1</sup>	1.58 <sup>1</sup>	3.22 <sup>2</sup>
	24				0.09 <sup>1</sup>	1.06 <sup>1</sup>			0.38 <sup>1</sup>	1.56 <sup>1</sup>				0.56 <sup>1</sup>	1.88 <sup>1</sup>				0.74 <sup>1</sup>	2.33 <sup>1</sup>	

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

Bally Metal Products, Dass Metal Products, DCI Metal Corp., EB Metal Inc., Imperial Building Products, Managryse, Groupe UP, Trebor Building Products Ltd.

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 30 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	362S162					362S200					362S250					362S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	1.76	2.85	5.06	6.83	10.5	2.21	3.68	6.45	8.62	12.9	2.49	4.25	7.31	10.1	14.9	2.66	4.40	7.43	10.7	16.5
	16	1.38	2.46	4.69	6.46	10.2	1.80	3.26	6.04	8.20	12.5	2.07	3.80	6.87	9.62	14.4	2.24	3.95	7.01	10.2	16.0
	24	0.69 <sup>3</sup>	1.73 <sup>4</sup>	3.99	5.74	9.46	1.04 <sup>4</sup>	2.46	5.25	7.41	11.8	1.29 <sup>4</sup>	2.94	6.03	8.75	13.6	1.45	3.09	6.20	9.35	15.2
9	12	1.37	2.40	4.44	6.05	9.47	1.78	3.15	5.67	7.65	11.6	2.05	3.70	6.54	8.98	13.4	2.21	3.86	6.70	9.67	15.2
	16	0.94 <sup>3</sup>	1.94 <sup>4</sup>	4.00	5.61	9.03	1.31 <sup>4</sup>	2.65	5.18	7.16	11.2	1.56 <sup>4</sup>	3.16	6.01	8.43	12.9	1.72	3.32	6.19	9.12	14.6
	24	0.16 <sup>3</sup>	1.11 <sup>3</sup>	3.19 <sup>3</sup>	4.77 <sup>4</sup>	8.21	0.45 <sup>3</sup>	1.74 <sup>3</sup>	4.27 <sup>4</sup>	6.24	10.3	0.67 <sup>3</sup>	2.16 <sup>4</sup>	5.02	7.41	11.9	0.81 <sup>3</sup>	2.31 <sup>4</sup>	5.23	8.08	13.6
10	12	0.99 <sup>3</sup>	1.94 <sup>4</sup>	3.79	5.24	8.35	1.35 <sup>4</sup>	2.61	4.86	6.65	10.3	1.60 <sup>4</sup>	3.13	5.74	7.84	11.9	1.76	3.30	5.93	8.57	13.7
	16	0.52 <sup>3</sup>	1.43 <sup>3</sup>	3.30 <sup>4</sup>	4.74	7.86	0.83 <sup>3</sup>	2.05 <sup>4</sup>	4.32	6.10	9.75	1.06 <sup>3</sup>	2.51 <sup>4</sup>	5.13	7.23	11.3	1.20 <sup>3</sup>	2.68	5.34	7.94	13.0
	24		0.53 <sup>2</sup>	2.43 <sup>3</sup>	3.83 <sup>3</sup>	6.94 <sup>4</sup>		1.06 <sup>3</sup>	3.34 <sup>3</sup>	5.10 <sup>4</sup>	8.77	0.08 <sup>2</sup>	1.40 <sup>3</sup>	4.04 <sup>3</sup>	6.10	10.2	0.20 <sup>3</sup>	1.54 <sup>3</sup>	4.25 <sup>4</sup>	6.77	11.8
12	12	0.32 <sup>2</sup>	1.08 <sup>3</sup>	2.54 <sup>3</sup>	3.68 <sup>4</sup>	6.14	0.57 <sup>3</sup>	1.59 <sup>3</sup>	3.34 <sup>3</sup>	4.74 <sup>4</sup>	7.66	0.77 <sup>3</sup>	1.98 <sup>3</sup>	4.01 <sup>4</sup>	5.66	8.97	0.90 <sup>3</sup>	2.18 <sup>4</sup>	4.42 <sup>4</sup>	6.44	10.4
	16		0.53 <sup>2</sup>	2.03 <sup>3</sup>	3.14 <sup>3</sup>	5.59 <sup>4</sup>	0.01 <sup>2</sup>	0.98 <sup>2</sup>	2.76 <sup>3</sup>	4.15 <sup>3</sup>	7.07	0.17 <sup>2</sup>	1.29 <sup>3</sup>	3.36 <sup>3</sup>	4.99 <sup>4</sup>	8.28	0.27 <sup>2</sup>	1.45 <sup>3</sup>	3.73 <sup>3</sup>	5.71 <sup>4</sup>	9.63
	24			1.12 <sup>2</sup>	2.19 <sup>2</sup>	4.61 <sup>3</sup>			1.74 <sup>2</sup>	3.10 <sup>2</sup>	6.00 <sup>3</sup>		0.10 <sup>2</sup>	2.20 <sup>2</sup>	3.80 <sup>3</sup>	7.06 <sup>3</sup>		0.19 <sup>2</sup>	2.50 <sup>2</sup>	4.41 <sup>3</sup>	8.29 <sup>4</sup>
14	12		0.40 <sup>2</sup>	1.58 <sup>2</sup>	2.46 <sup>3</sup>	4.36 <sup>3</sup>		0.77 <sup>2</sup>	2.15 <sup>3</sup>	3.24 <sup>3</sup>	5.53 <sup>4</sup>	0.10 <sup>2</sup>	1.03 <sup>2</sup>	2.62 <sup>3</sup>	3.92 <sup>3</sup>	6.53	0.19 <sup>2</sup>	1.20 <sup>3</sup>	3.04 <sup>3</sup>	4.58 <sup>3</sup>	7.63
	16			1.08 <sup>1</sup>	1.93 <sup>2</sup>	3.82 <sup>3</sup>		0.16 <sup>1</sup>	1.59 <sup>2</sup>	2.66 <sup>2</sup>	4.94 <sup>3</sup>		0.34 <sup>2</sup>	1.98 <sup>2</sup>	3.25 <sup>3</sup>	5.84 <sup>3</sup>		0.44 <sup>2</sup>	2.33 <sup>2</sup>	3.84 <sup>3</sup>	6.88 <sup>4</sup>
	24			0.22 <sup>1</sup>	1.02 <sup>1</sup>	2.88 <sup>2</sup>			0.62 <sup>1</sup>	1.65 <sup>1</sup>	3.91 <sup>2</sup>			0.88 <sup>1</sup>	2.11 <sup>2</sup>	4.63 <sup>3</sup>			1.10 <sup>1</sup>	2.55 <sup>2</sup>	5.54 <sup>3</sup>
16	12			0.90 <sup>1</sup>	1.58 <sup>2</sup>	3.08 <sup>2</sup>		0.17 <sup>1</sup>	1.31 <sup>2</sup>	2.17 <sup>2</sup>	3.99 <sup>3</sup>		0.32 <sup>1</sup>	1.63 <sup>2</sup>	2.66 <sup>2</sup>	4.73 <sup>3</sup>		0.42 <sup>2</sup>	1.93 <sup>2</sup>	3.14 <sup>3</sup>	5.59 <sup>3</sup>
	16			0.43 <sup>1</sup>	1.08 <sup>1</sup>	2.57 <sup>2</sup>			0.78 <sup>1</sup>	1.62 <sup>1</sup>	3.42 <sup>2</sup>			1.03 <sup>1</sup>	2.03 <sup>2</sup>	4.07 <sup>3</sup>			1.26 <sup>1</sup>	2.43 <sup>2</sup>	4.86 <sup>3</sup>
	24				0.23 <sup>1</sup>	1.68 <sup>1</sup>				0.68 <sup>1</sup>	2.45 <sup>1</sup>			0.01 <sup>1</sup>	0.95 <sup>1</sup>	2.93 <sup>2</sup>			0.10 <sup>1</sup>	1.22 <sup>1</sup>	3.59 <sup>2</sup>
18	12			0.42 <sup>1</sup>	0.96 <sup>1</sup>	2.16 <sup>2</sup>			0.72 <sup>1</sup>	1.40 <sup>1</sup>	2.87 <sup>2</sup>			0.94 <sup>1</sup>	1.75 <sup>2</sup>	3.42 <sup>2</sup>			1.13 <sup>1</sup>	2.10 <sup>2</sup>	4.09 <sup>3</sup>
	16				0.50 <sup>1</sup>	1.68 <sup>1</sup>			0.23 <sup>1</sup>	0.89 <sup>1</sup>	2.34 <sup>1</sup>			0.38 <sup>1</sup>	1.17 <sup>1</sup>	2.80 <sup>2</sup>			0.50 <sup>1</sup>	1.44 <sup>1</sup>	3.40 <sup>2</sup>
	24					0.87 <sup>1</sup>				0.02 <sup>1</sup>	1.44 <sup>1</sup>				0.17 <sup>1</sup>	1.73 <sup>1</sup>				0.32 <sup>1</sup>	2.20 <sup>1</sup>
20	12			0.09 <sup>1</sup>	0.52 <sup>1</sup>	1.50 <sup>1</sup>			0.31 <sup>1</sup>	0.86 <sup>1</sup>	2.06 <sup>1</sup>			0.45 <sup>1</sup>	1.10 <sup>1</sup>	2.46 <sup>2</sup>			0.57 <sup>1</sup>	1.35 <sup>1</sup>	2.98 <sup>2</sup>
	16				0.09 <sup>1</sup>	1.06 <sup>1</sup>				0.38 <sup>1</sup>	1.56 <sup>1</sup>				0.56 <sup>1</sup>	1.88 <sup>1</sup>				0.74 <sup>1</sup>	2.33 <sup>1</sup>
	24					0.30 <sup>1</sup>					0.72 <sup>1</sup>				0.89 <sup>1</sup>						1.22 <sup>1</sup>

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720



## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 40 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	362S162					362S200					362S250					362S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	1.38	2.46	4.69	6.46	10.2	1.80	3.26	6.04	8.20	12.5	2.07	3.80	6.87	9.62	14.4	2.24	3.95	7.01	10.2	16.0
	16	0.91 <sup>3</sup>	1.97	4.22	5.97	9.69	1.29 <sup>4</sup>	2.72	5.51	7.67	12.0	1.55	3.22	6.30	9.03	13.9	1.71	3.37	6.46	9.64	15.5
	24	0.05 <sup>3</sup>	1.05 <sup>3</sup>	3.33 <sup>4</sup>	5.06	8.80	0.34 <sup>3</sup>	1.72 <sup>3</sup>	4.51	6.67	11.1	0.57 <sup>3</sup>	2.13 <sup>4</sup>	5.24	7.92	12.8	0.71 <sup>3</sup>	2.28	5.43	8.52	14.3
9	12	0.94 <sup>3</sup>	1.94 <sup>4</sup>	4.00	5.61	9.03	1.31 <sup>4</sup>	2.65	5.18	7.16	11.2	1.56 <sup>4</sup>	3.16	6.01	8.43	12.9	1.72	3.32	6.19	9.12	14.6
	16	0.41 <sup>3</sup>	1.38 <sup>3</sup>	3.45 <sup>4</sup>	5.04	8.48	0.72 <sup>3</sup>	2.03 <sup>4</sup>	4.57	6.54	10.6	0.95 <sup>3</sup>	2.48	5.34	7.74	12.2	1.10 <sup>3</sup>	2.64	5.54	8.42	13.9
	24		0.36 <sup>2</sup>	2.46 <sup>3</sup>	4.00 <sup>3</sup>	7.44		0.91 <sup>3</sup>	3.45 <sup>3</sup>	5.40 <sup>4</sup>	9.45		1.24 <sup>3</sup>	4.11 <sup>3</sup>	6.47	11.0		1.38 <sup>3</sup>	4.33 <sup>4</sup>	7.11	12.6
10	12	0.52 <sup>3</sup>	1.43 <sup>3</sup>	3.30 <sup>4</sup>	4.74	7.86	0.83 <sup>3</sup>	2.05 <sup>4</sup>	4.32	6.10	9.75	1.06 <sup>3</sup>	2.51 <sup>4</sup>	5.13	7.23	11.3	1.20 <sup>3</sup>	2.68	5.34	7.94	13.0
	16		0.82 <sup>3</sup>	2.71 <sup>3</sup>	4.12 <sup>3</sup>	7.23	0.20 <sup>2</sup>	1.37 <sup>3</sup>	3.65 <sup>3</sup>	5.42 <sup>4</sup>	9.09	0.39 <sup>3</sup>	1.76 <sup>3</sup>	4.39 <sup>4</sup>	6.46	10.6	0.52 <sup>3</sup>	1.91 <sup>3</sup>	4.60 <sup>4</sup>	7.15	12.2
	24			1.65 <sup>2</sup>	3.01 <sup>3</sup>	6.10 <sup>3</sup>		0.17 <sup>2</sup>	2.46 <sup>3</sup>	4.19 <sup>3</sup>	7.87 <sup>4</sup>		0.42 <sup>2</sup>	3.05 <sup>3</sup>	5.09 <sup>3</sup>	9.18		0.52 <sup>3</sup>	3.27 <sup>3</sup>	5.70 <sup>3</sup>	10.7
12	12		0.53 <sup>2</sup>	2.03 <sup>3</sup>	3.14 <sup>3</sup>	5.59 <sup>4</sup>	0.01 <sup>2</sup>	0.98 <sup>2</sup>	2.76 <sup>3</sup>	4.15 <sup>3</sup>	7.07	0.17 <sup>2</sup>	1.29 <sup>3</sup>	3.36 <sup>3</sup>	4.99 <sup>4</sup>	8.28	0.27 <sup>2</sup>	1.45 <sup>3</sup>	3.73 <sup>3</sup>	5.71 <sup>4</sup>	9.63
	16			1.41 <sup>2</sup>	2.49 <sup>2</sup>	4.92 <sup>3</sup>		0.25 <sup>2</sup>	2.07 <sup>2</sup>	3.43 <sup>3</sup>	6.34 <sup>3</sup>		0.48 <sup>2</sup>	2.57 <sup>3</sup>	4.17 <sup>3</sup>	7.45 <sup>4</sup>		0.59 <sup>2</sup>	2.89 <sup>3</sup>	4.82 <sup>3</sup>	8.72
	24			0.34 <sup>1</sup>	1.35 <sup>1</sup>	3.74 <sup>2</sup>			0.86 <sup>1</sup>	2.17 <sup>2</sup>	5.06 <sup>3</sup>			1.20 <sup>2</sup>	2.75 <sup>2</sup>	5.96 <sup>3</sup>			1.43 <sup>2</sup>	3.27 <sup>2</sup>	7.09 <sup>3</sup>
14	12			1.08 <sup>1</sup>	1.93 <sup>2</sup>	3.82 <sup>3</sup>		0.16 <sup>1</sup>	1.59 <sup>2</sup>	2.66 <sup>2</sup>	4.94 <sup>3</sup>		0.34 <sup>2</sup>	1.98 <sup>2</sup>	3.25 <sup>3</sup>	5.84 <sup>3</sup>		0.44 <sup>2</sup>	2.33 <sup>2</sup>	3.84 <sup>3</sup>	6.88 <sup>4</sup>
	16			0.49 <sup>1</sup>	1.30 <sup>1</sup>	3.18 <sup>2</sup>			0.93 <sup>1</sup>	1.97 <sup>2</sup>	4.23 <sup>2</sup>			1.23 <sup>1</sup>	2.47 <sup>2</sup>	5.01 <sup>3</sup>			1.49 <sup>2</sup>	2.96 <sup>2</sup>	5.97 <sup>3</sup>
	24				0.23 <sup>1</sup>	2.06 <sup>1</sup>				0.78 <sup>1</sup>	3.00 <sup>1</sup>				1.11 <sup>1</sup>	3.58 <sup>2</sup>			0.04 <sup>1</sup>	1.44 <sup>1</sup>	4.38 <sup>2</sup>
16	12			0.43 <sup>1</sup>	1.08 <sup>1</sup>	2.57 <sup>2</sup>			0.78 <sup>1</sup>	1.62 <sup>1</sup>	3.42 <sup>2</sup>			1.03 <sup>1</sup>	2.03 <sup>2</sup>	4.07 <sup>3</sup>			1.26 <sup>1</sup>	2.43 <sup>2</sup>	4.86 <sup>3</sup>
	16				0.50 <sup>1</sup>	1.96 <sup>1</sup>			0.17 <sup>1</sup>	0.97 <sup>1</sup>	2.76 <sup>1</sup>			0.33 <sup>1</sup>	1.29 <sup>1</sup>	3.29 <sup>2</sup>			0.46 <sup>1</sup>	1.60 <sup>1</sup>	3.99 <sup>2</sup>
	24					0.92 <sup>1</sup>					1.61 <sup>1</sup>				0.03 <sup>1</sup>	1.94 <sup>1</sup>				0.19 <sup>1</sup>	2.49 <sup>1</sup>
18	12				0.50 <sup>1</sup>	1.68 <sup>1</sup>			0.23 <sup>1</sup>	0.89 <sup>1</sup>	2.34 <sup>1</sup>			0.38 <sup>1</sup>	1.17 <sup>1</sup>	2.80 <sup>2</sup>			0.50 <sup>1</sup>	1.44 <sup>1</sup>	3.40 <sup>2</sup>
	16					1.12 <sup>1</sup>				0.30 <sup>1</sup>	1.72 <sup>1</sup>				0.48 <sup>1</sup>	2.07 <sup>1</sup>				0.67 <sup>1</sup>	2.58 <sup>1</sup>
	24					0.17 <sup>1</sup>					0.66 <sup>1</sup>					0.82 <sup>1</sup>					1.18 <sup>1</sup>
20	12				0.09 <sup>1</sup>	1.06 <sup>1</sup>				0.38 <sup>1</sup>	1.56 <sup>1</sup>				0.56 <sup>1</sup>	1.88 <sup>1</sup>				0.74 <sup>1</sup>	2.33 <sup>1</sup>
	16					0.54 <sup>1</sup>					0.99 <sup>1</sup>					1.20 <sup>1</sup>				0.02 <sup>1</sup>	1.57 <sup>1</sup>
	24										0.01 <sup>1</sup>					0.04 <sup>1</sup>					0.27 <sup>1</sup>

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 50 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	362S162					362S200					362S250					362S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	1.03 <sup>4</sup>	2.09	4.33	6.09	9.80	1.41	2.85	5.64	7.80	12.1	1.68	3.36	6.44	9.18	14.0	1.84	3.51	6.60	9.78	15.6
	16	0.47 <sup>3</sup>	1.50 <sup>4</sup>	3.77	5.50	9.24	0.80 <sup>3</sup>	2.21 <sup>4</sup>	5.00	7.16	11.5	1.05 <sup>4</sup>	2.66	5.76	8.47	13.3	1.20 <sup>4</sup>	2.81	5.94	9.07	14.9
	24		0.42 <sup>3</sup>	2.72 <sup>3</sup>	4.41 <sup>4</sup>	8.17	0.00 <sup>3</sup>	1.02 <sup>3</sup>	3.82 <sup>3</sup>	5.96	10.4		1.37 <sup>3</sup>	4.49 <sup>4</sup>	7.13	12.0	0.01 <sup>3</sup>	1.51 <sup>4</sup>	4.69	7.72	13.6
9	12	0.54 <sup>3</sup>	1.52 <sup>3</sup>	3.59 <sup>4</sup>	5.18	8.61	0.86 <sup>3</sup>	2.18 <sup>4</sup>	4.72	6.69	10.7	1.10 <sup>3</sup>	2.65	5.50	7.91	12.4	1.25 <sup>4</sup>	2.80	5.70	8.59	14.1
	16		0.85 <sup>3</sup>	2.94 <sup>3</sup>	4.51 <sup>4</sup>	7.95	0.18 <sup>3</sup>	1.45 <sup>3</sup>	3.99 <sup>4</sup>	5.95	9.99	0.39 <sup>3</sup>	1.84 <sup>3</sup>	4.71 <sup>4</sup>	7.09	11.6	0.52 <sup>3</sup>	1.99 <sup>4</sup>	4.92	7.75	13.3
	24			1.78 <sup>2</sup>	3.29 <sup>3</sup>	6.72 <sup>3</sup>		0.14 <sup>2</sup>	2.68 <sup>3</sup>	4.61 <sup>3</sup>	8.68 <sup>4</sup>		0.40 <sup>3</sup>	3.27 <sup>3</sup>	5.58 <sup>3</sup>	10.1		0.51 <sup>3</sup>	3.49 <sup>3</sup>	6.20 <sup>4</sup>	11.7
10	12	0.09 <sup>2</sup>	0.97 <sup>3</sup>	2.85 <sup>3</sup>	4.27 <sup>4</sup>	7.39	0.35 <sup>3</sup>	1.54 <sup>3</sup>	3.82 <sup>4</sup>	5.59	9.25	0.55 <sup>3</sup>	1.94 <sup>3</sup>	4.57 <sup>4</sup>	6.65	10.8	0.69 <sup>3</sup>	2.09 <sup>4</sup>	4.78	7.34	12.4
	16		0.25 <sup>2</sup>	2.16 <sup>3</sup>	3.54 <sup>3</sup>	6.65 <sup>4</sup>		0.75 <sup>3</sup>	3.04 <sup>3</sup>	4.79 <sup>3</sup>	8.46		1.06 <sup>3</sup>	3.70 <sup>3</sup>	5.75 <sup>4</sup>	9.86		1.19 <sup>3</sup>	3.91 <sup>3</sup>	6.40 <sup>4</sup>	11.4
	24			0.93 <sup>2</sup>	2.25 <sup>2</sup>	5.33 <sup>3</sup>			1.66 <sup>2</sup>	3.36 <sup>3</sup>	7.03 <sup>3</sup>			2.15 <sup>2</sup>	4.15 <sup>3</sup>	8.22 <sup>3</sup>			2.36 <sup>3</sup>	4.71 <sup>3</sup>	9.65 <sup>4</sup>
12	12		0.03 <sup>2</sup>	1.56 <sup>2</sup>	2.64 <sup>3</sup>	5.08 <sup>3</sup>		0.43 <sup>2</sup>	2.23 <sup>2</sup>	3.60 <sup>3</sup>	6.52 <sup>3</sup>		0.67 <sup>2</sup>	2.76 <sup>3</sup>	4.37 <sup>3</sup>	7.65 <sup>4</sup>		0.79 <sup>3</sup>	3.09 <sup>3</sup>	5.04 <sup>3</sup>	8.94
	16			0.85 <sup>1</sup>	1.90 <sup>2</sup>	4.31 <sup>3</sup>			1.44 <sup>2</sup>	2.78 <sup>2</sup>	5.68 <sup>3</sup>			1.86 <sup>2</sup>	3.43 <sup>3</sup>	6.68 <sup>3</sup>			2.13 <sup>2</sup>	4.01 <sup>3</sup>	7.88 <sup>3</sup>
	24				0.60 <sup>1</sup>	2.96 <sup>2</sup>			0.07 <sup>1</sup>	1.34 <sup>1</sup>	4.20 <sup>2</sup>			0.30 <sup>1</sup>	1.81 <sup>2</sup>	4.97 <sup>2</sup>			0.46 <sup>1</sup>	2.23 <sup>2</sup>	6.00 <sup>3</sup>
14	12			0.63 <sup>1</sup>	1.45 <sup>1</sup>	3.33 <sup>2</sup>			1.08 <sup>1</sup>	2.14 <sup>2</sup>	4.40 <sup>3</sup>			1.41 <sup>2</sup>	2.66 <sup>2</sup>	5.21 <sup>3</sup>			1.69 <sup>2</sup>	3.17 <sup>2</sup>	6.18 <sup>3</sup>
	16				0.74 <sup>1</sup>	2.59 <sup>1</sup>			0.34 <sup>1</sup>	1.35 <sup>1</sup>	3.59 <sup>2</sup>			0.56 <sup>1</sup>	1.76 <sup>1</sup>	4.26 <sup>2</sup>			0.73 <sup>1</sup>	2.17 <sup>2</sup>	5.14 <sup>3</sup>
	24					1.32 <sup>1</sup>			0.01 <sup>1</sup>	2.19 <sup>1</sup>				0.23 <sup>1</sup>	2.63 <sup>1</sup>				0.44 <sup>1</sup>	3.33 <sup>2</sup>	
16	12			0.01 <sup>1</sup>	0.64 <sup>1</sup>	2.11 <sup>1</sup>			0.32 <sup>1</sup>	1.13 <sup>1</sup>	2.92 <sup>2</sup>			0.50 <sup>1</sup>	1.47 <sup>1</sup>	3.47 <sup>2</sup>			0.65 <sup>1</sup>	1.80 <sup>1</sup>	4.20 <sup>2</sup>
	16					1.42 <sup>1</sup>			0.40 <sup>1</sup>	2.16 <sup>1</sup>				0.63 <sup>1</sup>	2.58 <sup>1</sup>				0.86 <sup>1</sup>	3.21 <sup>2</sup>	
	24					0.25 <sup>1</sup>				0.86 <sup>1</sup>					1.06 <sup>1</sup>					1.51 <sup>1</sup>	
18	12				0.09 <sup>1</sup>	1.26 <sup>1</sup>			0.44 <sup>1</sup>	1.87 <sup>1</sup>				0.65 <sup>1</sup>	2.24 <sup>1</sup>					0.85 <sup>1</sup>	2.77 <sup>1</sup>
	16					0.62 <sup>1</sup>				1.17 <sup>1</sup>					1.41 <sup>1</sup>						1.85 <sup>1</sup>
	24																				0.27 <sup>1</sup>
20	12					0.66 <sup>1</sup>				1.13 <sup>1</sup>				0.08 <sup>1</sup>	1.36 <sup>1</sup>					0.19 <sup>1</sup>	1.75 <sup>1</sup>
	16					0.07 <sup>1</sup>				0.48 <sup>1</sup>					0.59 <sup>1</sup>						0.89 <sup>1</sup>
	24																				

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 60 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	362S162					362S200					362S250					362S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	0.69 <sup>3</sup>	1.73 <sup>4</sup>	3.99	5.74	9.46	1.04 <sup>4</sup>	2.46	5.25	7.41	11.8	1.29 <sup>4</sup>	2.94	6.03	8.75	13.6	1.45	3.09	6.20	9.35	15.2
	16	0.05 <sup>3</sup>	1.05 <sup>3</sup>	3.33 <sup>4</sup>	5.06	8.80	0.34 <sup>3</sup>	1.72 <sup>3</sup>	4.51	6.67	11.1	0.57 <sup>3</sup>	2.13 <sup>4</sup>	5.24	7.92	12.8	0.71 <sup>3</sup>	2.28	5.43	8.52	14.3
	24			2.13 <sup>3</sup>	3.80 <sup>3</sup>	7.56 <sup>4</sup>		0.36 <sup>3</sup>	3.16 <sup>3</sup>	5.29 <sup>4</sup>	9.73		0.65 <sup>3</sup>	3.77 <sup>3</sup>	6.38 <sup>4</sup>	11.3		0.77 <sup>3</sup>	3.98 <sup>4</sup>	6.95	12.8
9	12	0.16 <sup>3</sup>	1.11 <sup>3</sup>	3.19 <sup>3</sup>	4.77 <sup>4</sup>	8.21	0.45 <sup>3</sup>	1.74 <sup>3</sup>	4.27 <sup>4</sup>	6.24	10.3	0.67 <sup>3</sup>	2.16 <sup>4</sup>	5.02	7.41	11.9	0.81 <sup>3</sup>	2.31 <sup>4</sup>	5.23	8.08	13.6
	16		0.36 <sup>2</sup>	2.46 <sup>3</sup>	4.00 <sup>3</sup>	7.44		0.91 <sup>3</sup>	3.45 <sup>3</sup>	5.40 <sup>4</sup>	9.45		1.24 <sup>3</sup>	4.11 <sup>3</sup>	6.47	11.0		1.38 <sup>3</sup>	4.33 <sup>4</sup>	7.11	12.6
	24			1.14 <sup>2</sup>	2.62 <sup>2</sup>	6.04 <sup>3</sup>			1.97 <sup>2</sup>	3.86 <sup>3</sup>	7.94 <sup>3</sup>			2.48 <sup>3</sup>	4.75 <sup>3</sup>	9.25 <sup>4</sup>			2.70 <sup>3</sup>	5.33 <sup>3</sup>	10.8
10	12		0.53 <sup>2</sup>	2.43 <sup>3</sup>	3.83 <sup>3</sup>	6.94 <sup>4</sup>		1.06 <sup>3</sup>	3.34 <sup>3</sup>	5.10 <sup>4</sup>	8.77	0.08 <sup>2</sup>	1.40 <sup>3</sup>	4.04 <sup>3</sup>	6.10	10.2	0.20 <sup>3</sup>	1.54 <sup>3</sup>	4.25 <sup>4</sup>	6.77	11.8
	16			1.65 <sup>2</sup>	3.01 <sup>3</sup>	6.10 <sup>3</sup>		0.17 <sup>2</sup>	2.46 <sup>3</sup>	4.19 <sup>3</sup>	7.87 <sup>4</sup>		0.42 <sup>2</sup>	3.05 <sup>3</sup>	5.09 <sup>3</sup>	9.18		0.52 <sup>3</sup>	3.27 <sup>3</sup>	5.70 <sup>3</sup>	10.7
	24			0.27 <sup>1</sup>	1.55 <sup>2</sup>	4.60 <sup>2</sup>			0.92 <sup>2</sup>	2.58 <sup>2</sup>	6.25 <sup>3</sup>			1.31 <sup>2</sup>	3.27 <sup>3</sup>	7.31 <sup>3</sup>			1.51 <sup>2</sup>	3.79 <sup>3</sup>	8.67 <sup>3</sup>
12	12			1.12 <sup>2</sup>	2.19 <sup>2</sup>	4.61 <sup>3</sup>			1.74 <sup>2</sup>	3.10 <sup>2</sup>	6.00 <sup>3</sup>		0.10 <sup>2</sup>	2.20 <sup>2</sup>	3.80 <sup>3</sup>	7.06 <sup>3</sup>		0.19 <sup>2</sup>	2.50 <sup>2</sup>	4.41 <sup>3</sup>	8.29 <sup>4</sup>
	16			0.34 <sup>1</sup>	1.35 <sup>1</sup>	3.74 <sup>2</sup>			0.86 <sup>1</sup>	2.17 <sup>2</sup>	5.06 <sup>3</sup>			1.20 <sup>2</sup>	2.75 <sup>2</sup>	5.96 <sup>3</sup>			1.43 <sup>2</sup>	3.27 <sup>2</sup>	7.09 <sup>3</sup>
	24					2.24 <sup>1</sup>				0.58 <sup>1</sup>	3.41 <sup>2</sup>				0.94 <sup>1</sup>	4.05 <sup>2</sup>				1.28 <sup>1</sup>	4.99 <sup>2</sup>
14	12			0.22 <sup>1</sup>	1.02 <sup>1</sup>	2.88 <sup>2</sup>			0.62 <sup>1</sup>	1.65 <sup>1</sup>	3.91 <sup>2</sup>			0.88 <sup>1</sup>	2.11 <sup>2</sup>	4.63 <sup>3</sup>			1.10 <sup>1</sup>	2.55 <sup>2</sup>	5.54 <sup>3</sup>
	16				0.23 <sup>1</sup>	2.06 <sup>1</sup>			0.78 <sup>1</sup>	3.00 <sup>1</sup>				1.11 <sup>1</sup>	3.58 <sup>2</sup>			0.04 <sup>1</sup>	1.44 <sup>1</sup>	4.38 <sup>2</sup>	
	24					0.65 <sup>1</sup>				1.45 <sup>1</sup>					1.76 <sup>1</sup>						2.37 <sup>1</sup>
16	12				0.23 <sup>1</sup>	1.68 <sup>1</sup>			0.68 <sup>1</sup>	2.45 <sup>1</sup>				0.01 <sup>1</sup>	0.95 <sup>1</sup>	2.93 <sup>2</sup>			0.10 <sup>1</sup>	1.22 <sup>1</sup>	3.59 <sup>2</sup>
	16					0.92 <sup>1</sup>				1.61 <sup>1</sup>				0.03 <sup>1</sup>	1.94 <sup>1</sup>					0.19 <sup>1</sup>	2.49 <sup>1</sup>
	24									0.18 <sup>1</sup>					0.26 <sup>1</sup>						0.61 <sup>1</sup>
18	12					0.87 <sup>1</sup>			0.02 <sup>1</sup>	1.44 <sup>1</sup>				0.17 <sup>1</sup>	1.73 <sup>1</sup>					0.32 <sup>1</sup>	2.20 <sup>1</sup>
	16					0.17 <sup>1</sup>				0.66 <sup>1</sup>					0.82 <sup>1</sup>						1.18 <sup>1</sup>
	24																				
20	12					0.30 <sup>1</sup>					0.72 <sup>1</sup>				0.89 <sup>1</sup>						1.22 <sup>1</sup>
	16										0.01 <sup>1</sup>				0.04 <sup>1</sup>						0.27 <sup>1</sup>
	24																				

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 70 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	362S162					362S200					362S250					362S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	0.36 <sup>3</sup>	1.39 <sup>3</sup>	3.66 <sup>4</sup>	5.39	9.13	0.68 <sup>3</sup>	2.08 <sup>4</sup>	4.88	7.04	11.4	0.92 <sup>3</sup>	2.53	5.63	8.33	13.2	1.07 <sup>4</sup>	2.68	5.81	8.93	14.8
	16		0.63 <sup>3</sup>	2.92 <sup>3</sup>	4.62 <sup>4</sup>	8.37	0.00 <sup>3</sup>	1.25 <sup>3</sup>	4.04 <sup>4</sup>	6.19	10.6	0.11 <sup>3</sup>	1.62 <sup>3</sup>	4.73 <sup>4</sup>	7.39	12.3	0.24 <sup>3</sup>	1.76 <sup>4</sup>	4.93	7.98	13.8
	24			1.57 <sup>2</sup>	3.21 <sup>3</sup>	6.97 <sup>3</sup>			2.53 <sup>3</sup>	4.64 <sup>3</sup>	9.09 <sup>4</sup>			3.09 <sup>3</sup>	5.65 <sup>4</sup>	10.6		0.07 <sup>3</sup>	3.30 <sup>3</sup>	6.21 <sup>4</sup>	12.0
9	12		0.72 <sup>3</sup>	2.82 <sup>3</sup>	4.38 <sup>4</sup>	7.82	0.05 <sup>3</sup>	1.31 <sup>3</sup>	3.85 <sup>3</sup>	5.81	9.86	0.25 <sup>3</sup>	1.69 <sup>3</sup>	4.56 <sup>4</sup>	6.93	11.4	0.38 <sup>3</sup>	1.83 <sup>4</sup>	4.77	7.59	13.1
	16			2.00 <sup>3</sup>	3.52 <sup>3</sup>	6.96 <sup>4</sup>		0.39 <sup>3</sup>	2.93 <sup>3</sup>	4.86 <sup>3</sup>	8.93		0.67 <sup>3</sup>	3.55 <sup>3</sup>	5.87 <sup>4</sup>	10.4		0.79 <sup>3</sup>	3.76 <sup>3</sup>	6.49 <sup>4</sup>	12.0
	24			0.54 <sup>2</sup>	1.98 <sup>2</sup>	5.38 <sup>3</sup>			1.29 <sup>2</sup>	3.16 <sup>3</sup>	7.24 <sup>3</sup>			1.73 <sup>2</sup>	3.96 <sup>3</sup>	8.45 <sup>3</sup>			1.94 <sup>3</sup>	4.50 <sup>3</sup>	9.88 <sup>4</sup>
10	12		0.12 <sup>2</sup>	2.03 <sup>3</sup>	3.41 <sup>3</sup>	6.51 <sup>4</sup>		0.60 <sup>2</sup>	2.89 <sup>3</sup>	4.63 <sup>3</sup>	8.31 <sup>4</sup>		0.90 <sup>3</sup>	3.53 <sup>3</sup>	5.58 <sup>4</sup>	9.69		1.02 <sup>3</sup>	3.75 <sup>3</sup>	6.23 <sup>4</sup>	11.2
	16			1.16 <sup>2</sup>	2.50 <sup>2</sup>	5.58 <sup>3</sup>			1.92 <sup>2</sup>	3.63 <sup>3</sup>	7.31 <sup>3</sup>			2.44 <sup>3</sup>	4.45 <sup>3</sup>	8.53 <sup>4</sup>			2.65 <sup>3</sup>	5.04 <sup>3</sup>	9.99
	24				0.90 <sup>1</sup>	3.92 <sup>2</sup>			0.22 <sup>1</sup>	1.86 <sup>2</sup>	5.50 <sup>2</sup>			0.53 <sup>2</sup>	2.45 <sup>2</sup>	6.46 <sup>3</sup>			0.70 <sup>2</sup>	2.92 <sup>2</sup>	7.73 <sup>3</sup>
12	12			0.72 <sup>1</sup>	1.76 <sup>2</sup>	4.17 <sup>2</sup>			1.29 <sup>2</sup>	2.62 <sup>2</sup>	5.52 <sup>3</sup>			1.69 <sup>2</sup>	3.26 <sup>2</sup>	6.50 <sup>3</sup>			1.95 <sup>2</sup>	3.82 <sup>3</sup>	7.68 <sup>3</sup>
	16				0.85 <sup>1</sup>	3.21 <sup>2</sup>			0.33 <sup>1</sup>	1.61 <sup>1</sup>	4.48 <sup>2</sup>			0.59 <sup>1</sup>	2.11 <sup>2</sup>	5.29 <sup>3</sup>			0.77 <sup>1</sup>	2.56 <sup>2</sup>	6.35 <sup>3</sup>
	24					1.56 <sup>1</sup>					2.67 <sup>1</sup>				0.14 <sup>1</sup>	3.19 <sup>2</sup>				0.39 <sup>1</sup>	4.04 <sup>2</sup>
14	12				0.61 <sup>1</sup>	2.45 <sup>1</sup>			0.20 <sup>1</sup>	1.20 <sup>1</sup>	3.44 <sup>2</sup>			0.40 <sup>1</sup>	1.59 <sup>1</sup>	4.09 <sup>2</sup>			0.55 <sup>1</sup>	1.98 <sup>2</sup>	4.94 <sup>2</sup>
	16					1.56 <sup>1</sup>				0.26 <sup>1</sup>	2.46 <sup>1</sup>				0.51 <sup>1</sup>	2.93 <sup>1</sup>				0.77 <sup>1</sup>	3.67 <sup>2</sup>
	24					0.02 <sup>1</sup>				0.76 <sup>1</sup>					0.96 <sup>1</sup>						1.47 <sup>1</sup>
16	12					1.29 <sup>1</sup>				0.26 <sup>1</sup>	2.02 <sup>1</sup>				0.48 <sup>1</sup>	2.42 <sup>1</sup>				0.69 <sup>1</sup>	3.02 <sup>1</sup>
	16					0.46 <sup>1</sup>					1.10 <sup>1</sup>					1.34 <sup>1</sup>					1.82 <sup>1</sup>
	24																				
18	12					0.50 <sup>1</sup>					1.03 <sup>1</sup>					1.26 <sup>1</sup>					1.68 <sup>1</sup>
	16										0.19 <sup>1</sup>					0.27 <sup>1</sup>					0.57 <sup>1</sup>
	24																				
20	12										0.35 <sup>1</sup>					0.45 <sup>1</sup>					0.73 <sup>1</sup>
	16																				
	24																				

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 0 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	400S162					400S200					400S250					400S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	3.23	4.44	6.93	9.20	13.4	3.79	5.45	8.64	11.3	16.2	4.08	6.07	9.35	12.8	18.7	4.24	6.19	9.54	13.3	20.2
	16	3.23	4.44	6.93	9.20	13.4	3.79	5.45	8.64	11.3	16.2	4.08	6.07	9.35	12.8	18.7	4.24	6.19	9.54	13.3	20.2
	24	3.23	4.44	6.93	9.20	13.4	3.79	5.45	8.64	11.3	16.2	4.08	6.07	9.35	12.8	18.7	4.24	6.19	9.53	13.3	20.2
9	12	3.15	4.33	6.66	8.82	12.7	3.69	5.29	8.25	10.8	15.3	3.98	5.93	9.12	12.4	17.7	4.14	6.05	9.21	12.9	19.3
	16	3.15	4.33	6.66	8.82	12.7	3.69	5.29	8.24	10.8	15.3	3.98	5.93	9.12	12.4	17.7	4.14	6.05	9.21	12.9	19.3
	24	3.15	4.33	6.66	8.82	12.7	3.69	5.29	8.24	10.8	15.3	3.98	5.93	9.12	12.4	17.7	4.14	6.05	9.21	12.9	19.3
10	12	3.05	4.19	6.34	8.37	12.0	3.59	5.10	7.80	10.2	14.4	3.87	5.77	8.77	11.8	16.6	4.03	5.90	8.85	12.5	18.4
	16	3.05	4.19	6.33	8.37	12.0	3.59	5.10	7.80	10.2	14.4	3.87	5.77	8.77	11.8	16.6	4.03	5.90	8.84	12.5	18.4
	24	3.05	4.19	6.33	8.37	12.0	3.59	5.10	7.80	10.2	14.4	3.87	5.77	8.77	11.8	16.6	4.03	5.90	8.84	12.5	18.4
12	12	2.81	3.86	5.57	7.24	10.2	3.33	4.66	6.79	8.77	12.2	3.61	5.39	7.92	10.2	14.2	3.77	5.55	8.01	11.0	16.1
	16	2.81	3.85	5.57	7.24	10.2	3.33	4.66	6.79	8.77	12.2	3.61	5.39	7.92	10.2	14.2	3.77	5.55	8.01	11.0	16.1
	24	2.81	3.85	5.57	7.24	10.2	3.33	4.66	6.79	8.77	12.2	3.61	5.39	7.92	10.2	14.2	3.77	5.55	8.01	11.0	16.1
14	12	2.52	3.46	4.71	5.98	8.33	3.03	4.16	5.70	7.22	9.99	3.31	4.85	6.66	8.44	11.7	3.47	5.14	7.22	9.47	13.3
	16	2.52	3.46	4.71	5.98	8.33	3.03	4.16	5.70	7.22	9.99	3.30	4.85	6.66	8.44	11.7	3.47	5.14	7.22	9.47	13.3
	24	2.52	3.45	4.71	5.98	8.33	3.03	4.16	5.70	7.21	9.99	3.30	4.85	6.66	8.44	11.7	3.47	5.14	7.22	9.47	13.3
16	12	2.21	3.02	3.96	4.91	6.78	2.68	3.63	4.75	5.91	8.13	2.98	4.25	5.56	6.93	9.55	3.15	4.68	6.29	7.93	10.9
	16	2.21	3.02	3.96	4.91	6.78	2.68	3.63	4.75	5.91	8.13	2.98	4.25	5.56	6.93	9.55	3.15	4.68	6.29	7.93	10.9
	24	2.20	3.02	3.96	4.91	6.78	2.67	3.63	4.75	5.91	8.13	2.97	4.25	5.56	6.93	9.55	3.15	4.68	6.29	7.93	10.9
18	12	1.89	2.58	3.29	4.07	5.57	2.29	3.10	3.96	4.89	6.70	2.63	3.64	4.65	5.75	7.90	2.81	4.18	5.33	6.60	9.08
	16	1.88	2.58	3.29	4.07	5.57	2.28	3.10	3.96	4.89	6.70	2.63	3.64	4.65	5.75	7.89	2.81	4.18	5.33	6.59	9.08
	24	1.88	2.58	3.29	4.07	5.57	2.28	3.10	3.96	4.89	6.70	2.63	3.64	4.65	5.75	7.89	2.80	4.17	5.33	6.59	9.08
20	12	1.61	2.20	2.76	3.40	4.64	1.95	2.64	3.31	4.09	5.58	2.30	3.10	3.90	4.82	6.61	2.48	3.56	4.48	5.54	7.62
	16	1.61	2.20	2.76	3.40	4.63	1.95	2.64	3.31	4.09	5.58	2.30	3.10	3.90	4.82	6.61	2.48	3.56	4.48	5.54	7.62
	24	1.61	2.20	2.76	3.40	4.63	1.95	2.64	3.31	4.09	5.58	2.30	3.10	3.90	4.82	6.60	2.47	3.55	4.48	5.54	7.62

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 10 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	400S162					400S200					400S250					400S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	2.81	4.02	6.53	8.79	13.0	3.34	5.00	8.19	10.9	15.8	3.63	5.59	8.90	12.4	18.3	3.80	5.72	9.10	12.9	19.8
	16	2.67	3.88	6.40	8.65	12.9	3.19	4.85	8.05	10.7	15.7	3.49	5.44	8.75	12.2	18.1	3.66	5.57	8.96	12.7	19.6
	24	2.41	3.61	6.14	8.39	12.7	2.91	4.56	7.76	10.4	15.4	3.20	5.13	8.46	11.9	17.8	3.38	5.27	8.68	12.4	19.3
9	12	2.61	3.78	6.14	8.28	12.3	3.12	4.70	7.67	10.2	14.8	3.41	5.32	8.52	11.8	17.1	3.58	5.46	8.65	12.3	18.7
	16	2.44	3.61	5.97	8.11	12.1	2.94	4.52	7.48	10.0	14.7	3.23	5.12	8.33	11.6	16.9	3.40	5.26	8.47	12.1	18.6
	24	2.12	3.28	5.65	7.77	11.8	2.59	4.15	7.12	9.64	14.3	2.88	4.74	7.96	11.2	16.5	3.05	4.89	8.11	11.7	18.2
10	12	2.39	3.51	5.69	7.70	11.4	2.88	4.37	7.08	9.45	13.7	3.16	5.00	8.02	11.0	15.9	3.34	5.15	8.14	11.7	17.6
	16	2.19	3.30	5.49	7.49	11.2	2.66	4.14	6.86	9.22	13.5	2.95	4.76	7.78	10.7	15.6	3.12	4.91	7.92	11.4	17.4
	24	1.81	2.91	5.10	7.08	10.8	2.25	3.71	6.43	8.78	13.1	2.53	4.29	7.32	10.3	15.2	2.70	4.46	7.48	11.0	16.9
12	12	1.89	2.90	4.67	6.31	9.36	2.33	3.63	5.80	7.76	11.3	2.61	4.26	6.82	9.08	13.2	2.79	4.45	7.00	9.91	15.0
	16	1.64	2.63	4.41	6.03	9.10	2.05	3.33	5.51	7.46	11.1	2.32	3.93	6.49	8.75	12.8	2.50	4.13	6.69	9.57	14.7
	24	1.18 <sup>3</sup>	2.13	3.94	5.52	8.61	1.54 <sup>4</sup>	2.79	4.98	6.90	10.5	1.80	3.33	5.90	8.13	12.2	1.96	3.52	6.11	8.93	14.0
14	12	1.40	2.26	3.64	4.88	7.32	1.78	2.87	4.52	6.03	8.92	2.04	3.41	5.34	7.11	10.4	2.21	3.69	5.87	8.06	12.0
	16	1.12 <sup>3</sup>	1.95 <sup>4</sup>	3.35	4.59	7.04	1.46 <sup>4</sup>	2.53	4.20	5.70	8.61	1.71 <sup>4</sup>	3.03	4.98	6.75	10.1	1.87	3.29	5.49	7.66	11.6
	24	0.62 <sup>3</sup>	1.41 <sup>3</sup>	2.84 <sup>3</sup>	4.05 <sup>4</sup>	6.51	0.90 <sup>3</sup>	1.93 <sup>3</sup>	3.64 <sup>4</sup>	5.11	8.04	1.12 <sup>3</sup>	2.36 <sup>4</sup>	4.34	6.08	9.40	1.26 <sup>3</sup>	2.59 <sup>4</sup>	4.81	6.94	10.9
16	12	0.97 <sup>3</sup>	1.68 <sup>4</sup>	2.79	3.74	5.69	1.27 <sup>3</sup>	2.17	3.47	4.64	6.97	1.50 <sup>4</sup>	2.60	4.11	5.50	8.18	1.66 <sup>4</sup>	2.92	4.70	6.34	9.47
	16	0.68 <sup>3</sup>	1.36 <sup>3</sup>	2.50 <sup>3</sup>	3.44	5.40	0.94 <sup>3</sup>	1.82 <sup>3</sup>	3.15 <sup>4</sup>	4.31	6.65	1.15 <sup>3</sup>	2.21 <sup>4</sup>	3.75	5.13	7.81	1.30 <sup>3</sup>	2.49 <sup>4</sup>	4.30	5.93	9.06
	24	0.19 <sup>2</sup>	0.81 <sup>2</sup>	1.99 <sup>3</sup>	2.91 <sup>3</sup>	4.87 <sup>4</sup>	0.38 <sup>2</sup>	1.21 <sup>3</sup>	2.59 <sup>3</sup>	3.73 <sup>3</sup>	6.08	0.55 <sup>2</sup>	1.53 <sup>3</sup>	3.11 <sup>3</sup>	4.47 <sup>4</sup>	7.14	0.66 <sup>2</sup>	1.75 <sup>3</sup>	3.59 <sup>3</sup>	5.19	8.33
18	12	0.61 <sup>2</sup>	1.19 <sup>3</sup>	2.10 <sup>3</sup>	2.87 <sup>4</sup>	4.45	0.84 <sup>3</sup>	1.57 <sup>3</sup>	2.64 <sup>4</sup>	3.58	5.49	1.05 <sup>3</sup>	1.92 <sup>4</sup>	3.15	4.27	6.47	1.18 <sup>3</sup>	2.23 <sup>4</sup>	3.65	4.95	7.52
	16	0.34 <sup>2</sup>	0.88 <sup>2</sup>	1.82 <sup>3</sup>	2.58 <sup>3</sup>	4.16 <sup>4</sup>	0.53 <sup>2</sup>	1.24 <sup>3</sup>	2.33 <sup>3</sup>	3.26 <sup>3</sup>	5.18	0.70 <sup>2</sup>	1.53 <sup>3</sup>	2.80 <sup>3</sup>	3.90 <sup>4</sup>	6.10	0.82 <sup>3</sup>	1.79 <sup>3</sup>	3.25 <sup>3</sup>	4.54	7.12
	24		0.36 <sup>1</sup>	1.34 <sup>2</sup>	2.08 <sup>2</sup>	3.66 <sup>3</sup>		0.66 <sup>2</sup>	1.80 <sup>2</sup>	2.71 <sup>3</sup>	4.62 <sup>3</sup>	0.10 <sup>1</sup>	0.88 <sup>2</sup>	2.19 <sup>3</sup>	3.27 <sup>3</sup>	5.44 <sup>4</sup>	0.18 <sup>2</sup>	1.05 <sup>2</sup>	2.56 <sup>3</sup>	3.83 <sup>3</sup>	6.40
20	12	0.35 <sup>2</sup>	0.81 <sup>2</sup>	1.58 <sup>3</sup>	2.21 <sup>3</sup>	3.51 <sup>4</sup>	0.52 <sup>2</sup>	1.12 <sup>3</sup>	2.01 <sup>3</sup>	2.78 <sup>3</sup>	4.37	0.68 <sup>2</sup>	1.38 <sup>3</sup>	2.41 <sup>3</sup>	3.33 <sup>4</sup>	5.15	0.79 <sup>2</sup>	1.61 <sup>3</sup>	2.80 <sup>3</sup>	3.88	6.03
	16	0.09 <sup>1</sup>	0.52 <sup>2</sup>	1.31 <sup>2</sup>	1.93 <sup>3</sup>	3.24 <sup>3</sup>	0.22 <sup>1</sup>	0.80 <sup>2</sup>	1.71 <sup>2</sup>	2.48 <sup>3</sup>	4.06 <sup>3</sup>	0.35 <sup>2</sup>	1.01 <sup>2</sup>	2.08 <sup>3</sup>	2.99 <sup>3</sup>	4.80 <sup>4</sup>	0.43 <sup>2</sup>	1.19 <sup>3</sup>	2.42 <sup>3</sup>	3.49 <sup>3</sup>	5.63
	24		0.03 <sup>1</sup>	0.86 <sup>1</sup>	1.46 <sup>2</sup>	2.76 <sup>2</sup>		0.25 <sup>1</sup>	1.21 <sup>1</sup>	1.96 <sup>2</sup>	3.54 <sup>3</sup>		0.39 <sup>1</sup>	1.50 <sup>2</sup>	2.39 <sup>2</sup>	4.17 <sup>3</sup>		0.49 <sup>2</sup>	1.77 <sup>2</sup>	2.82 <sup>3</sup>	4.94 <sup>3</sup>

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 20 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	400S162					400S200					400S250					400S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	2.41	3.61	6.14	8.39	12.7	2.91	4.56	7.76	10.4	15.4	3.20	5.13	8.46	11.9	17.8	3.38	5.27	8.68	12.4	19.3
	16	2.16	3.35	5.89	8.12	12.4	2.64	4.27	7.48	10.1	15.2	2.93	4.84	8.18	11.6	17.5	3.10	4.98	8.40	12.1	19.1
	24	1.67	2.85	5.41	7.62	11.9	2.11	3.73	6.93	9.59	14.7	2.40	4.26	7.62	11.0	16.9	2.57	4.41	7.86	11.5	18.5
9	12	2.12	3.28	5.65	7.77	11.8	2.59	4.15	7.12	9.64	14.3	2.88	4.74	7.96	11.2	16.5	3.05	4.89	8.11	11.7	18.2
	16	1.81	2.96	5.34	7.44	11.5	2.26	3.81	6.78	9.29	14.0	2.54	4.37	7.59	10.8	16.2	2.72	4.52	7.76	11.4	17.8
	24	1.23 <sup>4</sup>	2.35	4.75	6.82	10.9	1.63	3.15	6.12	8.61	13.4	1.90	3.66	6.90	10.0	15.4	2.07	3.82	7.09	10.6	17.1
10	12	1.81	2.91	5.10	7.08	10.8	2.25	3.71	6.43	8.78	13.1	2.53	4.29	7.32	10.3	15.2	2.70	4.46	7.48	11.0	16.9
	16	1.45	2.53	4.74	6.69	10.4	1.86	3.30	6.02	8.35	12.7	2.13	3.85	6.88	9.79	14.7	2.30	4.02	7.07	10.5	16.5
	24	0.80 <sup>3</sup>	1.84 <sup>4</sup>	4.06	5.96	9.72	1.15 <sup>3</sup>	2.55	5.26	7.56	12.0	1.40 <sup>4</sup>	3.04	6.07	8.91	13.9	1.56 <sup>4</sup>	3.20	6.27	9.61	15.6
12	12	1.18 <sup>3</sup>	2.13	3.94	5.52	8.61	1.54 <sup>4</sup>	2.79	4.98	6.90	10.5	1.80	3.33	5.90	8.13	12.2	1.96	3.52	6.11	8.93	14.0
	16	0.76 <sup>3</sup>	1.68 <sup>3</sup>	3.50 <sup>4</sup>	5.06	8.15	1.08 <sup>3</sup>	2.30 <sup>4</sup>	4.49	6.39	10.0	1.32 <sup>3</sup>	2.78	5.35	7.56	11.7	1.47 <sup>4</sup>	2.97	5.58	8.34	13.4
	24	0.03 <sup>2</sup>	0.88 <sup>3</sup>	2.72 <sup>3</sup>	4.22 <sup>3</sup>	7.32	0.27 <sup>2</sup>	1.42 <sup>3</sup>	3.62 <sup>3</sup>	5.47 <sup>4</sup>	9.15	0.46 <sup>3</sup>	1.80 <sup>3</sup>	4.36 <sup>4</sup>	6.52	10.6	0.59 <sup>3</sup>	1.96 <sup>3</sup>	4.60 <sup>4</sup>	7.26	12.3
14	12	0.62 <sup>3</sup>	1.41 <sup>3</sup>	2.84 <sup>3</sup>	4.05 <sup>4</sup>	6.51	0.90 <sup>3</sup>	1.93 <sup>3</sup>	3.64 <sup>4</sup>	5.11	8.04	1.12 <sup>3</sup>	2.36 <sup>4</sup>	4.34	6.08	9.40	1.26 <sup>3</sup>	2.59 <sup>4</sup>	4.81	6.94	10.9
	16	0.19 <sup>2</sup>	0.93 <sup>2</sup>	2.39 <sup>3</sup>	3.57 <sup>3</sup>	6.03	0.41 <sup>2</sup>	1.40 <sup>3</sup>	3.13 <sup>3</sup>	4.59 <sup>4</sup>	7.53	0.60 <sup>2</sup>	1.77 <sup>3</sup>	3.77 <sup>3</sup>	5.48	8.79	0.72 <sup>3</sup>	1.96 <sup>3</sup>	4.21 <sup>4</sup>	6.29	10.2
	24		0.10 <sup>1</sup>	1.60 <sup>2</sup>	2.73 <sup>2</sup>	5.18 <sup>3</sup>		0.49 <sup>2</sup>	2.25 <sup>2</sup>	3.66 <sup>3</sup>	6.60 <sup>3</sup>		0.73 <sup>2</sup>	2.77 <sup>3</sup>	4.43 <sup>3</sup>	7.71 <sup>4</sup>		0.86 <sup>2</sup>	3.13 <sup>3</sup>	5.13 <sup>3</sup>	9.04
16	12	0.19 <sup>2</sup>	0.81 <sup>2</sup>	1.99 <sup>3</sup>	2.91 <sup>3</sup>	4.87 <sup>4</sup>	0.38 <sup>2</sup>	1.21 <sup>3</sup>	2.59 <sup>3</sup>	3.73 <sup>3</sup>	6.08	0.55 <sup>2</sup>	1.53 <sup>3</sup>	3.11 <sup>3</sup>	4.47 <sup>4</sup>	7.14	0.66 <sup>2</sup>	1.75 <sup>3</sup>	3.59 <sup>3</sup>	5.19	8.33
	16		0.34 <sup>1</sup>	1.55 <sup>2</sup>	2.45 <sup>3</sup>	4.41 <sup>3</sup>		0.69 <sup>2</sup>	2.10 <sup>2</sup>	3.22 <sup>3</sup>	5.57 <sup>3</sup>	0.02 <sup>2</sup>	0.94 <sup>2</sup>	2.56 <sup>3</sup>	3.89 <sup>3</sup>	6.53 <sup>4</sup>	0.10 <sup>2</sup>	1.10 <sup>2</sup>	2.97 <sup>3</sup>	4.55 <sup>3</sup>	7.67
	24			0.79 <sup>1</sup>	1.65 <sup>2</sup>	3.59 <sup>2</sup>			1.26 <sup>1</sup>	2.33 <sup>2</sup>	4.68 <sup>3</sup>			1.60 <sup>2</sup>	2.88 <sup>2</sup>	5.48 <sup>3</sup>			1.90 <sup>2</sup>	3.42 <sup>3</sup>	6.51 <sup>3</sup>
18	12		0.36 <sup>1</sup>	1.34 <sup>2</sup>	2.08 <sup>2</sup>	3.66 <sup>3</sup>		0.66 <sup>2</sup>	1.80 <sup>2</sup>	2.71 <sup>3</sup>	4.62 <sup>3</sup>	0.10 <sup>1</sup>	0.88 <sup>2</sup>	2.19 <sup>3</sup>	3.27 <sup>3</sup>	5.44 <sup>4</sup>	0.18 <sup>2</sup>	1.05 <sup>2</sup>	2.56 <sup>3</sup>	3.83 <sup>3</sup>	6.40
	16			0.92 <sup>1</sup>	1.64 <sup>2</sup>	3.22 <sup>2</sup>		0.16 <sup>1</sup>	1.34 <sup>2</sup>	2.23 <sup>2</sup>	4.14 <sup>3</sup>		0.31 <sup>1</sup>	1.66 <sup>2</sup>	2.72 <sup>2</sup>	4.86 <sup>3</sup>		0.41 <sup>2</sup>	1.97 <sup>2</sup>	3.22 <sup>3</sup>	5.76 <sup>3</sup>
	24			0.22 <sup>1</sup>	0.89 <sup>1</sup>	2.45 <sup>1</sup>			0.55 <sup>1</sup>	1.40 <sup>1</sup>	3.29 <sup>2</sup>			0.76 <sup>1</sup>	1.78 <sup>1</sup>	3.86 <sup>2</sup>			0.95 <sup>1</sup>	2.16 <sup>2</sup>	4.65 <sup>3</sup>
20	12		0.03 <sup>1</sup>	0.86 <sup>1</sup>	1.46 <sup>2</sup>	2.76 <sup>2</sup>		0.25 <sup>1</sup>	1.21 <sup>1</sup>	1.96 <sup>2</sup>	3.54 <sup>3</sup>		0.39 <sup>1</sup>	1.50 <sup>2</sup>	2.39 <sup>2</sup>	4.17 <sup>3</sup>		0.49 <sup>2</sup>	1.77 <sup>2</sup>	2.82 <sup>3</sup>	4.94 <sup>3</sup>
	16			0.48 <sup>1</sup>	1.05 <sup>1</sup>	2.34 <sup>2</sup>			0.78 <sup>1</sup>	1.51 <sup>1</sup>	3.08 <sup>2</sup>			1.01 <sup>1</sup>	1.87 <sup>2</sup>	3.62 <sup>2</sup>			1.22 <sup>1</sup>	2.24 <sup>2</sup>	4.33 <sup>3</sup>
	24			0.36 <sup>1</sup>	1.63 <sup>1</sup>			0.06 <sup>1</sup>	0.74 <sup>1</sup>	2.29 <sup>1</sup>				0.18 <sup>1</sup>	0.99 <sup>1</sup>	2.68 <sup>1</sup>			0.28 <sup>1</sup>	1.25 <sup>1</sup>	3.29 <sup>2</sup>

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 30 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	400S162					400S200					400S250					400S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	2.03	3.23	5.77	8.00	12.3	2.50	4.14	7.34	10.0	15.0	2.79	4.69	8.04	11.4	17.4	2.97	4.83	8.26	12.0	18.9
	16	1.67	2.85	5.41	7.62	11.9	2.11	3.73	6.93	9.59	14.7	2.40	4.26	7.62	11.0	16.9	2.57	4.41	7.86	11.5	18.5
	24	0.98 <sup>4</sup>	2.14	4.71	6.89	11.3	1.37	2.95	6.15	8.79	13.9	1.64	3.44	6.82	10.1	16.1	1.81	3.59	7.07	10.7	17.6
9	12	1.66	2.80	5.19	7.28	11.3	2.10	3.64	6.61	9.11	13.8	2.38	4.19	7.42	10.6	16.0	2.55	4.34	7.59	11.2	17.6
	16	1.23 <sup>4</sup>	2.35	4.75	6.82	10.9	1.63	3.15	6.12	8.61	13.4	1.90	3.66	6.90	10.0	15.4	2.07	3.82	7.09	10.6	17.1
	24	0.44 <sup>3</sup>	1.52 <sup>3</sup>	3.93	5.94	10.0	0.77 <sup>3</sup>	2.23 <sup>4</sup>	5.19	7.65	12.5	1.02 <sup>3</sup>	2.68	5.92	8.97	14.4	1.17 <sup>4</sup>	2.83	6.14	9.57	16.0
10	12	1.28 <sup>4</sup>	2.35	4.56	6.50	10.2	1.67	3.11	5.82	8.15	12.5	1.94	3.64	6.67	9.56	14.5	2.11	3.81	6.86	10.3	16.2
	16	0.80 <sup>3</sup>	1.84 <sup>4</sup>	4.06	5.96	9.72	1.15 <sup>3</sup>	2.55	5.26	7.56	12.0	1.40 <sup>4</sup>	3.04	6.07	8.91	13.9	1.56 <sup>4</sup>	3.20	6.27	9.61	15.6
	24		0.91 <sup>3</sup>	3.14 <sup>3</sup>	4.97 <sup>4</sup>	8.75	0.20 <sup>3</sup>	1.53 <sup>3</sup>	4.23 <sup>4</sup>	6.48	11.0	0.41 <sup>3</sup>	1.92 <sup>3</sup>	4.95 <sup>4</sup>	7.70	12.7	0.55 <sup>3</sup>	2.07 <sup>4</sup>	5.18	8.38	14.3
12	12	0.57 <sup>3</sup>	1.47 <sup>3</sup>	3.29 <sup>4</sup>	4.84	7.94	0.87 <sup>3</sup>	2.07 <sup>3</sup>	4.26	6.15	9.81	1.09 <sup>3</sup>	2.53 <sup>4</sup>	5.09	7.29	11.4	1.24 <sup>3</sup>	2.70	5.32	8.06	13.1
	16	0.03 <sup>2</sup>	0.88 <sup>3</sup>	2.72 <sup>3</sup>	4.22 <sup>3</sup>	7.32	0.27 <sup>2</sup>	1.42 <sup>3</sup>	3.62 <sup>3</sup>	5.47 <sup>4</sup>	9.15	0.46 <sup>3</sup>	1.80 <sup>3</sup>	4.36 <sup>4</sup>	6.52	10.6	0.59 <sup>3</sup>	1.96 <sup>3</sup>	4.60 <sup>4</sup>	7.26	12.3
	24			1.70 <sup>2</sup>	3.12 <sup>3</sup>	6.21 <sup>3</sup>		0.28 <sup>2</sup>	2.48 <sup>3</sup>	4.26 <sup>3</sup>	7.95 <sup>4</sup>		0.53 <sup>2</sup>	3.08 <sup>3</sup>	5.16 <sup>3</sup>	9.22 <sup>4</sup>		0.64 <sup>3</sup>	3.31 <sup>3</sup>	5.82 <sup>3</sup>	10.8
14	12		0.71 <sup>2</sup>	2.18 <sup>3</sup>	3.35 <sup>3</sup>	5.81 <sup>4</sup>	0.19 <sup>2</sup>	1.16 <sup>3</sup>	2.90 <sup>3</sup>	4.34 <sup>3</sup>	7.28	0.35 <sup>2</sup>	1.49 <sup>3</sup>	3.51 <sup>3</sup>	5.21 <sup>4</sup>	8.51	0.47 <sup>2</sup>	1.67 <sup>3</sup>	3.92 <sup>3</sup>	5.98	9.91
	16		0.10 <sup>1</sup>	1.60 <sup>2</sup>	2.73 <sup>2</sup>	5.18 <sup>3</sup>		0.49 <sup>2</sup>	2.25 <sup>2</sup>	3.66 <sup>3</sup>	6.60 <sup>3</sup>		0.73 <sup>2</sup>	2.77 <sup>3</sup>	4.43 <sup>3</sup>	7.71 <sup>4</sup>		0.86 <sup>2</sup>	3.13 <sup>3</sup>	5.13 <sup>3</sup>	9.04
	24			0.60 <sup>1</sup>	1.66 <sup>1</sup>	4.08 <sup>2</sup>			1.14 <sup>1</sup>	2.47 <sup>2</sup>	5.40 <sup>3</sup>			1.50 <sup>2</sup>	3.09 <sup>2</sup>	6.30 <sup>3</sup>			1.76 <sup>2</sup>	3.65 <sup>3</sup>	7.50 <sup>3</sup>
16	12		0.12 <sup>1</sup>	1.35 <sup>2</sup>	2.24 <sup>2</sup>	4.19 <sup>3</sup>		0.45 <sup>2</sup>	1.87 <sup>2</sup>	2.98 <sup>3</sup>	5.34 <sup>3</sup>		0.66 <sup>2</sup>	2.30 <sup>2</sup>	3.62 <sup>3</sup>	6.25 <sup>4</sup>		0.80 <sup>2</sup>	2.68 <sup>3</sup>	4.25 <sup>3</sup>	7.36 <sup>4</sup>
	16			0.79 <sup>1</sup>	1.65 <sup>2</sup>	3.59 <sup>2</sup>			1.26 <sup>1</sup>	2.33 <sup>2</sup>	4.68 <sup>3</sup>			1.60 <sup>2</sup>	2.88 <sup>2</sup>	5.48 <sup>3</sup>			1.90 <sup>2</sup>	3.42 <sup>3</sup>	6.51 <sup>3</sup>
	24				0.65 <sup>1</sup>	2.55 <sup>1</sup>			0.20 <sup>1</sup>	1.22 <sup>1</sup>	3.54 <sup>2</sup>			0.40 <sup>1</sup>	1.62 <sup>1</sup>	4.13 <sup>2</sup>			0.55 <sup>1</sup>	2.00 <sup>2</sup>	5.02 <sup>2</sup>
18	12			0.73 <sup>1</sup>	1.44 <sup>1</sup>	3.01 <sup>2</sup>			1.12 <sup>1</sup>	2.00 <sup>2</sup>	3.91 <sup>3</sup>		0.06 <sup>1</sup>	1.42 <sup>2</sup>	2.47 <sup>2</sup>	4.60 <sup>3</sup>		0.12 <sup>1</sup>	1.70 <sup>2</sup>	2.93 <sup>2</sup>	5.46 <sup>3</sup>
	16			0.22 <sup>1</sup>	0.89 <sup>1</sup>	2.45 <sup>1</sup>			0.55 <sup>1</sup>	1.40 <sup>1</sup>	3.29 <sup>2</sup>			0.76 <sup>1</sup>	1.78 <sup>1</sup>	3.86 <sup>2</sup>			0.95 <sup>1</sup>	2.16 <sup>2</sup>	4.65 <sup>3</sup>
	24					1.48 <sup>1</sup>				0.37 <sup>1</sup>	2.23 <sup>1</sup>				0.60 <sup>1</sup>	2.60 <sup>1</sup>			0.83 <sup>1</sup>	3.26 <sup>2</sup>	
20	12			0.30 <sup>1</sup>	0.87 <sup>1</sup>	2.15 <sup>1</sup>			0.59 <sup>1</sup>	1.30 <sup>1</sup>	2.87 <sup>2</sup>			0.79 <sup>1</sup>	1.64 <sup>1</sup>	3.37 <sup>2</sup>			0.97 <sup>1</sup>	1.97 <sup>2</sup>	4.05 <sup>2</sup>
	16				0.36 <sup>1</sup>	1.63 <sup>1</sup>			0.06 <sup>1</sup>	0.74 <sup>1</sup>	2.29 <sup>1</sup>			0.18 <sup>1</sup>	0.99 <sup>1</sup>	2.68 <sup>1</sup>			0.28 <sup>1</sup>	1.25 <sup>1</sup>	3.29 <sup>2</sup>
	24					0.74 <sup>1</sup>				1.30 <sup>1</sup>					1.51 <sup>1</sup>				0.02 <sup>1</sup>	1.99 <sup>1</sup>	

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720



## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 40 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	400S162					400S200					400S250					400S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	1.67	2.85	5.41	7.62	11.9	2.11	3.73	6.93	9.59	14.7	2.40	4.26	7.62	11.0	16.9	2.57	4.41	7.86	11.5	18.5
	16	1.20	2.37	4.94	7.13	11.5	1.61	3.20	6.41	9.05	14.2	1.89	3.71	7.08	10.4	16.4	2.06	3.86	7.33	11.0	17.9
	24	0.34 <sup>3</sup>	1.47 <sup>4</sup>	4.05	6.19	10.6	0.68 <sup>3</sup>	2.22	5.42	8.03	13.2	0.93 <sup>4</sup>	2.66	6.06	9.31	15.3	1.08 <sup>4</sup>	2.80	6.32	9.87	16.8
9	12	1.23 <sup>4</sup>	2.35	4.75	6.82	10.9	1.63	3.15	6.12	8.61	13.4	1.90	3.66	6.90	10.0	15.4	2.07	3.82	7.09	10.6	17.1
	16	0.70 <sup>3</sup>	1.79 <sup>4</sup>	4.19	6.23	10.3	1.05 <sup>4</sup>	2.53	5.49	7.96	12.8	1.30 <sup>4</sup>	3.00	6.24	9.31	14.7	1.46	3.15	6.45	9.91	16.4
	24		0.75 <sup>3</sup>	3.16 <sup>3</sup>	5.13 <sup>4</sup>	9.24		1.39 <sup>3</sup>	4.34 <sup>4</sup>	6.75	11.6	0.20 <sup>3</sup>	1.77 <sup>4</sup>	5.01	7.98	13.4	0.34 <sup>3</sup>	1.91 <sup>4</sup>	5.24	8.58	15.0
10	12	0.80 <sup>3</sup>	1.84 <sup>4</sup>	4.06	5.96	9.72	1.15 <sup>3</sup>	2.55	5.26	7.56	12.0	1.40 <sup>4</sup>	3.04	6.07	8.91	13.9	1.56 <sup>4</sup>	3.20	6.27	9.61	15.6
	16	0.21 <sup>3</sup>	1.21 <sup>3</sup>	3.43 <sup>4</sup>	5.29	9.06	0.50 <sup>3</sup>	1.85 <sup>3</sup>	4.56 <sup>4</sup>	6.83	11.3	0.73 <sup>3</sup>	2.28 <sup>4</sup>	5.31	8.09	13.0	0.87 <sup>3</sup>	2.43	5.53	8.78	14.7
	24		0.07 <sup>2</sup>	2.30 <sup>3</sup>	4.07 <sup>3</sup>	7.85 <sup>4</sup>		0.60 <sup>3</sup>	3.29 <sup>3</sup>	5.48 <sup>3</sup>	9.98		0.91 <sup>3</sup>	3.93 <sup>3</sup>	6.59 <sup>4</sup>	11.5		1.04 <sup>3</sup>	4.16 <sup>3</sup>	7.24	13.2
12	12	0.03 <sup>2</sup>	0.88 <sup>3</sup>	2.72 <sup>3</sup>	4.22 <sup>3</sup>	7.32	0.27 <sup>2</sup>	1.42 <sup>3</sup>	3.62 <sup>3</sup>	5.47 <sup>4</sup>	9.15	0.46 <sup>3</sup>	1.80 <sup>3</sup>	4.36 <sup>4</sup>	6.52	10.6	0.59 <sup>3</sup>	1.96 <sup>3</sup>	4.60 <sup>4</sup>	7.26	12.3
	16		0.17 <sup>2</sup>	2.02 <sup>2</sup>	3.47 <sup>3</sup>	6.56 <sup>3</sup>		0.64 <sup>2</sup>	2.84 <sup>3</sup>	4.64 <sup>3</sup>	8.33 <sup>4</sup>		0.93 <sup>3</sup>	3.49 <sup>3</sup>	5.59 <sup>3</sup>	9.67		1.06 <sup>3</sup>	3.72 <sup>3</sup>	6.28 <sup>4</sup>	11.3
	24			0.81 <sup>1</sup>	2.16 <sup>2</sup>	5.22 <sup>3</sup>			1.49 <sup>2</sup>	3.19 <sup>2</sup>	6.87 <sup>3</sup>			1.95 <sup>2</sup>	3.96 <sup>3</sup>	7.97 <sup>3</sup>			2.16 <sup>2</sup>	4.54 <sup>3</sup>	9.42 <sup>4</sup>
14	12		0.10 <sup>1</sup>	1.60 <sup>2</sup>	2.73 <sup>2</sup>	5.18 <sup>3</sup>		0.49 <sup>2</sup>	2.25 <sup>2</sup>	3.66 <sup>3</sup>	6.60 <sup>3</sup>		0.73 <sup>2</sup>	2.77 <sup>3</sup>	4.43 <sup>3</sup>	7.71 <sup>4</sup>		0.86 <sup>2</sup>	3.13 <sup>3</sup>	5.13 <sup>3</sup>	9.04
	16			0.92 <sup>1</sup>	2.00 <sup>2</sup>	4.43 <sup>3</sup>			1.49 <sup>2</sup>	2.85 <sup>2</sup>	5.78 <sup>3</sup>			1.90 <sup>2</sup>	3.51 <sup>3</sup>	6.74 <sup>3</sup>			2.19 <sup>2</sup>	4.12 <sup>3</sup>	7.99 <sup>3</sup>
	24			0.73 <sup>1</sup>	3.12 <sup>2</sup>				0.17 <sup>1</sup>	1.45 <sup>1</sup>	4.35 <sup>2</sup>			0.41 <sup>1</sup>	1.93 <sup>2</sup>	5.06 <sup>2</sup>			0.57 <sup>1</sup>	2.36 <sup>2</sup>	6.14 <sup>3</sup>
16	12			0.79 <sup>1</sup>	1.65 <sup>2</sup>	3.59 <sup>2</sup>			1.26 <sup>1</sup>	2.33 <sup>2</sup>	4.68 <sup>3</sup>			1.60 <sup>2</sup>	2.88 <sup>2</sup>	5.48 <sup>3</sup>			1.90 <sup>2</sup>	3.42 <sup>3</sup>	6.51 <sup>3</sup>
	16			0.14 <sup>1</sup>	0.96 <sup>1</sup>	2.88 <sup>2</sup>			0.53 <sup>1</sup>	1.57 <sup>1</sup>	3.90 <sup>2</sup>			0.77 <sup>1</sup>	2.01 <sup>2</sup>	4.56 <sup>2</sup>			0.98 <sup>1</sup>	2.45 <sup>2</sup>	5.49 <sup>3</sup>
	24					1.66 <sup>1</sup>				0.27 <sup>1</sup>	2.55 <sup>1</sup>				0.53 <sup>1</sup>	2.97 <sup>1</sup>				0.78 <sup>1</sup>	3.74 <sup>2</sup>
18	12			0.22 <sup>1</sup>	0.89 <sup>1</sup>	2.45 <sup>1</sup>			0.55 <sup>1</sup>	1.40 <sup>1</sup>	3.29 <sup>2</sup>			0.76 <sup>1</sup>	1.78 <sup>1</sup>	3.86 <sup>2</sup>			0.95 <sup>1</sup>	2.16 <sup>2</sup>	4.65 <sup>3</sup>
	16				0.25 <sup>1</sup>	1.79 <sup>1</sup>				0.69 <sup>1</sup>	2.56 <sup>1</sup>				0.97 <sup>1</sup>	3.00 <sup>1</sup>			0.09 <sup>1</sup>	1.25 <sup>1</sup>	3.69 <sup>2</sup>
	24					0.66 <sup>1</sup>					1.32 <sup>1</sup>					1.52 <sup>1</sup>					2.06 <sup>1</sup>
20	12				0.36 <sup>1</sup>	1.63 <sup>1</sup>			0.06 <sup>1</sup>	0.74 <sup>1</sup>	2.29 <sup>1</sup>			0.18 <sup>1</sup>	0.99 <sup>1</sup>	2.68 <sup>1</sup>			0.28 <sup>1</sup>	1.25 <sup>1</sup>	3.29 <sup>2</sup>
	16					1.02 <sup>1</sup>				0.08 <sup>1</sup>	1.61 <sup>1</sup>				0.24 <sup>1</sup>	1.88 <sup>1</sup>				0.40 <sup>1</sup>	2.39 <sup>1</sup>
	24										0.45 <sup>1</sup>					0.51 <sup>1</sup>					0.87 <sup>1</sup>

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 50 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	400S162					400S200					400S250					400S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	1.32	2.49	5.05	7.25	11.6	1.73	3.33	6.54	9.18	14.3	2.01	3.84	7.22	10.6	16.5	2.18	3.99	7.46	11.1	18.1
	16	0.76 <sup>3</sup>	1.91	4.49	6.65	11.0	1.13 <sup>4</sup>	2.70	5.90	8.53	13.7	1.40	3.17	6.56	9.85	15.8	1.56	3.32	6.82	10.4	17.4
	24		0.83 <sup>3</sup>	3.43 <sup>4</sup>	5.53	9.94	0.02 <sup>3</sup>	1.52 <sup>4</sup>	4.71	7.30	12.5	0.25 <sup>3</sup>	1.91 <sup>4</sup>	5.32	8.51	14.5	0.40 <sup>3</sup>	2.05	5.59	9.08	16.0
9	12	0.83 <sup>3</sup>	1.93 <sup>4</sup>	4.33	6.37	10.5	1.19 <sup>4</sup>	2.68	5.64	8.12	12.9	1.45 <sup>4</sup>	3.16	6.40	9.48	14.9	1.61	3.32	6.61	10.1	16.5
	16	0.20 <sup>3</sup>	1.25 <sup>3</sup>	3.67 <sup>4</sup>	5.67	9.77	0.50 <sup>3</sup>	1.94 <sup>4</sup>	4.90	7.34	12.2	0.74 <sup>3</sup>	2.37	5.61	8.63	14.1	0.89 <sup>3</sup>	2.52	5.84	9.23	15.7
	24		0.03 <sup>2</sup>	2.45 <sup>3</sup>	4.36 <sup>3</sup>	8.49		0.60 <sup>3</sup>	3.54 <sup>3</sup>	5.91 <sup>4</sup>	10.8		0.92 <sup>3</sup>	4.16 <sup>3</sup>	7.05	12.5		1.04 <sup>3</sup>	4.39 <sup>4</sup>	7.64	14.0
10	12	0.35 <sup>3</sup>	1.36 <sup>3</sup>	3.59 <sup>4</sup>	5.45	9.22	0.66 <sup>3</sup>	2.02 <sup>4</sup>	4.73	7.00	11.5	0.89 <sup>3</sup>	2.46 <sup>4</sup>	5.49	8.29	13.2	1.04 <sup>3</sup>	2.62	5.71	8.98	14.9
	16		0.62 <sup>3</sup>	2.85 <sup>3</sup>	4.66 <sup>3</sup>	8.44		1.21 <sup>3</sup>	3.91 <sup>3</sup>	6.14 <sup>4</sup>	10.6	0.10 <sup>3</sup>	1.57 <sup>3</sup>	4.60 <sup>4</sup>	7.32	12.3	0.23 <sup>3</sup>	1.72 <sup>3</sup>	4.83 <sup>4</sup>	7.99	13.9
	24			1.53 <sup>2</sup>	3.23 <sup>3</sup>	7.01 <sup>3</sup>			2.43 <sup>3</sup>	4.57 <sup>3</sup>	9.08 <sup>4</sup>			2.98 <sup>3</sup>	5.56 <sup>3</sup>	10.5		0.08 <sup>3</sup>	3.21 <sup>3</sup>	6.18 <sup>3</sup>	12.1
12	12		0.34 <sup>2</sup>	2.19 <sup>3</sup>	3.65 <sup>3</sup>	6.75 <sup>4</sup>		0.83 <sup>2</sup>	3.03 <sup>3</sup>	4.84 <sup>3</sup>	8.53		1.14 <sup>3</sup>	3.70 <sup>3</sup>	5.82 <sup>4</sup>	9.90		1.27 <sup>3</sup>	3.93 <sup>3</sup>	6.51 <sup>4</sup>	11.5
	16			1.39 <sup>2</sup>	2.79 <sup>2</sup>	5.87 <sup>3</sup>			2.14 <sup>2</sup>	3.89 <sup>3</sup>	7.58 <sup>3</sup>		0.14 <sup>2</sup>	2.69 <sup>3</sup>	4.75 <sup>3</sup>	8.79 <sup>4</sup>		0.23 <sup>2</sup>	2.91 <sup>3</sup>	5.37 <sup>3</sup>	10.3
	24			0.01 <sup>1</sup>	1.29 <sup>1</sup>	4.33 <sup>2</sup>			0.59 <sup>1</sup>	2.23 <sup>2</sup>	5.89 <sup>3</sup>			0.93 <sup>2</sup>	2.87 <sup>2</sup>	6.83 <sup>3</sup>			1.11 <sup>2</sup>	3.37 <sup>2</sup>	8.18 <sup>3</sup>
14	12			1.08 <sup>1</sup>	2.17 <sup>2</sup>	4.61 <sup>3</sup>			1.67 <sup>2</sup>	3.04 <sup>2</sup>	5.98 <sup>3</sup>		0.05 <sup>2</sup>	2.11 <sup>2</sup>	3.73 <sup>3</sup>	6.97 <sup>3</sup>		0.13 <sup>2</sup>	2.42 <sup>2</sup>	4.36 <sup>3</sup>	8.24 <sup>4</sup>
	16			0.30 <sup>1</sup>	1.34 <sup>1</sup>	3.75 <sup>2</sup>			0.80 <sup>1</sup>	2.12 <sup>2</sup>	5.03 <sup>2</sup>			1.12 <sup>1</sup>	2.69 <sup>2</sup>	5.87 <sup>3</sup>			1.35 <sup>2</sup>	3.20 <sup>2</sup>	7.03 <sup>3</sup>
	24					2.26 <sup>1</sup>			0.53 <sup>1</sup>	3.40 <sup>1</sup>				0.88 <sup>1</sup>	3.95 <sup>2</sup>				1.21 <sup>1</sup>	4.91 <sup>2</sup>	
16	12			0.29 <sup>1</sup>	1.13 <sup>1</sup>	3.05 <sup>2</sup>			0.70 <sup>1</sup>	1.75 <sup>1</sup>	4.08 <sup>2</sup>			0.97 <sup>1</sup>	2.22 <sup>2</sup>	4.78 <sup>3</sup>			1.20 <sup>1</sup>	2.68 <sup>2</sup>	5.73 <sup>3</sup>
	16				0.35 <sup>1</sup>	2.24 <sup>1</sup>			0.89 <sup>1</sup>	3.20 <sup>1</sup>			0.04 <sup>1</sup>	1.24 <sup>1</sup>	3.73 <sup>2</sup>			0.15 <sup>1</sup>	1.58 <sup>1</sup>	4.58 <sup>2</sup>	
	24					0.86 <sup>1</sup>				1.67 <sup>1</sup>				1.93 <sup>1</sup>						2.59 <sup>1</sup>	
18	12				0.40 <sup>1</sup>	1.94 <sup>1</sup>			0.04 <sup>1</sup>	0.86 <sup>1</sup>	2.74 <sup>1</sup>			0.18 <sup>1</sup>	1.16 <sup>1</sup>	3.20 <sup>2</sup>			0.29 <sup>1</sup>	1.46 <sup>1</sup>	3.92 <sup>2</sup>
	16					1.20 <sup>1</sup>				0.06 <sup>1</sup>	1.91 <sup>1</sup>				0.25 <sup>1</sup>	2.23 <sup>1</sup>				0.44 <sup>1</sup>	2.84 <sup>1</sup>
	24										0.50 <sup>1</sup>				0.56 <sup>1</sup>						0.99 <sup>1</sup>
20	12					1.16 <sup>1</sup>				0.24 <sup>1</sup>	1.77 <sup>1</sup>			0.42 <sup>1</sup>	2.07 <sup>1</sup>					0.60 <sup>1</sup>	2.61 <sup>1</sup>
	16					0.47 <sup>1</sup>					1.00 <sup>1</sup>				1.16 <sup>1</sup>						1.60 <sup>1</sup>
	24																				

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 60 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	400S162					400S200					400S250					400S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	0.98 <sup>4</sup>	2.14	4.71	6.89	11.3	1.37	2.95	6.15	8.79	13.9	1.64	3.44	6.82	10.1	16.1	1.81	3.59	7.07	10.7	17.6
	16	0.34 <sup>3</sup>	1.47 <sup>4</sup>	4.05	6.19	10.6	0.68 <sup>3</sup>	2.22	5.42	8.03	13.2	0.93 <sup>4</sup>	2.66	6.06	9.31	15.3	1.08 <sup>4</sup>	2.80	6.32	9.87	16.8
	24		0.23 <sup>3</sup>	2.83 <sup>3</sup>	4.89 <sup>4</sup>	9.32		0.85 <sup>3</sup>	4.04 <sup>4</sup>	6.60	11.9		1.20 <sup>3</sup>	4.62 <sup>4</sup>	7.75	13.7		1.33 <sup>4</sup>	4.89	8.31	15.2
9	12	0.44 <sup>3</sup>	1.52 <sup>3</sup>	3.93	5.94	10.0	0.77 <sup>3</sup>	2.23 <sup>4</sup>	5.19	7.65	12.5	1.02 <sup>3</sup>	2.68	5.92	8.97	14.4	1.17 <sup>4</sup>	2.83	6.14	9.57	16.0
	16		0.75 <sup>3</sup>	3.16 <sup>3</sup>	5.13 <sup>4</sup>	9.24		1.39 <sup>3</sup>	4.34 <sup>4</sup>	6.75	11.6	0.20 <sup>3</sup>	1.77 <sup>4</sup>	5.01	7.98	13.4	0.34 <sup>3</sup>	1.91 <sup>4</sup>	5.24	8.58	15.0
	24			1.78 <sup>3</sup>	3.64 <sup>3</sup>	7.77 <sup>4</sup>			2.78 <sup>3</sup>	5.12 <sup>3</sup>	10.0		0.12 <sup>3</sup>	3.34 <sup>3</sup>	6.17 <sup>4</sup>	11.6		0.22 <sup>3</sup>	3.58 <sup>3</sup>	6.74 <sup>4</sup>	13.1
10	12		0.91 <sup>3</sup>	3.14 <sup>3</sup>	4.97 <sup>4</sup>	8.75	0.20 <sup>3</sup>	1.53 <sup>3</sup>	4.23 <sup>4</sup>	6.48	11.0	0.41 <sup>3</sup>	1.92 <sup>3</sup>	4.95 <sup>4</sup>	7.70	12.7	0.55 <sup>3</sup>	2.07 <sup>4</sup>	5.18	8.38	14.3
	16		0.07 <sup>2</sup>	2.30 <sup>3</sup>	4.07 <sup>3</sup>	7.85 <sup>4</sup>		0.60 <sup>3</sup>	3.29 <sup>3</sup>	5.48 <sup>3</sup>	9.98		0.91 <sup>3</sup>	3.93 <sup>3</sup>	6.59 <sup>4</sup>	11.5		1.04 <sup>3</sup>	4.16 <sup>3</sup>	7.24	13.2
	24			0.82 <sup>2</sup>	2.46 <sup>2</sup>	6.22 <sup>3</sup>			1.63 <sup>2</sup>	3.71 <sup>3</sup>	8.23 <sup>3</sup>			2.10 <sup>2</sup>	4.60 <sup>3</sup>	9.50 <sup>4</sup>			2.32 <sup>3</sup>	5.18 <sup>3</sup>	11.0 <sup>4</sup>
12	12			1.70 <sup>2</sup>	3.12 <sup>3</sup>	6.21 <sup>3</sup>		0.28 <sup>2</sup>	2.48 <sup>3</sup>	4.26 <sup>3</sup>	7.95 <sup>4</sup>		0.53 <sup>2</sup>	3.08 <sup>3</sup>	5.16 <sup>3</sup>	9.22 <sup>4</sup>		0.64 <sup>3</sup>	3.31 <sup>3</sup>	5.82 <sup>3</sup>	10.8
	16			0.81 <sup>1</sup>	2.16 <sup>2</sup>	5.22 <sup>3</sup>			1.49 <sup>2</sup>	3.19 <sup>2</sup>	6.87 <sup>3</sup>			1.95 <sup>2</sup>	3.96 <sup>3</sup>	7.97 <sup>3</sup>			2.16 <sup>2</sup>	4.54 <sup>3</sup>	9.42 <sup>4</sup>
	24				0.49 <sup>1</sup>	3.49 <sup>2</sup>				1.34 <sup>1</sup>	4.99 <sup>2</sup>				1.87 <sup>2</sup>	5.77 <sup>2</sup>			0.15 <sup>1</sup>	2.30 <sup>2</sup>	7.02 <sup>3</sup>
14	12			0.60 <sup>1</sup>	1.66 <sup>1</sup>	4.08 <sup>2</sup>			1.14 <sup>1</sup>	2.47 <sup>2</sup>	5.40 <sup>3</sup>			1.50 <sup>2</sup>	3.09 <sup>2</sup>	6.30 <sup>3</sup>			1.76 <sup>2</sup>	3.65 <sup>3</sup>	7.50 <sup>3</sup>
	16				0.73 <sup>1</sup>	3.12 <sup>2</sup>			0.17 <sup>1</sup>	1.45 <sup>1</sup>	4.35 <sup>2</sup>			0.41 <sup>1</sup>	1.93 <sup>2</sup>	5.06 <sup>2</sup>			0.57 <sup>1</sup>	2.36 <sup>2</sup>	6.14 <sup>3</sup>
	24					1.48 <sup>1</sup>				2.53 <sup>1</sup>					2.93 <sup>1</sup>				0.16 <sup>1</sup>	3.79 <sup>2</sup>	
16	12				0.65 <sup>1</sup>	2.55 <sup>1</sup>			0.20 <sup>1</sup>	1.22 <sup>1</sup>	3.54 <sup>2</sup>			0.40 <sup>1</sup>	1.62 <sup>1</sup>	4.13 <sup>2</sup>			0.55 <sup>1</sup>	2.00 <sup>2</sup>	5.02 <sup>2</sup>
	16					1.66 <sup>1</sup>				0.27 <sup>1</sup>	2.55 <sup>1</sup>				0.53 <sup>1</sup>	2.97 <sup>1</sup>				0.78 <sup>1</sup>	3.74 <sup>2</sup>
	24					0.13 <sup>1</sup>					0.87 <sup>1</sup>				0.99 <sup>1</sup>						1.54 <sup>1</sup>
18	12					1.48 <sup>1</sup>				0.37 <sup>1</sup>	2.23 <sup>1</sup>				0.60 <sup>1</sup>	2.60 <sup>1</sup>				0.83 <sup>1</sup>	3.26 <sup>2</sup>
	16					0.66 <sup>1</sup>					1.32 <sup>1</sup>				1.52 <sup>1</sup>						2.06 <sup>1</sup>
	24																				0.02 <sup>1</sup>
20	12					0.74 <sup>1</sup>					1.30 <sup>1</sup>				1.51 <sup>1</sup>					0.02 <sup>1</sup>	1.99 <sup>1</sup>
	16										0.45 <sup>1</sup>				0.51 <sup>1</sup>						0.87 <sup>1</sup>
	24																				

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 70 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	400S162					400S200					400S250					400S300					
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	
8	12	0.66 <sup>3</sup>	1.80	4.38	6.54	10.9	1.02 <sup>4</sup>	2.58	5.78	8.41	13.6	1.28	3.04	6.43	9.71	15.7	1.44	3.19	6.69	10.3	17.2	
	16		1.04 <sup>3</sup>	3.63 <sup>4</sup>	5.75	10.2	0.24 <sup>3</sup>	1.75 <sup>4</sup>	4.94	7.54	12.8	0.47 <sup>3</sup>	2.16	5.56	8.78	14.7	0.62 <sup>3</sup>	2.30	5.83	9.34	16.3	
	24			2.25 <sup>3</sup>	4.27 <sup>3</sup>	8.72		0.22 <sup>3</sup>	3.39 <sup>3</sup>	5.92 <sup>4</sup>	11.2		0.52 <sup>3</sup>	3.94 <sup>3</sup>	7.01	13.0		0.64 <sup>3</sup>	4.21 <sup>4</sup>	7.57	14.5	
9	12	0.08 <sup>3</sup>	1.13 <sup>3</sup>	3.54 <sup>4</sup>	5.53	9.64	0.37 <sup>3</sup>	1.80 <sup>4</sup>	4.76	7.19	12.1	0.60 <sup>3</sup>	2.22 <sup>4</sup>	5.46	8.47	13.9	0.75 <sup>3</sup>	2.37	5.69	9.07	15.5	
	16		0.27 <sup>3</sup>	2.68 <sup>3</sup>	4.61 <sup>3</sup>	8.74		0.86 <sup>3</sup>	3.80 <sup>3</sup>	6.19 <sup>4</sup>	11.1		1.20 <sup>3</sup>	4.44 <sup>4</sup>	7.36	12.8		1.33 <sup>3</sup>	4.67 <sup>4</sup>	7.95	14.4	
	24			1.14 <sup>2</sup>	2.95 <sup>3</sup>	7.08 <sup>3</sup>			2.06 <sup>3</sup>	4.35 <sup>3</sup>	9.30 <sup>4</sup>			2.57 <sup>3</sup>	5.33 <sup>3</sup>	10.7			2.80 <sup>3</sup>	5.88 <sup>3</sup>	12.2	
10	12		0.48 <sup>3</sup>	2.71 <sup>3</sup>	4.51 <sup>3</sup>	8.29		1.05 <sup>3</sup>	3.75 <sup>3</sup>	5.97 <sup>4</sup>	10.5		1.41 <sup>3</sup>	4.43 <sup>4</sup>	7.14	12.1	0.07 <sup>3</sup>	1.54 <sup>3</sup>	4.66 <sup>4</sup>	7.80	13.7	
	16			1.78 <sup>2</sup>	3.51 <sup>3</sup>	7.29 <sup>3</sup>		0.03 <sup>2</sup>	2.71 <sup>3</sup>	4.86 <sup>3</sup>	9.38 <sup>4</sup>		0.28 <sup>3</sup>	3.29 <sup>3</sup>	5.90 <sup>3</sup>	10.8		0.39 <sup>3</sup>	3.52 <sup>3</sup>	6.53 <sup>4</sup>	12.4	
	24			0.14 <sup>1</sup>	1.72 <sup>2</sup>	5.47 <sup>3</sup>			0.87 <sup>2</sup>	2.90 <sup>2</sup>	7.41 <sup>3</sup>			1.27 <sup>2</sup>	3.69 <sup>3</sup>	8.55 <sup>3</sup>			1.48 <sup>2</sup>	4.23 <sup>3</sup>	10.0 <sup>4</sup>	
12	12			1.24 <sup>2</sup>	2.63 <sup>2</sup>	5.70 <sup>3</sup>			1.97 <sup>2</sup>	3.71 <sup>3</sup>	7.40 <sup>3</sup>			2.50 <sup>2</sup>	4.54 <sup>3</sup>	8.58 <sup>4</sup>		0.04 <sup>2</sup>	2.72 <sup>3</sup>	5.16 <sup>3</sup>	10.1 <sup>4</sup>	
	16			0.27 <sup>1</sup>	1.57 <sup>2</sup>	4.62 <sup>2</sup>			0.88 <sup>1</sup>	2.54 <sup>2</sup>	6.21 <sup>3</sup>			1.26 <sup>2</sup>	3.22 <sup>2</sup>	7.20 <sup>3</sup>			1.45 <sup>2</sup>	3.75 <sup>3</sup>	8.58 <sup>3</sup>	
	24					2.72 <sup>1</sup>				0.52 <sup>1</sup>	4.14 <sup>2</sup>				0.93 <sup>1</sup>	4.77 <sup>2</sup>				1.29 <sup>2</sup>	5.94 <sup>2</sup>	
14	12			0.16 <sup>1</sup>	1.18 <sup>1</sup>	3.59 <sup>2</sup>			0.64 <sup>1</sup>	1.94 <sup>2</sup>	4.86 <sup>2</sup>			0.94 <sup>1</sup>	2.49 <sup>2</sup>	5.66 <sup>3</sup>			1.15 <sup>1</sup>	2.99 <sup>2</sup>	6.80 <sup>3</sup>	
	16				0.17 <sup>1</sup>	2.54 <sup>1</sup>				0.83 <sup>1</sup>	3.71 <sup>2</sup>				1.22 <sup>1</sup>	4.31 <sup>2</sup>				1.58 <sup>1</sup>	5.31 <sup>2</sup>	
	24					0.74 <sup>1</sup>				1.73 <sup>1</sup>					1.98 <sup>1</sup>						2.75 <sup>1</sup>	
16	12				0.20 <sup>1</sup>	2.09 <sup>1</sup>				0.73 <sup>1</sup>	3.03 <sup>1</sup>				1.06 <sup>1</sup>	3.53 <sup>2</sup>					1.37 <sup>1</sup>	4.36 <sup>2</sup>
	16					1.12 <sup>1</sup>					1.96 <sup>1</sup>					2.27 <sup>1</sup>					0.05 <sup>1</sup>	2.96 <sup>1</sup>
	24										0.13 <sup>1</sup>					0.11 <sup>1</sup>						0.57 <sup>1</sup>
18	12					1.06 <sup>1</sup>					1.76 <sup>1</sup>				0.08 <sup>1</sup>	2.05 <sup>1</sup>					0.25 <sup>1</sup>	2.64 <sup>1</sup>
	16					0.16 <sup>1</sup>					0.77 <sup>1</sup>					0.87 <sup>1</sup>						1.33 <sup>1</sup>
	24																					
20	12					0.34 <sup>1</sup>					0.86 <sup>1</sup>					0.99 <sup>1</sup>						1.41 <sup>1</sup>
	16																					0.20 <sup>1</sup>
	24																					

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 0 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	600S162					600S200					600S250					600S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	3.68	5.07	8.24	10.9	16.6	4.28	6.42	11.0	14.6	22.7	4.63	6.92	11.2	16.1	26.5	4.82	7.06	11.6	16.3	28.3
	16	3.68	5.07	8.24	10.9	16.6	4.28	6.42	11.0	14.6	22.7	4.63	6.92	11.2	16.1	26.5	4.82	7.06	11.6	16.3	28.3
	24	3.68	5.07	8.24	10.9	16.6	4.28	6.42	11.0	14.6	22.7	4.63	6.92	11.2	16.1	26.5	4.82	7.06	11.6	16.3	28.3
9	12	3.68	5.07	8.24	10.9	16.6	4.25	6.36	10.8	14.4	22.4	4.59	6.87	11.1	15.9	26.1	4.78	7.00	11.5	16.1	27.8
	16	3.68	5.07	8.24	10.9	16.6	4.25	6.36	10.8	14.4	22.4	4.59	6.87	11.1	15.9	26.1	4.78	7.00	11.5	16.1	27.8
	24	3.68	5.07	8.24	10.9	16.6	4.25	6.36	10.8	14.4	22.4	4.59	6.87	11.1	15.9	26.1	4.78	7.00	11.5	16.1	27.8
10	12	3.68	5.07	8.24	10.9	16.6	4.21	6.29	10.6	14.1	22.0	4.55	6.81	10.9	15.6	25.5	4.73	6.93	11.3	15.9	27.3
	16	3.68	5.07	8.24	10.9	16.6	4.21	6.29	10.6	14.1	22.0	4.55	6.81	10.9	15.6	25.5	4.73	6.93	11.3	15.9	27.3
	24	3.68	5.07	8.24	10.9	16.6	4.21	6.29	10.6	14.1	22.0	4.55	6.81	10.9	15.6	25.5	4.73	6.93	11.3	15.9	27.3
12	12	3.60	4.98	8.14	10.9	16.6	4.12	6.10	10.1	13.5	21.0	4.43	6.64	10.5	15.0	24.2	4.61	6.76	10.9	15.3	25.9
	16	3.60	4.98	8.14	10.9	16.6	4.12	6.10	10.1	13.5	21.0	4.43	6.64	10.5	15.0	24.2	4.61	6.76	10.9	15.3	25.9
	24	3.59	4.98	8.14	10.9	16.6	4.12	6.10	10.1	13.5	21.0	4.43	6.64	10.5	15.0	24.2	4.61	6.76	10.9	15.3	25.9
14	12	3.47	4.82	7.72	10.4	16.5	3.98	5.84	9.48	12.6	19.6	4.29	6.42	10.0	14.1	22.5	4.46	6.55	10.4	14.6	24.2
	16	3.47	4.82	7.72	10.4	16.5	3.98	5.84	9.48	12.6	19.6	4.28	6.42	10.0	14.1	22.5	4.46	6.55	10.4	14.6	24.2
	24	3.47	4.82	7.72	10.4	16.5	3.98	5.84	9.48	12.6	19.6	4.28	6.42	10.0	14.1	22.5	4.46	6.55	10.4	14.6	24.2
16	12	3.30	4.59	7.16	9.62	15.2	3.81	5.52	8.70	11.6	17.9	4.11	6.16	9.55	13.2	20.6	4.28	6.30	9.75	13.8	22.5
	16	3.30	4.58	7.16	9.62	15.2	3.81	5.52	8.70	11.6	17.9	4.11	6.16	9.55	13.2	20.6	4.28	6.30	9.75	13.8	22.5
	24	3.30	4.58	7.16	9.62	15.2	3.81	5.52	8.70	11.6	17.9	4.11	6.16	9.55	13.2	20.6	4.28	6.30	9.75	13.8	22.5
18	12	3.10	4.30	6.50	8.71	13.7	3.60	5.15	7.85	10.4	16.1	3.90	5.87	8.92	12.1	18.5	4.08	6.02	9.07	13.0	20.7
	16	3.10	4.30	6.50	8.71	13.7	3.60	5.15	7.85	10.4	16.1	3.90	5.87	8.92	12.1	18.5	4.08	6.02	9.07	13.0	20.7
	24	3.10	4.30	6.49	8.71	13.7	3.60	5.15	7.84	10.4	16.1	3.90	5.86	8.92	12.1	18.5	4.07	6.02	9.07	13.0	20.7
20	12	2.86	3.98	5.78	7.74	12.1	3.37	4.76	6.96	9.24	14.2	3.67	5.52	8.17	10.8	16.4	3.85	5.71	8.35	11.7	18.6
	16	2.86	3.98	5.78	7.74	12.1	3.37	4.76	6.96	9.24	14.2	3.66	5.52	8.17	10.8	16.4	3.85	5.71	8.35	11.7	18.6
	24	2.86	3.98	5.77	7.74	12.1	3.37	4.76	6.96	9.24	14.2	3.66	5.52	8.17	10.8	16.4	3.85	5.71	8.35	11.7	18.6

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 10 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	600S162					600S200					600S250					600S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	3.40	4.80	7.98	10.6	16.3	4.00	6.12	10.7	14.3	22.4	4.34	6.62	10.9	15.8	26.2	4.53	6.76	11.3	16.0	28.0
	16	3.31	4.71	7.90	10.5	16.2	3.90	6.02	10.6	14.2	22.3	4.24	6.51	10.8	15.7	26.1	4.43	6.66	11.2	15.9	27.9
	24	3.13	4.53	7.73	10.4	16.0	3.72	5.82	10.4	14.0	22.1	4.05	6.31	10.6	15.5	25.8	4.24	6.46	11.1	15.7	27.6
9	12	3.32	4.72	7.90	10.5	16.2	3.89	5.97	10.4	14.0	22.0	4.22	6.48	10.7	15.5	25.6	4.40	6.61	11.1	15.7	27.4
	16	3.20	4.60	7.79	10.4	16.1	3.77	5.85	10.3	13.8	21.9	4.10	6.35	10.6	15.4	25.5	4.28	6.49	11.0	15.6	27.2
	24	2.97	4.37	7.57	10.2	15.9	3.53	5.59	10.0	13.6	21.6	3.85	6.09	10.3	15.1	25.2	4.04	6.23	10.7	15.3	26.9
10	12	3.22	4.62	7.81	10.5	16.1	3.76	5.80	10.1	13.6	21.5	4.08	6.31	10.4	15.1	25.0	4.26	6.45	10.9	15.4	26.7
	16	3.08	4.48	7.67	10.3	16.0	3.61	5.64	9.96	13.5	21.3	3.93	6.15	10.3	14.9	24.8	4.11	6.29	10.7	15.2	26.5
	24	2.79	4.19	7.39	10.0	15.7	3.32	5.33	9.64	13.1	21.0	3.63	5.83	9.97	14.6	24.4	3.81	5.98	10.4	14.9	26.1
12	12	2.93	4.32	7.47	10.2	15.9	3.45	5.38	9.40	12.7	20.2	3.76	5.91	9.79	14.2	23.3	3.93	6.06	10.2	14.5	25.0
	16	2.72	4.11	7.26	9.98	15.6	3.24	5.15	9.16	12.5	19.9	3.54	5.67	9.56	13.9	23.0	3.71	5.83	9.97	14.3	24.7
	24	2.32	3.70	6.84	9.55	15.2	2.83	4.70	8.69	12.0	19.4	3.11	5.21	9.11	13.4	22.5	3.29	5.37	9.52	13.8	24.2
14	12	2.57	3.91	6.80	9.41	15.4	3.07	4.86	8.46	11.5	18.4	3.36	5.41	9.01	13.0	21.3	3.54	5.57	9.40	13.5	23.0
	16	2.30	3.62	6.51	9.11	15.0	2.80	4.55	8.14	11.2	18.1	3.07	5.09	8.70	12.7	20.9	3.25	5.26	9.09	13.2	22.6
	24	1.78	3.09	5.96	8.53	14.3	2.27	3.97	7.53	10.6	17.3	2.53	4.48	8.10	12.0	20.1	2.69	4.67	8.50	12.6	21.8
16	12	2.16	3.41	5.97	8.35	13.7	2.65	4.25	7.40	10.2	16.4	2.92	4.83	8.21	11.7	18.9	3.09	5.02	8.48	12.4	20.8
	16	1.83	3.06	5.62	7.97	13.3	2.31	3.88	7.01	9.77	15.9	2.56	4.43	7.81	11.3	18.4	2.74	4.63	8.09	12.0	20.3
	24	1.23 <sup>4</sup>	2.42	4.97	7.27	12.4	1.68	3.18	6.28	9.00	15.0	1.91	3.69	7.05	10.5	17.5	2.06	3.89	7.36	11.1	19.3
18	12	1.74	2.88	5.08	7.18	11.8	2.19	3.62	6.29	8.75	14.2	2.45	4.20	7.24	10.3	16.5	2.62	4.41	7.50	11.1	18.5
	16	1.37 <sup>4</sup>	2.48	4.68	6.75	11.3	1.80	3.19	5.85	8.29	13.6	2.04	3.74	6.76	9.74	15.9	2.20	3.95	7.04	10.6	17.9
	24	0.71 <sup>3</sup>	1.77 <sup>3</sup>	3.97 <sup>4</sup>	5.96	10.4	1.11 <sup>3</sup>	2.42 <sup>4</sup>	5.06	7.43	12.6	1.31 <sup>3</sup>	2.89	5.90	8.78	14.8	1.45 <sup>4</sup>	3.10	6.19	9.61	16.7
20	12	1.33 <sup>4</sup>	2.35	4.20	6.02	9.99	1.75	3.00	5.23	7.36	12.0	1.98	3.56	6.20	8.67	14.0	2.15	3.79	6.49	9.58	16.0
	16	0.95 <sup>3</sup>	1.93 <sup>4</sup>	3.79	5.56	9.44	1.33 <sup>3</sup>	2.54	4.77	6.87	11.5	1.54 <sup>4</sup>	3.04	5.68	8.11	13.4	1.69 <sup>4</sup>	3.27	5.98	8.99	15.3
	24	0.26 <sup>2</sup>	1.18 <sup>3</sup>	3.05 <sup>3</sup>	4.75 <sup>4</sup>	8.47	0.60 <sup>3</sup>	1.72 <sup>3</sup>	3.96 <sup>4</sup>	5.98	10.4	0.76 <sup>3</sup>	2.13 <sup>3</sup>	4.75 <sup>4</sup>	7.11	12.3	0.87 <sup>3</sup>	2.34 <sup>4</sup>	5.06	7.93	14.1

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 20 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	600S162					600S200					600S250					600S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	3.13	4.53	7.73	10.4	16.0	3.72	5.82	10.4	14.0	22.1	4.05	6.31	10.6	15.5	25.8	4.24	6.46	11.1	15.7	27.6
	16	2.95	4.35	7.56	10.2	15.9	3.53	5.62	10.2	13.8	21.9	3.86	6.11	10.4	15.3	25.6	4.04	6.26	10.9	15.5	27.4
	24	2.59	4.00	7.22	9.9	15.5	3.17	5.23	9.75	13.4	21.5	3.48	5.71	10.1	14.9	25.2	3.66	5.86	10.5	15.1	27.0
9	12	2.97	4.37	7.57	10.2	15.9	3.53	5.59	10.0	13.6	21.6	3.85	6.09	10.3	15.1	25.2	4.04	6.23	10.7	15.3	26.9
	16	2.74	4.14	7.35	10.0	15.7	3.30	5.34	9.77	13.3	21.3	3.61	5.83	10.1	14.8	24.9	3.79	5.98	10.5	15.1	26.6
	24	2.29	3.70	6.92	9.57	15.2	2.84	4.84	9.26	12.8	20.8	3.14	5.32	9.59	14.3	24.3	3.31	5.48	10.0	14.6	26.1
10	12	2.79	4.19	7.39	10.0	15.7	3.32	5.33	9.64	13.1	21.0	3.63	5.83	9.97	14.6	24.4	3.81	5.98	10.4	14.9	26.1
	16	2.50	3.91	7.11	9.75	15.4	3.04	5.02	9.32	12.8	20.6	3.33	5.51	9.66	14.3	24.1	3.51	5.67	10.1	14.5	25.8
	24	1.95	3.36	6.57	9.21	14.8	2.48	4.41	8.70	12.2	20.0	2.76	4.89	9.06	13.6	23.3	2.93	5.06	9.48	13.9	25.0
12	12	2.32	3.70	6.84	9.55	15.2	2.83	4.70	8.69	12.0	19.4	3.11	5.21	9.11	13.4	22.5	3.29	5.37	9.52	13.8	24.2
	16	1.93	3.30	6.44	9.13	14.7	2.43	4.27	8.24	11.5	18.9	2.70	4.76	8.67	12.9	21.9	2.87	4.93	9.09	13.3	23.6
	24	1.19	2.54	5.67	8.32	13.9	1.68	3.44	7.37	10.6	17.9	1.92	3.90	7.82	12.0	20.9	2.08	4.09	8.24	12.4	22.6
14	12	1.78	3.09	5.96	8.53	14.3	2.27	3.97	7.53	10.6	17.3	2.53	4.48	8.10	12.0	20.1	2.69	4.67	8.50	12.6	21.8
	16	1.30	2.58	5.44	7.97	13.7	1.77	3.42	6.96	9.96	16.7	2.01	3.90	7.52	11.4	19.4	2.16	4.09	7.92	11.9	21.1
	24	0.41 <sup>3</sup>	1.64 <sup>4</sup>	4.48	6.94	12.5	0.85 <sup>3</sup>	2.39 <sup>4</sup>	5.88	8.83	15.4	1.04 <sup>4</sup>	2.82	6.44	10.1	18.0	1.18 <sup>4</sup>	3.02	6.84	10.7	19.7
16	12	1.23 <sup>4</sup>	2.42	4.97	7.27	12.4	1.68	3.18	6.28	9.00	15.0	1.91	3.69	7.05	10.5	17.5	2.06	3.89	7.36	11.1	19.3
	16	0.68 <sup>3</sup>	1.84 <sup>4</sup>	4.36	6.61	11.6	1.10 <sup>3</sup>	2.54	5.62	8.29	14.2	1.30 <sup>4</sup>	3.00	6.35	9.67	16.6	1.44 <sup>4</sup>	3.20	6.67	10.4	18.4
	24		0.78 <sup>3</sup>	3.27 <sup>3</sup>	5.43 <sup>4</sup>	10.3	0.07 <sup>3</sup>	1.39 <sup>3</sup>	4.41 <sup>3</sup>	6.99	12.7	0.21 <sup>3</sup>	1.75 <sup>3</sup>	5.07 <sup>4</sup>	8.24	15.0	0.31 <sup>3</sup>	1.94 <sup>3</sup>	5.40 <sup>4</sup>	8.91	16.7
18	12	0.71 <sup>3</sup>	1.77 <sup>3</sup>	3.97 <sup>4</sup>	5.96	10.4	1.11 <sup>3</sup>	2.42 <sup>4</sup>	5.06	7.43	12.6	1.31 <sup>3</sup>	2.89	5.90	8.78	14.8	1.45 <sup>4</sup>	3.10	6.19	9.61	16.7
	16	0.13 <sup>2</sup>	1.14 <sup>3</sup>	3.32 <sup>3</sup>	5.26 <sup>4</sup>	9.55	0.49 <sup>3</sup>	1.72 <sup>3</sup>	4.35 <sup>4</sup>	6.66	11.8	0.64 <sup>3</sup>	2.12 <sup>3</sup>	5.11 <sup>4</sup>	7.92	13.8	0.76 <sup>3</sup>	2.32 <sup>4</sup>	5.41	8.71	15.7
	24		0.01 <sup>2</sup>	2.18 <sup>2</sup>	4.01 <sup>3</sup>	8.06 <sup>4</sup>		0.50 <sup>2</sup>	3.09 <sup>3</sup>	5.29 <sup>3</sup>	10.2 <sup>4</sup>		0.77 <sup>3</sup>	3.72 <sup>3</sup>	6.38 <sup>3</sup>	12.1		0.94 <sup>3</sup>	4.02 <sup>3</sup>	7.10 <sup>4</sup>	13.8
20	12	0.26 <sup>2</sup>	1.18 <sup>3</sup>	3.05 <sup>3</sup>	4.75 <sup>4</sup>	8.47	0.60 <sup>3</sup>	1.72 <sup>3</sup>	3.96 <sup>4</sup>	5.98	10.4	0.76 <sup>3</sup>	2.13 <sup>3</sup>	4.75 <sup>4</sup>	7.11	12.3	0.87 <sup>3</sup>	2.34 <sup>4</sup>	5.06	7.93	14.1
	16		0.52 <sup>2</sup>	2.40 <sup>3</sup>	4.03 <sup>3</sup>	7.62 <sup>4</sup>		1.00 <sup>3</sup>	3.24 <sup>3</sup>	5.19 <sup>3</sup>	9.49	0.07 <sup>2</sup>	1.33 <sup>3</sup>	3.94 <sup>3</sup>	6.23 <sup>4</sup>	11.3	0.15 <sup>2</sup>	1.51 <sup>3</sup>	4.23 <sup>3</sup>	6.99 <sup>4</sup>	13.0
	24			1.27 <sup>2</sup>	2.79 <sup>2</sup>	6.14 <sup>3</sup>			1.99 <sup>2</sup>	3.82 <sup>3</sup>	7.89 <sup>3</sup>			2.52 <sup>2</sup>	4.69 <sup>3</sup>	9.47 <sup>3</sup>		0.06 <sup>2</sup>	2.79 <sup>3</sup>	5.34 <sup>3</sup>	11.0 <sup>4</sup>

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 30 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	600S162					600S200					600S250					600S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	2.86	4.26	7.47	10.1	15.8	3.44	5.52	10.1	13.7	21.8	3.76	6.01	10.3	15.2	25.5	3.95	6.16	10.8	15.4	27.3
	16	2.59	4.00	7.22	9.87	15.5	3.17	5.23	9.75	13.4	21.5	3.48	5.71	10.1	14.9	25.2	3.66	5.86	10.5	15.1	27.0
	24	2.06	3.48	6.72	9.38	15.0	2.63	4.64	9.16	12.8	20.9	2.92	5.11	9.48	14.3	24.5	3.10	5.28	9.91	14.5	26.3
9	12	2.63	4.03	7.24	9.89	15.6	3.18	5.21	9.64	13.2	21.2	3.49	5.70	9.95	14.7	24.8	3.67	5.86	10.4	14.9	26.5
	16	2.29	3.70	6.92	9.57	15.2	2.84	4.84	9.26	12.8	20.8	3.14	5.32	9.59	14.3	24.3	3.31	5.48	10.0	14.6	26.1
	24	1.63	3.04	6.29	8.93	14.6	2.17	4.11	8.52	12.1	20.0	2.44	4.58	8.87	13.5	23.5	2.61	4.75	9.30	13.8	25.2
10	12	2.36	3.77	6.98	9.61	15.3	2.89	4.87	9.16	12.6	20.5	3.19	5.35	9.51	14.1	23.9	3.36	5.51	9.93	14.4	25.6
	16	1.95	3.36	6.57	9.21	14.8	2.48	4.41	8.70	12.2	20.0	2.76	4.89	9.06	13.6	23.3	2.93	5.06	9.48	13.9	25.0
	24	1.16	2.56	5.79	8.41	14.0	1.67	3.53	7.79	11.2	19.0	1.92	3.98	8.18	12.6	22.3	2.08	4.17	8.61	13.0	24.0
12	12	1.74	3.11	6.24	8.93	14.5	2.24	4.06	8.02	11.3	18.6	2.50	4.54	8.45	12.7	21.7	2.67	4.72	8.87	13.1	23.4
	16	1.19	2.54	5.67	8.32	13.9	1.68	3.44	7.37	10.6	17.9	1.92	3.90	7.82	12.0	20.9	2.08	4.09	8.24	12.4	22.6
	24	0.17 <sup>3</sup>	1.48 <sup>4</sup>	4.58	7.18	12.6	0.63 <sup>3</sup>	2.27	6.15	9.35	16.5	0.82 <sup>4</sup>	2.68	6.62	10.6	19.4	0.95 <sup>4</sup>	2.88	7.04	11.1	21.0
14	12	1.07 <sup>4</sup>	2.34	5.19	7.71	13.4	1.53	3.15	6.68	9.67	16.3	1.76	3.62	7.24	11.0	19.0	1.91	3.82	7.65	11.6	20.8
	16	0.41 <sup>3</sup>	1.64 <sup>4</sup>	4.48	6.94	12.5	0.85 <sup>3</sup>	2.39 <sup>4</sup>	5.88	8.83	15.4	1.04 <sup>4</sup>	2.82	6.44	10.1	18.0	1.18 <sup>4</sup>	3.02	6.84	10.7	19.7
	24		0.38 <sup>3</sup>	3.17 <sup>3</sup>	5.53 <sup>4</sup>	10.9		1.01 <sup>3</sup>	4.43 <sup>3</sup>	7.28	13.6		1.35 <sup>3</sup>	4.96 <sup>4</sup>	8.47	16.1		1.54 <sup>3</sup>	5.35 <sup>4</sup>	9.06	17.8
16	12	0.42 <sup>3</sup>	1.56 <sup>3</sup>	4.08 <sup>4</sup>	6.30	11.3	0.83 <sup>3</sup>	2.24 <sup>4</sup>	5.30	7.95	13.8	1.02 <sup>3</sup>	2.67	6.02	9.30	16.2	1.15 <sup>3</sup>	2.88	6.34	9.97	17.9
	16		0.78 <sup>3</sup>	3.27 <sup>3</sup>	5.43 <sup>4</sup>	10.3	0.07 <sup>3</sup>	1.39 <sup>3</sup>	4.41 <sup>3</sup>	6.99	12.7	0.21 <sup>3</sup>	1.75 <sup>3</sup>	5.07 <sup>4</sup>	8.24	15.0	0.31 <sup>3</sup>	1.94 <sup>3</sup>	5.40 <sup>4</sup>	8.91	16.7
	24			1.84 <sup>2</sup>	3.87 <sup>3</sup>	8.40 <sup>3</sup>			2.83 <sup>3</sup>	5.28 <sup>3</sup>	10.7 <sup>4</sup>		0.11 <sup>3</sup>	3.38 <sup>3</sup>	6.35 <sup>3</sup>	12.8		0.27 <sup>3</sup>	3.69 <sup>3</sup>	6.97 <sup>4</sup>	14.4
18	12		0.84 <sup>3</sup>	3.02 <sup>3</sup>	4.93 <sup>3</sup>	9.16	0.20 <sup>2</sup>	1.40 <sup>3</sup>	4.02 <sup>3</sup>	6.30 <sup>4</sup>	11.3	0.34 <sup>3</sup>	1.77 <sup>3</sup>	4.75 <sup>4</sup>	7.51	13.4	0.44 <sup>3</sup>	1.96 <sup>3</sup>	5.04 <sup>4</sup>	8.29	15.2
	16		0.01 <sup>2</sup>	2.18 <sup>2</sup>	4.01 <sup>3</sup>	8.06 <sup>4</sup>		0.50 <sup>2</sup>	3.09 <sup>3</sup>	5.29 <sup>3</sup>	10.2 <sup>4</sup>		0.77 <sup>3</sup>	3.72 <sup>3</sup>	6.38 <sup>3</sup>	12.1		0.94 <sup>3</sup>	4.02 <sup>3</sup>	7.10 <sup>4</sup>	13.8
	24			0.72 <sup>1</sup>	2.40 <sup>2</sup>	6.16 <sup>3</sup>			1.48 <sup>2</sup>	3.52 <sup>2</sup>	8.10 <sup>3</sup>			1.94 <sup>2</sup>	4.40 <sup>3</sup>	9.79 <sup>3</sup>			2.20 <sup>2</sup>	5.01 <sup>3</sup>	11.3 <sup>4</sup>
20	12		0.22 <sup>2</sup>	2.10 <sup>2</sup>	3.70 <sup>3</sup>	7.22 <sup>3</sup>		0.67 <sup>2</sup>	2.91 <sup>3</sup>	4.83 <sup>3</sup>	9.06 <sup>4</sup>		0.95 <sup>3</sup>	3.56 <sup>3</sup>	5.82 <sup>3</sup>	10.8		1.13 <sup>3</sup>	3.85 <sup>3</sup>	6.55 <sup>4</sup>	12.4
	16			1.27 <sup>2</sup>	2.79 <sup>2</sup>	6.14 <sup>3</sup>			1.99 <sup>2</sup>	3.82 <sup>3</sup>	7.89 <sup>3</sup>			2.52 <sup>2</sup>	4.69 <sup>3</sup>	9.47 <sup>3</sup>		0.06 <sup>2</sup>	2.79 <sup>3</sup>	5.34 <sup>3</sup>	11.0 <sup>4</sup>
	24				1.21 <sup>1</sup>	4.27 <sup>2</sup>			0.41 <sup>1</sup>	2.09 <sup>2</sup>	5.86 <sup>2</sup>			0.73 <sup>1</sup>	2.73 <sup>2</sup>	7.22 <sup>3</sup>			0.94 <sup>2</sup>	3.24 <sup>2</sup>	8.53 <sup>3</sup>

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720



## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 40 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	600S162					600S200					600S250					600S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	2.59	4.00	7.22	9.87	15.5	3.17	5.23	9.75	13.4	21.5	3.48	5.71	10.1	14.9	25.2	3.66	5.86	10.5	15.1	27.0
	16	2.24	3.65	6.89	9.54	15.2	2.81	4.84	9.36	13.0	21.1	3.11	5.31	9.67	14.5	24.7	3.28	5.48	10.1	14.7	26.5
	24	1.55	2.97	6.23	8.89	14.5	2.10	4.07	8.58	12.2	20.3	2.37	4.53	8.92	13.7	23.8	2.54	4.71	9.35	13.9	25.6
9	12	2.29	3.70	6.92	9.57	15.2	2.84	4.84	9.26	12.8	20.8	3.14	5.32	9.59	14.3	24.3	3.31	5.48	10.0	14.6	26.1
	16	1.85	3.26	6.50	9.14	14.8	2.39	4.36	8.76	12.3	20.3	2.67	4.82	9.11	13.8	23.8	2.84	4.99	9.53	14.1	25.5
	24	1.00	2.41	5.67	8.31	13.9	1.52	3.41	7.79	11.3	19.2	1.77	3.85	8.17	12.7	22.6	1.92	4.04	8.59	13.1	24.4
10	12	1.95	3.36	6.57	9.21	14.8	2.48	4.41	8.70	12.2	20.0	2.76	4.89	9.06	13.6	23.3	2.93	5.06	9.48	13.9	25.0
	16	1.42	2.82	6.04	8.68	14.3	1.94	3.82	8.09	11.6	19.3	2.20	4.28	8.47	13.0	22.6	2.36	4.46	8.89	13.3	24.3
	24	0.41 <sup>4</sup>	1.80	5.03	7.64	13.2	0.91	2.69	6.92	10.3	18.0	1.12	3.11	7.33	11.7	21.2	1.27	3.31	7.75	12.1	22.9
12	12	1.19	2.54	5.67	8.32	13.9	1.68	3.44	7.37	10.6	17.9	1.92	3.90	7.82	12.0	20.9	2.08	4.09	8.24	12.4	22.6
	16	0.50 <sup>3</sup>	1.82	4.93	7.56	13.0	0.97 <sup>4</sup>	2.65	6.55	9.77	17.0	1.18 <sup>4</sup>	3.08	7.01	11.1	19.9	1.32	3.27	7.43	11.6	21.5
	24		0.49 <sup>3</sup>	3.56 <sup>4</sup>	6.11	11.5		1.19 <sup>3</sup>	5.01 <sup>4</sup>	8.15	15.2		1.54 <sup>4</sup>	5.48	9.38	17.9		1.74 <sup>4</sup>	5.89	9.87	19.6
14	12	0.41 <sup>3</sup>	1.64 <sup>4</sup>	4.48	6.94	12.5	0.85 <sup>3</sup>	2.39 <sup>4</sup>	5.88	8.83	15.4	1.04 <sup>4</sup>	2.82	6.44	10.1	18.0	1.18 <sup>4</sup>	3.02	6.84	10.7	19.7
	16		0.78 <sup>3</sup>	3.59 <sup>3</sup>	5.98 <sup>4</sup>	11.4	0.01 <sup>3</sup>	1.45 <sup>3</sup>	4.90 <sup>4</sup>	7.78	14.2	0.16 <sup>3</sup>	1.82 <sup>4</sup>	5.43	9.01	16.7	0.27 <sup>3</sup>	2.02 <sup>4</sup>	5.83	9.60	18.4
	24			1.98 <sup>3</sup>	4.25 <sup>3</sup>	9.36 <sup>4</sup>			3.11 <sup>3</sup>	5.86 <sup>3</sup>	12.0		0.01 <sup>3</sup>	3.60 <sup>3</sup>	6.95 <sup>4</sup>	14.4		0.19 <sup>3</sup>	3.97 <sup>3</sup>	7.53 <sup>4</sup>	15.9
16	12		0.78 <sup>3</sup>	3.27 <sup>3</sup>	5.43 <sup>4</sup>	10.3	0.07 <sup>3</sup>	1.39 <sup>3</sup>	4.41 <sup>3</sup>	6.99	12.7	0.21 <sup>3</sup>	1.75 <sup>3</sup>	5.07 <sup>4</sup>	8.24	15.0	0.31 <sup>3</sup>	1.94 <sup>3</sup>	5.40 <sup>4</sup>	8.91	16.7
	16			2.30 <sup>3</sup>	4.36 <sup>3</sup>	8.99 <sup>4</sup>		0.35 <sup>3</sup>	3.33 <sup>3</sup>	5.82 <sup>3</sup>	11.4		0.63 <sup>3</sup>	3.92 <sup>3</sup>	6.96 <sup>4</sup>	13.5		0.80 <sup>3</sup>	4.24 <sup>3</sup>	7.59 <sup>4</sup>	15.1
	24			0.58 <sup>2</sup>	2.49 <sup>2</sup>	6.77 <sup>3</sup>			1.43 <sup>2</sup>	3.76 <sup>3</sup>	8.98 <sup>3</sup>			1.88 <sup>2</sup>	4.67 <sup>3</sup>	10.9 <sup>3</sup>			2.16 <sup>2</sup>	5.24 <sup>3</sup>	12.4 <sup>4</sup>
18	12		0.01 <sup>2</sup>	2.18 <sup>2</sup>	4.01 <sup>3</sup>	8.06 <sup>4</sup>		0.50 <sup>2</sup>	3.09 <sup>3</sup>	5.29 <sup>3</sup>	10.2 <sup>4</sup>		0.77 <sup>3</sup>	3.72 <sup>3</sup>	6.38 <sup>3</sup>	12.1		0.94 <sup>3</sup>	4.02 <sup>3</sup>	7.10 <sup>4</sup>	13.8
	16			1.18 <sup>2</sup>	2.91 <sup>2</sup>	6.76 <sup>3</sup>			1.99 <sup>2</sup>	4.08 <sup>3</sup>	8.75 <sup>3</sup>			2.50 <sup>2</sup>	5.03 <sup>3</sup>	10.5 <sup>4</sup>			2.78 <sup>3</sup>	5.68 <sup>3</sup>	12.1 <sup>4</sup>
	24				1.01 <sup>1</sup>	4.50 <sup>2</sup>			0.08 <sup>1</sup>	1.99 <sup>2</sup>	6.31 <sup>2</sup>			0.39 <sup>1</sup>	2.68 <sup>2</sup>	7.82 <sup>3</sup>			0.61 <sup>2</sup>	3.19 <sup>2</sup>	9.18 <sup>3</sup>
20	12			1.27 <sup>2</sup>	2.79 <sup>2</sup>	6.14 <sup>3</sup>			1.99 <sup>2</sup>	3.82 <sup>3</sup>	7.89 <sup>3</sup>			2.52 <sup>2</sup>	4.69 <sup>3</sup>	9.47 <sup>3</sup>		0.06 <sup>2</sup>	2.79 <sup>3</sup>	5.34 <sup>3</sup>	11.0 <sup>4</sup>
	16			0.29 <sup>1</sup>	1.71 <sup>2</sup>	4.85 <sup>2</sup>			0.91 <sup>1</sup>	2.64 <sup>2</sup>	6.50 <sup>3</sup>			1.29 <sup>2</sup>	3.35 <sup>2</sup>	7.93 <sup>3</sup>			1.52 <sup>2</sup>	3.90 <sup>2</sup>	9.31 <sup>3</sup>
	24					2.66 <sup>1</sup>				0.60 <sup>1</sup>	4.12 <sup>2</sup>				1.05 <sup>1</sup>	5.29 <sup>2</sup>			1.43 <sup>1</sup>	6.40 <sup>2</sup>	

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 50 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	600S162					600S200					600S250					600S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	2.32	3.74	6.97	9.62	15.3	2.90	4.93	9.45	13.1	21.2	3.20	5.41	9.76	14.6	24.8	3.38	5.57	10.2	14.8	26.6
	16	1.89	3.31	6.56	9.21	14.9	2.45	4.45	8.97	12.6	20.7	2.74	4.92	9.29	14.1	24.3	2.91	5.09	9.73	14.3	26.1
	24	1.04	2.47	5.75	8.40	14.0	1.58	3.51	8.01	11.6	19.7	1.84	3.95	8.37	13.0	23.2	1.99	4.14	8.80	13.4	25.0
9	12	1.96	3.37	6.60	9.25	14.9	2.50	4.48	8.89	12.4	20.4	2.79	4.95	9.23	13.9	23.9	2.96	5.12	9.65	14.2	25.6
	16	1.42	2.83	6.08	8.72	14.4	1.95	3.88	8.27	11.8	19.7	2.22	4.33	8.63	13.2	23.2	2.38	4.51	9.06	13.6	24.9
	24	0.39	1.79	5.06	7.70	13.3	0.89	2.72	7.08	10.6	18.5	1.11	3.14	7.48	12.0	21.8	1.26	3.33	7.90	12.3	23.5
10	12	1.55	2.96	6.17	8.81	14.4	2.07	3.97	8.24	11.7	19.5	2.34	4.43	8.62	13.1	22.8	2.50	4.61	9.04	13.4	24.5
	16	0.91	2.30	5.53	8.16	13.7	1.42	3.25	7.50	10.9	18.7	1.65	3.69	7.89	12.3	21.9	1.81	3.88	8.32	12.7	23.6
	24		1.06 <sup>4</sup>	4.30	6.90	12.4	0.17 <sup>4</sup>	1.88	6.07	9.47	17.1	0.35 <sup>4</sup>	2.27	6.50	10.8	20.2	0.48 <sup>4</sup>	2.47	6.92	11.2	21.9
12	12	0.67 <sup>4</sup>	2.00	5.11	7.74	13.2	1.14 <sup>4</sup>	2.85	6.75	9.98	17.2	1.36	3.28	7.21	11.3	20.1	1.51	3.47	7.63	11.8	21.8
	16		1.14 <sup>3</sup>	4.23	6.82	12.2	0.30 <sup>3</sup>	1.90 <sup>4</sup>	5.76	8.94	16.1	0.47 <sup>3</sup>	2.29	6.23	10.2	18.9	0.60 <sup>4</sup>	2.49	6.65	10.7	20.6
	24			2.60 <sup>3</sup>	5.09 <sup>3</sup>	10.4		0.17 <sup>3</sup>	3.94 <sup>3</sup>	7.02 <sup>4</sup>	13.9		0.47 <sup>3</sup>	4.40 <sup>4</sup>	8.17	16.6		0.66 <sup>3</sup>	4.80 <sup>4</sup>	8.68	18.2
14	12		0.99 <sup>3</sup>	3.81 <sup>4</sup>	6.22	11.7	0.21 <sup>3</sup>	1.68 <sup>3</sup>	5.14 <sup>4</sup>	8.03	14.5	0.37 <sup>3</sup>	2.06 <sup>4</sup>	5.68	9.28	17.0	0.49 <sup>3</sup>	2.26 <sup>4</sup>	6.08	9.88	18.7
	16			2.76 <sup>3</sup>	5.09 <sup>3</sup>	10.3		0.58 <sup>3</sup>	3.97 <sup>3</sup>	6.79 <sup>4</sup>	13.1		0.89 <sup>3</sup>	4.49 <sup>3</sup>	7.95	15.5		1.08 <sup>3</sup>	4.87 <sup>4</sup>	8.54	17.1
	24			0.89 <sup>2</sup>	3.06 <sup>3</sup>	7.97 <sup>3</sup>			1.90 <sup>2</sup>	4.56 <sup>3</sup>	10.6 <sup>3</sup>			2.34 <sup>3</sup>	5.53 <sup>3</sup>	12.7 <sup>4</sup>			2.68 <sup>3</sup>	6.09 <sup>3</sup>	14.2
16	12		0.06 <sup>2</sup>	2.53 <sup>3</sup>	4.62 <sup>3</sup>	9.29 <sup>4</sup>		0.60 <sup>3</sup>	3.59 <sup>3</sup>	6.10 <sup>3</sup>	11.7		0.90 <sup>3</sup>	4.20 <sup>3</sup>	7.27 <sup>4</sup>	13.9		1.08 <sup>3</sup>	4.52 <sup>3</sup>	7.91	15.5
	16			1.41 <sup>2</sup>	3.39 <sup>3</sup>	7.84 <sup>3</sup>			2.35 <sup>2</sup>	4.75 <sup>3</sup>	10.1 <sup>4</sup>			2.86 <sup>3</sup>	5.77 <sup>3</sup>	12.1 <sup>4</sup>			3.16 <sup>3</sup>	6.38 <sup>3</sup>	13.7
	24				1.23 <sup>3</sup>	5.29 <sup>2</sup>			0.17 <sup>1</sup>	2.38 <sup>2</sup>	7.39 <sup>3</sup>			0.52 <sup>2</sup>	3.15 <sup>2</sup>	9.12 <sup>3</sup>			0.77 <sup>2</sup>	3.66 <sup>3</sup>	10.5 <sup>3</sup>
18	12			1.42 <sup>2</sup>	3.17 <sup>2</sup>	7.07 <sup>3</sup>			2.25 <sup>2</sup>	4.37 <sup>3</sup>	9.08 <sup>3</sup>			2.80 <sup>3</sup>	5.35 <sup>3</sup>	10.9 <sup>4</sup>		0.01 <sup>2</sup>	3.07 <sup>3</sup>	6.02 <sup>3</sup>	12.5
	16			0.28 <sup>1</sup>	1.92 <sup>2</sup>	5.58 <sup>3</sup>			1.00 <sup>2</sup>	2.99 <sup>2</sup>	7.48 <sup>3</sup>			1.40 <sup>2</sup>	3.80 <sup>2</sup>	9.11 <sup>3</sup>			1.65 <sup>2</sup>	4.38 <sup>3</sup>	10.6 <sup>3</sup>
	24					3.02 <sup>2</sup>				0.62 <sup>1</sup>	4.71 <sup>2</sup>				1.13 <sup>1</sup>	6.04 <sup>2</sup>				1.54 <sup>2</sup>	7.25 <sup>3</sup>
20	12			0.52 <sup>1</sup>	1.96 <sup>2</sup>	5.16 <sup>2</sup>			1.17 <sup>2</sup>	2.92 <sup>2</sup>	6.83 <sup>3</sup>			1.58 <sup>2</sup>	3.67 <sup>2</sup>	8.30 <sup>3</sup>			1.83 <sup>2</sup>	4.25 <sup>3</sup>	9.72 <sup>3</sup>
	16				0.74 <sup>1</sup>	3.71 <sup>2</sup>				1.57 <sup>1</sup>	5.26 <sup>2</sup>			0.19 <sup>1</sup>	2.15 <sup>2</sup>	6.55 <sup>2</sup>			0.38 <sup>1</sup>	2.61 <sup>2</sup>	7.79 <sup>3</sup>
	24					1.23 <sup>1</sup>					2.57 <sup>1</sup>				3.56 <sup>1</sup>						4.49 <sup>2</sup>

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

Bally Metal Products, Dass Metal Products, DCI Metal Corp., EB Metal Inc., Imperial Building Products, Managryse, Groupe UP, Trebor Building Products Ltd.

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 60 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	600S162					600S200					600S250					600S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	2.06	3.48	6.72	9.38	15.0	2.63	4.64	9.16	12.8	20.9	2.92	5.11	9.48	14.3	24.5	3.10	5.28	9.91	14.5	26.3
	16	1.55	2.97	6.23	8.89	14.5	2.10	4.07	8.58	12.2	20.3	2.37	4.53	8.92	13.7	23.8	2.54	4.71	9.35	13.9	25.6
	24	0.55	1.97	5.28	7.93	13.6	1.08	2.96	7.45	11.0	19.1	1.31	3.39	7.82	12.5	22.5	1.46	3.58	8.25	12.8	24.3
9	12	1.63	3.04	6.29	8.93	14.6	2.17	4.11	8.52	12.1	20.0	2.44	4.58	8.87	13.5	23.5	2.61	4.75	9.30	13.8	25.2
	16	1.00	2.41	5.67	8.31	13.9	1.52	3.41	7.79	11.3	19.2	1.77	3.85	8.17	12.7	22.6	1.92	4.04	8.59	13.1	24.4
	24		1.18	4.47	7.10	12.7	0.28 <sup>4</sup>	2.05	6.39	9.89	17.7	0.47	2.44	6.80	11.2	21.0	0.60	2.65	7.22	11.6	22.7
10	12	1.16	2.56	5.79	8.41	14.0	1.67	3.53	7.79	11.2	19.0	1.92	3.98	8.18	12.6	22.3	2.08	4.17	8.61	13.0	24.0
	16	0.41 <sup>4</sup>	1.80	5.03	7.64	13.2	0.91	2.69	6.92	10.3	18.0	1.12	3.11	7.33	11.7	21.2	1.27	3.31	7.75	12.1	22.9
	24		0.35 <sup>3</sup>	3.59 <sup>4</sup>	6.17	11.6		1.09 <sup>4</sup>	5.25	8.63	16.2		1.45	5.69	9.89	19.2		1.66	6.11	10.3	20.9
12	12	0.17 <sup>3</sup>	1.48 <sup>4</sup>	4.58	7.18	12.6	0.63 <sup>3</sup>	2.27	6.15	9.35	16.5	0.82 <sup>4</sup>	2.68	6.62	10.6	19.4	0.95 <sup>4</sup>	2.88	7.04	11.1	21.0
	16		0.49 <sup>3</sup>	3.56 <sup>4</sup>	6.11	11.5		1.19 <sup>3</sup>	5.01 <sup>4</sup>	8.15	15.2		1.54 <sup>4</sup>	5.48	9.38	17.9		1.74 <sup>4</sup>	5.89	9.87	19.6
	24			1.69 <sup>3</sup>	4.13 <sup>3</sup>	9.29 <sup>4</sup>			2.92 <sup>3</sup>	5.94 <sup>3</sup>	12.7			3.38 <sup>3</sup>	7.02 <sup>4</sup>	15.2			3.75 <sup>3</sup>	7.54 <sup>4</sup>	16.8
14	12		0.38 <sup>3</sup>	3.17 <sup>3</sup>	5.53 <sup>4</sup>	10.9		1.01 <sup>3</sup>	4.43 <sup>3</sup>	7.28	13.6		1.35 <sup>3</sup>	4.96 <sup>4</sup>	8.47	16.1		1.54 <sup>3</sup>	5.35 <sup>4</sup>	9.06	17.8
	16			1.98 <sup>3</sup>	4.25 <sup>3</sup>	9.36 <sup>4</sup>			3.11 <sup>3</sup>	5.86 <sup>3</sup>	12.0		0.01 <sup>3</sup>	3.60 <sup>3</sup>	6.95 <sup>4</sup>	14.4		0.19 <sup>3</sup>	3.97 <sup>3</sup>	7.53 <sup>4</sup>	15.9
	24				1.96 <sup>2</sup>	6.67 <sup>3</sup>			0.76 <sup>2</sup>	3.34 <sup>3</sup>	9.15 <sup>3</sup>			1.17 <sup>2</sup>	4.21 <sup>3</sup>	11.2 <sup>3</sup>			1.47 <sup>2</sup>	4.74 <sup>3</sup>	12.6 <sup>4</sup>
16	12			1.84 <sup>2</sup>	3.87 <sup>3</sup>	8.40 <sup>3</sup>			2.83 <sup>3</sup>	5.28 <sup>3</sup>	10.7 <sup>4</sup>		0.11 <sup>3</sup>	3.38 <sup>3</sup>	6.35 <sup>3</sup>	12.8		0.27 <sup>3</sup>	3.69 <sup>3</sup>	6.97 <sup>4</sup>	14.4
	16			0.58 <sup>2</sup>	2.49 <sup>2</sup>	6.77 <sup>3</sup>			1.43 <sup>2</sup>	3.76 <sup>3</sup>	8.98 <sup>3</sup>			1.88 <sup>2</sup>	4.67 <sup>3</sup>	10.9 <sup>3</sup>			2.16 <sup>2</sup>	5.24 <sup>3</sup>	12.4 <sup>4</sup>
	24				0.08 <sup>1</sup>	3.92 <sup>2</sup>				1.11 <sup>2</sup>	5.91 <sup>2</sup>				1.74 <sup>2</sup>	7.49 <sup>3</sup>				2.19 <sup>2</sup>	8.77 <sup>3</sup>
18	12			0.72 <sup>1</sup>	2.40 <sup>2</sup>	6.16 <sup>3</sup>			1.48 <sup>2</sup>	3.52 <sup>2</sup>	8.10 <sup>3</sup>			1.94 <sup>2</sup>	4.40 <sup>3</sup>	9.79 <sup>3</sup>			2.20 <sup>2</sup>	5.01 <sup>3</sup>	11.3 <sup>4</sup>
	16				1.01 <sup>1</sup>	4.50 <sup>2</sup>			0.08 <sup>1</sup>	1.99 <sup>2</sup>	6.31 <sup>2</sup>			0.39 <sup>1</sup>	2.68 <sup>2</sup>	7.82 <sup>3</sup>			0.61 <sup>2</sup>	3.19 <sup>2</sup>	9.18 <sup>3</sup>
	24					1.66 <sup>1</sup>					3.24 <sup>1</sup>					4.42 <sup>2</sup>				0.03 <sup>1</sup>	5.47 <sup>2</sup>
20	12				1.21 <sup>1</sup>	4.27 <sup>2</sup>			0.41 <sup>1</sup>	2.09 <sup>2</sup>	5.86 <sup>2</sup>			0.73 <sup>1</sup>	2.73 <sup>2</sup>	7.22 <sup>3</sup>			0.94 <sup>2</sup>	3.24 <sup>2</sup>	8.53 <sup>3</sup>
	16					2.66 <sup>1</sup>				0.60 <sup>1</sup>	4.12 <sup>2</sup>				1.05 <sup>1</sup>	5.29 <sup>2</sup>				1.43 <sup>1</sup>	6.40 <sup>2</sup>
	24										1.16 <sup>1</sup>					1.99 <sup>1</sup>					2.76 <sup>1</sup>

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 70 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	600S162					600S200					600S250					600S300				
		33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi			33 ksi		50 ksi		
		33	43	54	68	97	33	43	54	68	97	33	43	54	68	97	33	43	54	68	97
8	12	1.80	3.22	6.48	9.13	14.8	2.36	4.36	8.87	12.5	20.6	2.65	4.82	9.20	14.0	24.2	2.82	4.99	9.63	14.2	25.9
	16	1.21	2.63	5.91	8.57	14.2	1.76	3.70	8.20	11.8	19.9	2.01	4.14	8.55	13.2	23.4	2.18	4.33	8.98	13.5	25.2
	24	0.07	1.49	4.81	7.46	13.1	0.58	2.42	6.89	10.5	18.5	0.79	2.83	7.28	11.9	21.9	0.93	3.03	7.71	12.2	23.6
9	12	1.31	2.72	5.97	8.62	14.2	1.84	3.76	8.15	11.7	19.6	2.10	4.21	8.52	13.1	23.0	2.26	4.39	8.94	13.4	24.8
	16	0.59	1.99	5.26	7.90	13.5	1.10	2.95	7.32	10.8	18.7	1.33	3.37	7.70	12.2	22.1	1.48	3.57	8.13	12.6	23.8
	24		0.60 <sup>4</sup>	3.89	6.51	12.0		1.39	5.71	9.19	17.0		1.77	6.13	10.5	20.2		1.97	6.55	10.9	21.9
10	12	0.78	2.17	5.40	8.03	13.6	1.29	3.11	7.35	10.8	18.5	1.52	3.54	7.75	12.2	21.7	1.67	3.73	8.18	12.5	23.4
	16		1.30	4.54	7.14	12.7	0.41 <sup>4</sup>	2.15	6.35	9.76	17.4	0.61 <sup>4</sup>	2.55	6.77	11.1	20.5	0.74	2.75	7.20	11.5	22.2
	24			2.90 <sup>3</sup>	5.46	10.9		0.33 <sup>3</sup>	4.46 <sup>4</sup>	7.80	15.3		0.66 <sup>4</sup>	4.91	9.02	18.2		0.86 <sup>4</sup>	5.32	9.46	19.9
12	12		0.97 <sup>3</sup>	4.06 <sup>4</sup>	6.64	12.0	0.13 <sup>3</sup>	1.72 <sup>4</sup>	5.57	8.74	15.8	0.30 <sup>3</sup>	2.10	6.04	10.0	18.6	0.42 <sup>3</sup>	2.30	6.46	10.5	20.3
	16			2.92 <sup>3</sup>	5.43 <sup>4</sup>	10.7		0.50 <sup>3</sup>	4.29 <sup>4</sup>	7.39	14.3		0.82 <sup>3</sup>	4.76 <sup>4</sup>	8.57	17.0		1.02 <sup>4</sup>	5.16 <sup>4</sup>	9.07	18.6
	24			0.83 <sup>2</sup>	3.20 <sup>3</sup>	8.27 <sup>3</sup>			1.94 <sup>3</sup>	4.91 <sup>3</sup>	11.6 <sup>4</sup>			2.39 <sup>3</sup>	5.91 <sup>3</sup>	14.0			2.75 <sup>3</sup>	6.43 <sup>4</sup>	15.5
14	12			2.56 <sup>3</sup>	4.88 <sup>3</sup>	10.1		0.37 <sup>3</sup>	3.75 <sup>3</sup>	6.56 <sup>4</sup>	12.8		0.66 <sup>3</sup>	4.26 <sup>3</sup>	7.69 <sup>4</sup>	15.2		0.85 <sup>3</sup>	4.64 <sup>4</sup>	8.28	16.8
	16			1.25 <sup>2</sup>	3.45 <sup>3</sup>	8.42 <sup>3</sup>			2.29 <sup>3</sup>	4.98 <sup>3</sup>	11.0 <sup>4</sup>			2.75 <sup>3</sup>	5.99 <sup>3</sup>	13.3			3.10 <sup>3</sup>	6.56 <sup>3</sup>	14.8
	24			0.92 <sup>2</sup>	5.45 <sup>3</sup>					2.19 <sup>2</sup>	7.83 <sup>3</sup>			0.06 <sup>2</sup>	2.96 <sup>2</sup>	9.73 <sup>3</sup>			0.32 <sup>2</sup>	3.46 <sup>3</sup>	11.1 <sup>3</sup>
16	12			1.20 <sup>2</sup>	3.16 <sup>3</sup>	7.56 <sup>3</sup>			2.11 <sup>2</sup>	4.50 <sup>3</sup>	9.84 <sup>3</sup>			2.61 <sup>3</sup>	5.49 <sup>3</sup>	11.8 <sup>4</sup>			2.91 <sup>3</sup>	6.09 <sup>3</sup>	13.4
	16				1.64 <sup>2</sup>	5.76 <sup>3</sup>			0.58 <sup>2</sup>	2.83 <sup>2</sup>	7.90 <sup>3</sup>			0.96 <sup>2</sup>	3.64 <sup>2</sup>	9.69 <sup>3</sup>			1.22 <sup>2</sup>	4.17 <sup>3</sup>	11.1 <sup>3</sup>
	24					2.65 <sup>2</sup>					4.54 <sup>2</sup>				0.42 <sup>1</sup>	5.97 <sup>2</sup>				0.81 <sup>2</sup>	7.14 <sup>3</sup>
18	12			0.07 <sup>1</sup>	1.68 <sup>2</sup>	5.30 <sup>2</sup>			0.76 <sup>1</sup>	2.73 <sup>2</sup>	7.18 <sup>3</sup>			1.14 <sup>2</sup>	3.51 <sup>2</sup>	8.78 <sup>3</sup>			1.38 <sup>2</sup>	4.07 <sup>3</sup>	10.2 <sup>3</sup>
	16				0.16 <sup>1</sup>	3.50 <sup>2</sup>				1.06 <sup>1</sup>	5.23 <sup>2</sup>				1.63 <sup>2</sup>	6.62 <sup>2</sup>				2.07 <sup>2</sup>	7.87 <sup>3</sup>
	24					0.41 <sup>1</sup>					1.88 <sup>1</sup>					2.91 <sup>1</sup>					3.82 <sup>2</sup>
20	12				0.51 <sup>1</sup>	3.44 <sup>2</sup>				1.32 <sup>1</sup>	4.96 <sup>2</sup>				1.87 <sup>2</sup>	6.23 <sup>2</sup>			0.12 <sup>1</sup>	2.31 <sup>2</sup>	7.43 <sup>3</sup>
	16					1.69 <sup>1</sup>					3.07 <sup>1</sup>				0.04 <sup>1</sup>	4.12 <sup>2</sup>				0.33 <sup>1</sup>	5.11 <sup>2</sup>
	24															0.54 <sup>1</sup>					1.15 <sup>1</sup>

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 0 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	800S162				800S200				800S250				800S300			
		33 ksi		50 ksi		33 ksi		50 ksi		33 ksi		50 ksi		33 ksi		50 ksi	
		43	54	68	97	43	54	68	97	43	54	68	97	43	54	68	97
8	12	4.96	7.94	10.5	16.3	6.59	11.3	14.9	23.1	7.22	11.9	17.1	28.6	7.37	12.4	17.5	31.2
	16	4.96	7.94	10.5	16.3	6.59	11.3	14.9	23.1	7.22	11.9	17.1	28.6	7.37	12.4	17.5	31.2
	24	4.96	7.94	10.5	16.3	6.59	11.3	14.9	23.1	7.22	11.9	17.1	28.6	7.37	12.4	17.5	31.2
9	12	4.96	7.94	10.5	16.3	6.59	11.3	14.9	23.1	7.20	11.9	17.1	28.5	7.34	12.3	17.4	31.0
	16	4.96	7.94	10.5	16.3	6.59	11.3	14.9	23.1	7.20	11.9	17.1	28.5	7.34	12.3	17.4	31.0
	24	4.96	7.94	10.5	16.3	6.59	11.3	14.9	23.1	7.20	11.9	17.1	28.5	7.34	12.3	17.4	31.0
10	12	4.96	7.94	10.5	16.3	6.59	11.3	14.9	23.1	7.17	11.8	17.0	28.3	7.31	12.3	17.3	30.7
	16	4.96	7.94	10.5	16.3	6.59	11.3	14.9	23.1	7.17	11.8	17.0	28.3	7.31	12.3	17.3	30.7
	24	4.96	7.94	10.5	16.3	6.59	11.3	14.9	23.1	7.17	11.8	17.0	28.3	7.31	12.3	17.3	30.7
12	12	4.96	7.94	10.5	16.3	6.59	11.3	14.9	23.1	7.10	11.6	16.8	27.9	7.23	12.0	17.0	29.9
	16	4.96	7.94	10.5	16.3	6.59	11.3	14.9	23.1	7.10	11.6	16.8	27.9	7.23	12.0	17.0	29.9
	24	4.96	7.94	10.5	16.3	6.59	11.3	14.9	23.1	7.10	11.6	16.8	27.9	7.23	12.0	17.0	29.9
14	12	4.96	7.94	10.5	16.3	6.51	11.1	14.8	23.1	6.99	11.3	16.4	27.1	7.11	11.7	16.5	28.9
	16	4.96	7.94	10.5	16.3	6.51	11.1	14.8	23.1	6.99	11.3	16.4	27.1	7.11	11.7	16.5	28.9
	24	4.96	7.94	10.5	16.3	6.51	11.1	14.8	23.1	6.99	11.3	16.4	27.1	7.11	11.7	16.5	28.9
16	12	4.96	7.94	10.5	16.3	6.34	10.7	14.3	22.5	6.84	11.0	15.8	25.9	6.96	11.4	16.0	27.7
	16	4.96	7.94	10.5	16.3	6.34	10.7	14.3	22.5	6.84	11.0	15.8	25.9	6.96	11.4	16.0	27.7
	24	4.96	7.94	10.5	16.3	6.34	10.7	14.3	22.5	6.84	11.0	15.8	25.9	6.96	11.4	16.0	27.7
18	12	4.96	7.94	10.5	16.3	6.13	10.2	13.6	21.3	6.66	10.5	15.0	24.5	6.79	10.9	15.4	26.3
	16	4.96	7.94	10.5	16.3	6.13	10.2	13.6	21.3	6.66	10.5	15.0	24.5	6.79	10.9	15.4	26.3
	24	4.96	7.93	10.5	16.3	6.13	10.2	13.6	21.3	6.66	10.5	15.0	24.5	6.79	10.9	15.4	26.3
20	12	4.88	7.84	10.5	16.3	5.87	9.52	12.7	20.0	6.46	10.1	14.3	22.9	6.59	10.4	14.8	24.8
	16	4.88	7.84	10.5	16.3	5.87	9.52	12.7	20.0	6.46	10.1	14.3	22.9	6.59	10.4	14.8	24.8
	24	4.88	7.84	10.5	16.3	5.87	9.52	12.7	20.0	6.46	10.1	14.3	22.9	6.59	10.4	14.8	24.8

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 10 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	800S162				800S200				800S250				800S300			
		33 ksi		50 ksi		33 ksi		50 ksi		33 ksi		50 ksi		33 ksi		50 ksi	
		43	54	68	97	43	54	68	97	43	54	68	97	43	54	68	97
8	12	4.77	7.77	10.4	16.2	6.38	11.1	14.7	22.9	6.99	11.7	16.9	28.4	7.14	12.2	17.3	30.9
	16	4.71	7.71	10.3	16.1	6.30	11.0	14.7	22.9	6.92	11.6	16.8	28.3	7.07	12.1	17.2	30.9
	24	4.59	7.59	10.2	16.0	6.16	10.9	14.5	22.7	6.76	11.5	16.7	28.1	6.92	12.0	17.1	30.7
9	12	4.72	7.72	10.3	16.1	6.32	11.0	14.7	22.9	6.91	11.6	16.8	28.2	7.06	12.1	17.1	30.6
	16	4.64	7.64	10.3	16.0	6.22	10.9	14.6	22.8	6.81	11.5	16.7	28.1	6.96	12.0	17.0	30.5
	24	4.48	7.50	10.1	15.9	6.04	10.8	14.4	22.6	6.62	11.3	16.5	27.9	6.77	11.8	16.9	30.3
10	12	4.66	7.66	10.3	16.1	6.24	11.0	14.6	22.8	6.81	11.5	16.6	27.9	6.96	11.9	16.9	30.3
	16	4.56	7.57	10.2	16.0	6.13	10.8	14.5	22.7	6.69	11.3	16.5	27.8	6.84	11.8	16.8	30.1
	24	4.36	7.39	10.0	15.8	5.90	10.6	14.3	22.5	6.45	11.1	16.3	27.5	6.60	11.6	16.6	29.9
12	12	4.52	7.52	10.1	15.9	6.07	10.8	14.4	22.6	6.57	11.1	16.2	27.3	6.71	11.5	16.4	29.3
	16	4.37	7.39	10.0	15.8	5.90	10.6	14.3	22.4	6.39	10.9	16.0	27.1	6.54	11.4	16.3	29.1
	24	4.08	7.12	9.74	15.5	5.57	10.3	13.9	22.1	6.05	10.6	15.7	26.7	6.20	11.0	15.9	28.7
14	12	4.34	7.35	9.96	15.7	5.79	10.4	14.1	22.4	6.26	10.6	15.6	26.3	6.40	11.0	15.8	28.1
	16	4.14	7.16	9.77	15.5	5.55	10.1	13.8	22.1	6.02	10.4	15.3	26.0	6.16	10.8	15.5	27.8
	24	3.74	6.78	9.39	15.2	5.09	9.66	13.4	21.6	5.55	9.93	14.8	25.5	5.70	10.3	15.1	27.2
16	12	4.12	7.13	9.74	15.5	5.39	9.72	13.3	21.4	5.88	10.0	14.7	24.8	6.02	10.4	15.0	26.5
	16	3.85	6.87	9.48	15.2	5.09	9.40	13.0	21.1	5.57	9.72	14.4	24.4	5.72	10.1	14.7	26.1
	24	3.34	6.36	8.97	14.7	4.50	8.78	12.3	20.4	4.96	9.13	13.7	23.7	5.12	9.54	14.0	25.4
18	12	3.87	6.86	9.45	15.2	4.93	8.91	12.3	20.0	5.43	9.32	13.7	23.0	5.59	9.74	14.1	24.8
	16	3.53	6.52	9.11	14.8	4.56	8.52	11.9	19.5	5.05	8.94	13.3	22.6	5.21	9.36	13.7	24.3
	24	2.88	5.87	8.45	14.1	3.85	7.77	11.1	18.7	4.31	8.21	12.5	21.6	4.48	8.63	12.9	23.3
20	12	3.52	6.46	9.10	14.8	4.42	8.01	11.1	18.3	4.94	8.59	12.6	21.1	5.12	8.97	13.2	22.9
	16	3.11	6.04	8.66	14.3	3.98	7.55	10.7	17.8	4.49	8.13	12.1	20.5	4.67	8.52	12.7	22.3
	24	2.35	5.25	7.83	13.4	3.17	6.70	9.76	16.7	3.62	7.27	11.1	19.4	3.81	7.66	11.7	21.2

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 20 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	800S162				800S200				800S250				800S300			
		33 ksi		50 ksi		33 ksi		50 ksi		33 ksi		50 ksi		33 ksi		50 ksi	
		43	54	68	97	43	54	68	97	43	54	68	97	43	54	68	97
8	12	4.59	7.59	10.2	16.0	6.16	10.9	14.5	22.7	6.76	11.5	16.7	28.1	6.92	12.0	17.1	30.7
	16	4.46	7.48	10.1	15.9	6.02	10.7	14.4	22.6	6.61	11.3	16.5	28.0	6.77	11.8	16.9	30.5
	24	4.21	7.25	9.88	15.7	5.73	10.4	14.1	22.3	6.32	11.1	16.2	27.6	6.48	11.5	16.6	30.2
9	12	4.48	7.50	10.1	15.9	6.04	10.8	14.4	22.6	6.62	11.3	16.5	27.9	6.77	11.8	16.9	30.3
	16	4.32	7.35	9.97	15.8	5.85	10.6	14.2	22.4	6.43	11.1	16.3	27.6	6.59	11.6	16.7	30.1
	24	4.01	7.06	9.69	15.5	5.49	10.2	13.9	22.1	6.05	10.8	15.9	27.2	6.21	11.2	16.3	29.7
10	12	4.36	7.39	10.0	15.8	5.90	10.6	14.3	22.5	6.45	11.1	16.3	27.5	6.60	11.6	16.6	29.9
	16	4.17	7.20	9.83	15.6	5.67	10.4	14.0	22.2	6.22	10.9	16.0	27.3	6.37	11.3	16.4	29.6
	24	3.78	6.84	9.47	15.3	5.22	9.91	13.6	21.8	5.75	10.4	15.5	26.8	5.91	10.9	15.9	29.1
12	12	4.08	7.12	9.74	15.5	5.57	10.3	13.9	22.1	6.05	10.6	15.7	26.7	6.20	11.0	15.9	28.7
	16	3.80	6.85	9.47	15.3	5.23	9.91	13.6	21.8	5.71	10.3	15.3	26.3	5.86	10.7	15.6	28.3
	24	3.23	6.32	8.95	14.7	4.57	9.23	12.9	21.1	5.03	9.61	14.6	25.5	5.20	10.0	14.9	27.5
14	12	3.74	6.78	9.39	15.2	5.09	9.66	13.4	21.6	5.55	9.93	14.8	25.5	5.70	10.3	15.1	27.2
	16	3.35	6.40	9.02	14.8	4.64	9.19	12.9	21.1	5.09	9.48	14.3	24.9	5.25	9.90	14.6	26.7
	24	2.60	5.68	8.30	14.0	3.77	8.27	12.0	20.2	4.19	8.60	13.4	23.8	4.36	9.01	13.7	25.6
16	12	3.34	6.36	8.97	14.7	4.50	8.78	12.3	20.4	4.96	9.13	13.7	23.7	5.12	9.54	14.0	25.4
	16	2.84	5.87	8.47	14.2	3.94	8.19	11.7	19.8	4.38	8.55	13.1	23.0	4.55	8.96	13.4	24.7
	24	1.88	4.93	7.52	13.2	2.86	7.05	10.5	18.5	3.26	7.44	11.9	21.6	3.44	7.85	12.2	23.3
18	12	2.88	5.87	8.45	14.1	3.85	7.77	11.1	18.7	4.31	8.21	12.5	21.6	4.48	8.63	12.9	23.3
	16	2.27	5.25	7.82	13.5	3.17	7.06	10.4	17.9	3.61	7.51	11.7	20.7	3.79	7.93	12.2	22.4
	24	1.13 <sup>3</sup>	4.10 <sup>4</sup>	6.62	12.2	1.92 <sup>4</sup>	5.74	8.97	16.3	2.30	6.19	10.2	19.1	2.48	6.60	10.7	20.7
20	12	2.35	5.25	7.83	13.4	3.17	6.70	9.76	16.7	3.62	7.27	11.1	19.4	3.81	7.66	11.7	21.2
	16	1.65 <sup>4</sup>	4.52	7.06	12.6	2.41	5.90	8.92	15.8	2.82	6.46	10.2	18.4	3.00	6.84	10.8	20.1
	24	0.37 <sup>3</sup>	3.20 <sup>3</sup>	5.64 <sup>4</sup>	11.0	1.03 <sup>3</sup>	4.44 <sup>4</sup>	7.38	14.0	1.35 <sup>3</sup>	4.97 <sup>4</sup>	8.55	16.5	1.52 <sup>3</sup>	5.33 <sup>4</sup>	9.13	18.1

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 30 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	800S162				800S200				800S250				800S300			
		33 ksi		50 ksi		33 ksi		50 ksi		33 ksi		50 ksi		33 ksi		50 ksi	
		43	54	68	97	43	54	68	97	43	54	68	97	43	54	68	97
8	12	4.40	7.42	10.0	15.8	5.94	10.7	14.3	22.5	6.54	11.3	16.5	27.9	6.70	11.8	16.9	30.4
	16	4.21	7.25	9.88	15.7	5.73	10.4	14.1	22.3	6.32	11.1	16.2	27.6	6.48	11.5	16.6	30.2
	24	3.84	6.91	9.55	15.3	5.30	10.0	13.7	21.9	5.87	10.6	15.8	27.2	6.04	11.1	16.2	29.7
9	12	4.24	7.28	9.90	15.7	5.76	10.5	14.1	22.3	6.33	11.0	16.2	27.5	6.49	11.5	16.6	30.0
	16	4.01	7.06	9.69	15.5	5.49	10.2	13.9	22.1	6.05	10.8	15.9	27.2	6.21	11.2	16.3	29.7
	24	3.54	6.63	9.26	15.1	4.94	9.65	13.3	21.5	5.48	10.2	15.3	26.6	5.65	10.7	15.7	29.0
10	12	4.07	7.11	9.74	15.5	5.56	10.3	13.9	22.1	6.10	10.8	15.9	27.1	6.25	11.2	16.2	29.5
	16	3.78	6.84	9.47	15.3	5.22	9.91	13.6	21.8	5.75	10.4	15.5	26.8	5.91	10.9	15.9	29.1
	24	3.20	6.31	8.94	14.7	4.54	9.24	12.9	21.1	5.05	9.76	14.8	26.0	5.22	10.2	15.2	28.3
12	12	3.65	6.71	9.34	15.1	5.07	9.74	13.4	21.6	5.54	10.1	15.1	26.1	5.69	10.5	15.4	28.1
	16	3.23	6.32	8.95	14.7	4.57	9.23	12.9	21.1	5.03	9.61	14.6	25.5	5.20	10.0	14.9	27.5
	24	2.41	5.54	8.18	14.0	3.62	8.25	11.9	20.1	4.05	8.65	13.6	24.4	4.22	9.08	13.9	26.4
14	12	3.16	6.22	8.84	14.6	4.42	8.96	12.7	20.9	4.86	9.26	14.1	24.6	5.02	9.67	14.4	26.4
	16	2.60	5.68	8.30	14.0	3.77	8.27	12.0	20.2	4.19	8.60	13.4	23.8	4.36	9.01	13.7	25.6
	24	1.52	4.63	7.24	13.0	2.52	6.96	10.6	18.8	2.91	7.33	12.0	22.3	3.09	7.74	12.3	24.0
16	12	2.59	5.63	8.23	13.9	3.66	7.90	11.4	19.4	4.09	8.27	12.8	22.6	4.26	8.68	13.1	24.3
	16	1.88	4.93	7.52	13.2	2.86	7.05	10.5	18.5	3.26	7.44	11.9	21.6	3.44	7.85	12.2	23.3
	24	0.56 <sup>3</sup>	3.61 <sup>4</sup>	6.16	11.8	1.36 <sup>4</sup>	5.46	8.9	16.7	1.70 <sup>4</sup>	5.88	10.1	19.6	1.88	6.27	10.5	21.3
18	12	1.97	4.96	7.51	13.1	2.85	6.72	10.0	17.5	3.27	7.17	11.3	20.3	3.45	7.58	11.8	22.0
	16	1.13 <sup>3</sup>	4.10 <sup>4</sup>	6.62	12.2	1.92 <sup>4</sup>	5.74	8.97	16.3	2.30	6.19	10.2	19.1	2.48	6.60	10.7	20.7
	24		2.53 <sup>3</sup>	4.98 <sup>3</sup>	10.4	0.23 <sup>3</sup>	3.93 <sup>3</sup>	7.07 <sup>4</sup>	14.2	0.51 <sup>3</sup>	4.39 <sup>4</sup>	8.18	16.7	0.67 <sup>3</sup>	4.76 <sup>4</sup>	8.68	18.3
20	12	1.31 <sup>3</sup>	4.18 <sup>4</sup>	6.69	12.2	2.05 <sup>4</sup>	5.52	8.52	15.3	2.43	6.07	9.78	17.9	2.62	6.45	10.4	19.6
	16	0.37 <sup>3</sup>	3.20 <sup>3</sup>	5.64 <sup>4</sup>	11.0	1.03 <sup>3</sup>	4.44 <sup>4</sup>	7.38	14.0	1.35 <sup>3</sup>	4.97 <sup>4</sup>	8.55	16.5	1.52 <sup>3</sup>	5.33 <sup>4</sup>	9.13	18.1
	24		1.44 <sup>2</sup>	3.75 <sup>3</sup>	8.89 <sup>3</sup>		2.52 <sup>3</sup>	5.31 <sup>3</sup>	11.7 <sup>4</sup>		2.98 <sup>3</sup>	6.31 <sup>3</sup>	13.9		3.30 <sup>3</sup>	6.85 <sup>4</sup>	15.4

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720



## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 40 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	800S162				800S200				800S250				800S300			
		33 ksi		50 ksi		33 ksi		50 ksi		33 ksi		50 ksi		33 ksi		50 ksi	
		43	54	68	97	43	54	68	97	43	54	68	97	43	54	68	97
8	12	4.21	7.25	9.88	15.7	5.73	10.4	14.1	22.3	6.32	11.1	16.2	27.6	6.48	11.5	16.6	30.2
	16	3.97	7.03	9.66	15.4	5.44	10.2	13.8	22.0	6.02	10.8	15.9	27.3	6.18	11.3	16.3	29.9
	24	3.48	6.58	9.22	15.0	4.87	9.59	13.3	21.5	5.43	10.2	15.3	26.7	5.60	10.7	15.7	29.2
9	12	4.01	7.06	9.69	15.5	5.49	10.2	13.9	22.1	6.05	10.8	15.9	27.2	6.21	11.2	16.3	29.7
	16	3.70	6.77	9.40	15.2	5.12	9.83	13.5	21.7	5.67	10.4	15.5	26.8	5.84	10.9	15.9	29.2
	24	3.08	6.20	8.84	14.6	4.40	9.11	12.8	21.0	4.92	9.68	14.8	26.0	5.10	10.2	15.2	28.4
10	12	3.78	6.84	9.47	15.3	5.22	9.91	13.6	21.8	5.75	10.4	15.5	26.8	5.91	10.9	15.9	29.1
	16	3.39	6.48	9.12	14.9	4.77	9.46	13.1	21.3	5.28	9.98	15.1	26.2	5.45	10.4	15.4	28.5
	24	2.63	5.77	8.42	14.2	3.88	8.57	12.3	20.5	4.36	9.09	14.1	25.2	4.54	9.54	14.5	27.5
12	12	3.23	6.32	8.95	14.7	4.57	9.23	12.9	21.1	5.03	9.61	14.6	25.5	5.20	10.0	14.9	27.5
	16	2.68	5.80	8.43	14.2	3.93	8.57	12.3	20.4	4.37	8.97	13.9	24.8	4.54	9.39	14.2	26.7
	24	1.62	4.78	7.42	13.2	2.69	7.29	11.0	19.1	3.09	7.71	12.5	23.3	3.27	8.13	12.9	25.2
14	12	2.60	5.68	8.30	14.0	3.77	8.27	12.0	20.2	4.19	8.60	13.4	23.8	4.36	9.01	13.7	25.6
	16	1.87	4.98	7.59	13.3	2.93	7.39	11.1	19.2	3.33	7.75	12.4	22.8	3.51	8.16	12.7	24.5
	24	0.49 <sup>3</sup>	3.63	6.23	11.9	1.34 <sup>4</sup>	5.72	9.34	17.4	1.69	6.11	10.6	20.8	1.87	6.51	11.0	22.4
16	12	1.88	4.93	7.52	13.2	2.86	7.05	10.5	18.5	3.26	7.44	11.9	21.6	3.44	7.85	12.2	23.3
	16	0.99 <sup>4</sup>	4.04	6.60	12.2	1.84 <sup>4</sup>	5.97	9.43	17.3	2.21	6.38	10.7	20.3	2.39	6.78	11.1	21.9
	24		2.38 <sup>3</sup>	4.89 <sup>4</sup>	10.4		3.98 <sup>3</sup>	7.34	15.0	0.25 <sup>3</sup>	4.41 <sup>4</sup>	8.47	17.7	0.42 <sup>3</sup>	4.78 <sup>4</sup>	8.90	19.3
18	12	1.13 <sup>3</sup>	4.10 <sup>4</sup>	6.62	12.2	1.92 <sup>4</sup>	5.74	8.97	16.3	2.30	6.19	10.2	19.1	2.48	6.60	10.7	20.7
	16	0.08 <sup>3</sup>	3.04 <sup>3</sup>	5.51 <sup>4</sup>	11.0	0.77 <sup>3</sup>	4.51 <sup>4</sup>	7.68	14.9	1.08 <sup>3</sup>	4.97 <sup>4</sup>	8.83	17.5	1.25 <sup>4</sup>	5.35	9.33	19.1
	24		1.10 <sup>2</sup>	3.48 <sup>3</sup>	8.75 <sup>4</sup>		2.30 <sup>3</sup>	5.33 <sup>3</sup>	12.3 <sup>4</sup>		2.73 <sup>3</sup>	6.32 <sup>3</sup>	14.6		3.06 <sup>3</sup>	6.81 <sup>4</sup>	16.1
20	12	0.37 <sup>3</sup>	3.20 <sup>3</sup>	5.64 <sup>4</sup>	11.0	1.03 <sup>3</sup>	4.44 <sup>4</sup>	7.38	14.0	1.35 <sup>3</sup>	4.97 <sup>4</sup>	8.55	16.5	1.52 <sup>3</sup>	5.33 <sup>4</sup>	9.13	18.1
	16		2.00 <sup>3</sup>	4.36 <sup>3</sup>	9.57 <sup>4</sup>		3.13 <sup>3</sup>	5.97 <sup>3</sup>	12.5	0.02 <sup>3</sup>	3.61 <sup>3</sup>	7.03 <sup>4</sup>	14.7	0.17 <sup>3</sup>	3.95 <sup>3</sup>	7.59 <sup>4</sup>	16.3
	24			2.07 <sup>2</sup>	7.00 <sup>3</sup>		0.80 <sup>2</sup>	3.46 <sup>3</sup>	9.58 <sup>3</sup>		1.19 <sup>2</sup>	4.30 <sup>3</sup>	11.6 <sup>3</sup>		1.46 <sup>2</sup>	4.80 <sup>3</sup>	13.0 <sup>4</sup>

<sup>1</sup> Deflection meets L/120      <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240      <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 50 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	800S162				800S200				800S250				800S300			
		33 ksi	50 ksi			33 ksi	50 ksi			33 ksi	50 ksi			33 ksi	50 ksi		
		43	54	68	97	43	54	68	97	43	54	68	97	43	54	68	97
8	12	4.03	7.08	9.71	15.5	5.51	10.2	13.9	22.1	6.09	10.8	16.0	27.4	6.26	11.3	16.4	29.9
	16	3.72	6.80	9.44	15.2	5.16	9.88	13.6	21.8	5.72	10.5	15.6	27.0	5.89	11.0	16.0	29.5
	24	3.11	6.24	8.89	14.7	4.45	9.17	12.9	21.1	4.99	9.8	14.9	26.2	5.16	10.3	15.3	28.7
9	12	3.77	6.85	9.48	15.3	5.21	9.92	13.6	21.8	5.77	10.5	15.6	26.9	5.93	11.0	16.0	29.4
	16	3.38	6.49	9.12	14.9	4.76	9.47	13.2	21.4	5.30	10.0	15.1	26.4	5.47	10.5	15.5	28.8
	24	2.62	5.77	8.43	14.2	3.87	8.58	12.3	20.5	4.37	9.15	14.2	25.4	4.55	9.61	14.6	27.8
10	12	3.49	6.57	9.21	15.0	4.88	9.58	13.3	21.5	5.40	10.1	15.2	26.4	5.56	10.6	15.5	28.7
	16	3.01	6.13	8.77	14.6	4.32	9.01	12.7	20.9	4.82	9.53	14.6	25.7	4.99	9.99	14.9	28.0
	24	2.07	5.25	7.90	13.7	3.23	7.91	11.6	19.8	3.69	8.44	13.4	24.5	3.87	8.88	13.8	26.7
12	12	2.82	5.93	8.56	14.3	4.09	8.74	12.4	20.6	4.54	9.13	14.1	25.0	4.71	9.55	14.4	26.9
	16	2.15	5.29	7.92	13.7	3.30	7.93	11.6	19.8	3.73	8.33	13.2	24.0	3.90	8.76	13.5	26.0
	24	0.85	4.04	6.68	12.4	1.79	6.36	10.0	18.1	2.16	6.79	11.5	22.2	2.35	7.21	11.9	24.1
14	12	2.05	5.15	7.76	13.5	3.13	7.61	11.3	19.4	3.54	7.96	12.7	23.0	3.72	8.37	13.0	24.8
	16	1.17 <sup>4</sup>	4.29	6.90	12.6	2.12	6.54	10.2	18.3	2.50	6.92	11.5	21.8	2.68	7.32	11.9	23.5
	24		2.67 <sup>3</sup>	5.25	10.9	0.21 <sup>3</sup>	4.53 <sup>4</sup>	8.11	16.1	0.52 <sup>4</sup>	4.94	9.31	19.3	0.70 <sup>4</sup>	5.33	9.70	21.0
16	12	1.21 <sup>4</sup>	4.26	6.83	12.5	2.09	6.24	9.70	17.6	2.47	6.64	11.0	20.6	2.65	7.05	11.4	22.2
	16	0.14 <sup>3</sup>	3.19 <sup>3</sup>	5.73	11.3	0.88 <sup>3</sup>	4.95 <sup>4</sup>	8.36	16.1	1.21 <sup>4</sup>	5.38	9.55	19.0	1.38 <sup>4</sup>	5.76	9.97	20.6
	24		1.22 <sup>3</sup>	3.68 <sup>3</sup>	9.12 <sup>4</sup>		2.59 <sup>3</sup>	5.89 <sup>3</sup>	13.4		3.03 <sup>3</sup>	6.92 <sup>4</sup>	16.0		3.37 <sup>3</sup>	7.37 <sup>4</sup>	17.5
18	12	0.34 <sup>3</sup>	3.30 <sup>3</sup>	5.78 <sup>4</sup>	11.3	1.05 <sup>3</sup>	4.81 <sup>4</sup>	8.00	15.2	1.38 <sup>4</sup>	5.27	9.17	17.9	1.55 <sup>4</sup>	5.66	9.66	19.5
	16		2.04 <sup>3</sup>	4.47 <sup>3</sup>	9.83		3.37 <sup>3</sup>	6.47 <sup>4</sup>	13.5		3.82 <sup>3</sup>	7.54 <sup>4</sup>	16.0	0.11 <sup>3</sup>	4.18 <sup>3</sup>	8.04	17.6
	24			2.08 <sup>2</sup>	7.21 <sup>3</sup>		0.80 <sup>2</sup>	3.72 <sup>3</sup>	10.4 <sup>3</sup>		1.20 <sup>3</sup>	4.59 <sup>3</sup>	12.6 <sup>4</sup>		1.49 <sup>3</sup>	5.07 <sup>3</sup>	14.0 <sup>4</sup>
20	12		2.29 <sup>3</sup>	4.67 <sup>3</sup>	9.91 <sup>4</sup>	0.08 <sup>3</sup>	3.45 <sup>3</sup>	6.31 <sup>3</sup>	12.8	0.34 <sup>3</sup>	3.94 <sup>3</sup>	7.39 <sup>4</sup>	15.1	0.49 <sup>3</sup>	4.29 <sup>3</sup>	7.96	16.7
	16		0.90 <sup>2</sup>	3.17 <sup>3</sup>	8.24 <sup>3</sup>		1.92 <sup>3</sup>	4.67 <sup>3</sup>	11.0 <sup>4</sup>		2.36 <sup>3</sup>	5.62 <sup>3</sup>	13.1 <sup>4</sup>		2.66 <sup>3</sup>	6.15 <sup>3</sup>	14.6
	24			0.53 <sup>2</sup>	5.26 <sup>2</sup>			1.78 <sup>2</sup>	7.65 <sup>3</sup>			2.47 <sup>2</sup>	9.42 <sup>3</sup>			2.91 <sup>3</sup>	10.7 <sup>3</sup>

<sup>1</sup> Deflection meets L/120    <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240    <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 60 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	800S162				800S200				800S250				800S300			
		33 ksi	50 ksi			33 ksi	50 ksi			33 ksi	50 ksi			33 ksi	50 ksi		
		43	54	68	97	43	54	68	97	43	54	68	97	43	54	68	97
8	12	3.84	6.91	9.55	15.3	5.30	10.0	13.7	21.9	5.87	10.6	15.8	27.2	6.04	11.1	16.2	29.7
	16	3.48	6.58	9.22	15.0	4.87	9.59	13.3	21.5	5.43	10.2	15.3	26.7	5.60	10.7	15.7	29.2
	24	2.75	5.91	8.56	14.4	4.03	8.76	12.5	20.7	4.55	9.36	14.4	25.7	4.72	9.83	14.9	28.2
9	12	3.54	6.63	9.26	15.1	4.94	9.65	13.3	21.5	5.48	10.2	15.3	26.6	5.65	10.7	15.7	29.0
	16	3.08	6.20	8.84	14.6	4.40	9.11	12.8	21.0	4.92	9.68	14.8	26.0	5.10	10.2	15.2	28.4
	24	2.16	5.35	8.01	13.8	3.34	8.05	11.8	20.0	3.82	8.62	13.6	24.8	4.00	9.07	14.0	27.1
10	12	3.20	6.31	8.94	14.7	4.54	9.24	12.9	21.1	5.05	9.76	14.8	26.0	5.22	10.2	15.2	28.3
	16	2.63	5.77	8.42	14.2	3.88	8.57	12.3	20.5	4.36	9.09	14.1	25.2	4.54	9.54	14.5	27.5
	24	1.52	4.73	7.39	13.2	2.59	7.26	11.0	19.2	3.02	7.79	12.7	23.7	3.21	8.23	13.1	25.9
12	12	2.41	5.54	8.18	14.0	3.62	8.25	11.9	20.1	4.05	8.65	13.6	24.4	4.22	9.08	13.9	26.4
	16	1.62	4.78	7.42	13.2	2.69	7.29	11.0	19.1	3.09	7.71	12.5	23.3	3.27	8.13	12.9	25.2
	24	0.09 <sup>4</sup>	3.32	5.95	11.7	0.91	5.45	9.11	17.2	1.26	5.90	10.6	21.1	1.44	6.30	10.9	23.0
14	12	1.52	4.63	7.24	13.0	2.52	6.96	10.6	18.8	2.91	7.33	12.0	22.3	3.09	7.74	12.3	24.0
	16	0.49 <sup>3</sup>	3.63	6.23	11.9	1.34 <sup>4</sup>	5.72	9.34	17.4	1.69	6.11	10.6	20.8	1.87	6.51	11.0	22.4
	24		1.75 <sup>3</sup>	4.30 <sup>4</sup>	9.90		3.38 <sup>3</sup>	6.92	14.8		3.82 <sup>4</sup>	8.06	17.9		4.18 <sup>4</sup>	8.47	19.5
16	12	0.56 <sup>3</sup>	3.61 <sup>4</sup>	6.16	11.8	1.36 <sup>4</sup>	5.46	8.89	16.7	1.70 <sup>4</sup>	5.88	10.1	19.6	1.88	6.27	10.5	21.3
	16		2.38 <sup>3</sup>	4.89 <sup>4</sup>	10.4		3.98 <sup>3</sup>	7.34	15.0	0.25 <sup>3</sup>	4.41 <sup>4</sup>	8.47	17.7	0.42 <sup>3</sup>	4.78 <sup>4</sup>	8.90	19.3
	24		0.12 <sup>2</sup>	2.54 <sup>3</sup>	7.88 <sup>3</sup>		1.29 <sup>3</sup>	4.50 <sup>3</sup>	11.9 <sup>4</sup>		1.72 <sup>3</sup>	5.45 <sup>3</sup>	14.3		2.03 <sup>3</sup>	5.90 <sup>3</sup>	15.8
18	12		2.53 <sup>3</sup>	4.98 <sup>3</sup>	10.4	0.23 <sup>3</sup>	3.93 <sup>3</sup>	7.07 <sup>4</sup>	14.2	0.51 <sup>3</sup>	4.39 <sup>4</sup>	8.18	16.7	0.67 <sup>3</sup>	4.76 <sup>4</sup>	8.68	18.3
	16		1.10 <sup>2</sup>	3.48 <sup>3</sup>	8.75 <sup>4</sup>		2.30 <sup>3</sup>	5.33 <sup>3</sup>	12.3 <sup>4</sup>		2.73 <sup>3</sup>	6.32 <sup>3</sup>	14.6		3.06 <sup>3</sup>	6.81 <sup>4</sup>	16.1
	24			0.77 <sup>2</sup>	5.76 <sup>3</sup>			2.22 <sup>2</sup>	8.73 <sup>3</sup>			2.97 <sup>3</sup>	10.7 <sup>3</sup>			3.42 <sup>3</sup>	12.1 <sup>3</sup>
20	12		1.44 <sup>2</sup>	3.75 <sup>3</sup>	8.89 <sup>3</sup>		2.52 <sup>3</sup>	5.31 <sup>3</sup>	11.7 <sup>4</sup>		2.98 <sup>3</sup>	6.31 <sup>3</sup>	13.9		3.30 <sup>3</sup>	6.85 <sup>4</sup>	15.4
	16			2.07 <sup>2</sup>	7.00 <sup>3</sup>		0.80 <sup>2</sup>	3.46 <sup>3</sup>	9.58 <sup>3</sup>		1.19 <sup>2</sup>	4.30 <sup>3</sup>	11.6 <sup>3</sup>		1.46 <sup>2</sup>	4.80 <sup>3</sup>	13.0 <sup>4</sup>
	24				3.65 <sup>2</sup>			0.22 <sup>2</sup>	5.85 <sup>2</sup>			0.77 <sup>2</sup>	7.44 <sup>3</sup>			1.15 <sup>2</sup>	8.62 <sup>3</sup>

<sup>1</sup> Deflection meets L/120    <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240    <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## COMBINED AXIAL AND LATERAL LOAD TABLE

Limiting Factored Axial Compressive Resistance Per Stud (kip)

### 70 psf Factored Lateral Load

Wall Height (ft)	Stud Spacing (in.) o.c.	800S162				800S200				800S250				800S300			
		33 ksi		50 ksi		33 ksi		50 ksi		33 ksi		50 ksi		33 ksi		50 ksi	
		43	54	68	97	43	54	68	97	43	54	68	97	43	54	68	97
8	12	3.66	6.75	9.38	15.2	5.09	9.81	13.5	21.7	5.65	10.4	15.6	26.9	5.82	10.9	16.0	29.4
	16	3.23	6.35	9.00	14.8	4.59	9.31	13.0	21.2	5.13	9.92	15.0	26.4	5.30	10.4	15.4	28.9
	24	2.39	5.58	8.23	14.0	3.61	8.34	12.1	20.3	4.11	8.95	14.0	25.3	4.29	9.41	14.4	27.7
9	12	3.31	6.41	9.05	14.9	4.67	9.38	13.1	21.3	5.20	9.95	15.0	26.3	5.37	10.4	15.4	28.7
	16	2.77	5.92	8.56	14.4	4.05	8.76	12.5	20.7	4.55	9.33	14.4	25.6	4.73	9.79	14.8	28.0
	24	1.71	4.93	7.60	13.4	2.82	7.53	11.2	19.4	3.28	8.10	13.1	24.2	3.46	8.54	13.5	26.5
10	12	2.91	6.04	8.68	14.5	4.21	8.90	12.6	20.8	4.71	9.42	14.5	25.6	4.88	9.87	14.8	27.9
	16	2.26	5.42	8.07	13.9	3.45	8.13	11.8	20.0	3.91	8.66	13.6	24.7	4.09	9.10	14.0	26.9
	24	0.97	4.22	6.88	12.7	1.96	6.62	10.3	18.5	2.36	7.15	12.0	23.0	2.55	7.58	12.4	25.1
12	12	2.01	5.16	7.80	13.6	3.15	7.77	11.4	19.6	3.57	8.18	13.0	23.8	3.75	8.60	13.4	25.8
	16	1.10	4.29	6.92	12.7	2.08	6.67	10.3	18.5	2.47	7.10	11.9	22.5	2.65	7.51	12.2	24.4
	24		2.61 <sup>4</sup>	5.24	11.0	0.06 <sup>4</sup>	4.56	8.21	16.3	0.38	5.02	9.58	20.0	0.56	5.41	9.98	21.9
14	12	1.00 <sup>4</sup>	4.13	6.73	12.4	1.92	6.33	9.97	18.1	2.29	6.72	11.3	21.5	2.47	7.12	11.6	23.2
	16		2.99 <sup>4</sup>	5.57	11.2	0.58 <sup>4</sup>	4.92	8.51	16.5	0.90 <sup>4</sup>	5.33	9.74	19.8	1.09	5.72	10.1	21.4
	24		0.85 <sup>3</sup>	3.38 <sup>3</sup>	8.93		2.28 <sup>3</sup>	5.78 <sup>4</sup>	13.6		2.72 <sup>3</sup>	6.84 <sup>4</sup>	16.5		3.07 <sup>3</sup>	7.27	18.1
16	12		2.99 <sup>3</sup>	5.52	11.1	0.65 <sup>3</sup>	4.71 <sup>4</sup>	8.10	15.8	0.96 <sup>4</sup>	5.13	9.27	18.7	1.14 <sup>4</sup>	5.51	9.70	20.3
	16		1.60 <sup>3</sup>	4.08 <sup>3</sup>	9.55		3.05 <sup>3</sup>	6.36 <sup>4</sup>	13.9		3.48 <sup>3</sup>	7.43 <sup>4</sup>	16.6		3.83 <sup>3</sup>	7.87	18.1
	24			1.44 <sup>3</sup>	6.69 <sup>3</sup>		0.05 <sup>2</sup>	3.19 <sup>3</sup>	10.4 <sup>3</sup>		0.47 <sup>3</sup>	4.04 <sup>3</sup>	12.7 <sup>4</sup>		0.74 <sup>3</sup>	4.49 <sup>3</sup>	14.1
18	12		1.80 <sup>3</sup>	4.21 <sup>3</sup>	9.56 <sup>4</sup>		3.10 <sup>3</sup>	6.18 <sup>3</sup>	13.2		3.54 <sup>3</sup>	7.23 <sup>4</sup>	15.6		3.90 <sup>3</sup>	7.73 <sup>4</sup>	17.2
	16		0.21 <sup>2</sup>	2.54 <sup>3</sup>	7.71 <sup>3</sup>		1.29 <sup>2</sup>	4.25 <sup>3</sup>	11.0 <sup>4</sup>		1.70 <sup>3</sup>	5.15 <sup>3</sup>	13.2 <sup>4</sup>		2.00 <sup>3</sup>	5.64 <sup>3</sup>	14.7
	24				4.38 <sup>2</sup>			0.80 <sup>2</sup>	7.11 <sup>3</sup>			1.44 <sup>2</sup>	8.93 <sup>3</sup>			1.86 <sup>2</sup>	10.2 <sup>3</sup>
20	12		0.63 <sup>2</sup>	2.89 <sup>3</sup>	7.92 <sup>3</sup>		1.64 <sup>2</sup>	4.36 <sup>3</sup>	10.6 <sup>3</sup>		2.06 <sup>3</sup>	5.28 <sup>3</sup>	12.7 <sup>4</sup>		2.36 <sup>3</sup>	5.80 <sup>3</sup>	14.2
	16			1.03 <sup>2</sup>	5.83 <sup>3</sup>			2.33 <sup>2</sup>	8.28 <sup>3</sup>		0.09 <sup>2</sup>	3.06 <sup>2</sup>	10.1 <sup>3</sup>		0.32 <sup>2</sup>	3.52 <sup>3</sup>	11.4 <sup>3</sup>
	24				2.14 <sup>2</sup>				4.17 <sup>2</sup>				5.58 <sup>2</sup>				6.65 <sup>3</sup>

<sup>1</sup> Deflection meets L/120    <sup>3</sup> Deflection meets L/360

<sup>2</sup> Deflection meets L/240    <sup>4</sup> Deflection meets L/600

If no note, deflection meets L/720

## Floor Joist Load Tables

### Table Notes

- 1 Loads are assumed to be uniformly distributed over entire span(s).
- 2 Load values are based on continuous support of the compression flange over the full length of the joist and the tension flange is laterally braced at a maximum spacing of 8'-0".
- 3 Joists must be braced against rotation at all supports.
- 4 End shear and web crippling resistances are not reduced for punchouts.
- 5 End web crippling check is based on a 3.5" bearing length. Where allowable spans are followed by (\*), web stiffeners are required at end supports.
- 6 Web stiffeners are required at interior supports.

### Bridging Recommendations

Bracing components shall be designed based on Section C2 of S136-16 with the minimum required number of rows as shown below. Additional bridging rows may be required by design.

<b>Span (ft)</b>	<b>Minimum Number of Rows</b>
up to 16	1 at mid span
16 to 24	2 at 1/3 point
24 to 32	3 at 1/4 point
32 to 40	4 at 1/5 point

**FLOOR JOIST LOAD TABLE**  
**Uniformly Distributed Single Span Loads (psf) with  $K_p = 0$**

Strength - Factored Loads												L/360 - Specified Loads														
Span (ft)	Section Design Criteria	600S162-43			600S162-54			600S162-68			600S162-97			600S200-43			600S200-54			600S200-68			600S200-97			
		Spacing (in.)			Spacing (in.)			Spacing (in.)			Spacing (in.)			Spacing (in.)			Spacing (in.)			Spacing (in.)			Spacing (in.)			
		12	16	24	12	16	24	12	16	24	12	16	24	12	16	24	12	16	24	12	16	24	12	16	24	
8	Strength	203*	152*	101*	360*	270*	180*	486*	364*	243*			371	232*	174*	116*	411*	308*	205*			416*	277*			430*
	L/360	197	147	98	243	182	121	300	225	150			204	228	171	114	282	212	141			262	174			239
9	Strength	160	120	80	284*	213*	142*	384	288	192		440	293	183*	137*	91*	325*	243*	162*	438*	329*	219*			339	
	L/360	138	103	69	171	128	85	210	158	105		215	143	160	120	80	198	148	99	245	184	122			167	
10	Strength	130	97	65	230	173	115	311	233	155	476	357	238	148	111	74	263*	197*	131*	355	266	177			413	
	L/360	101	75	50	124	93	62	153	115	76	209	156	104	117	87	58	144	108	72	178	134	89			183	
11	Strength	107	80	53	190	142	95	257	192	128	393	295	196	122	92	61	217	163*	108	293	220	146	455	341	227	
	L/360	75	56	37	93	70	46	115	86	57	157	117	78	87	65	43	108	81	54	134	100	67	183	137	91	
12	Strength	90	67	45	160	120	80	216	162	108	330	247	165	103	77	51	182	137	91	246	185	123	382	286	191	
	L/360	58	43	29	72	54	36	88	66	44	121	90	60	67	50	33	83	62	41	103	77	51	141	106	70	
13	Strength	76	57	38	136	102	68	184	138	92	281	211	140	87	65	43	155	116	77	210	157	105	325	244	162	
	L/360	45	34	22	56	42	28	69	52	34	95	71	47	53	39	26	65	49	32	81	61	40	111	83	55	
14	Strength	66	49	33	117	88	58	158	119	79	242	182	121	75	56	37	134	100	67	181	135	90	280	210	140	
	L/360	36	27	18	45	34	22	56	42	28	76	57	38	42	31	21	52	39	26	65	48	32	89	66	44	
15	Strength	57	43	28	102	76	51	138	103	69	211	158	105	66	49	33	117	87	58	157	118	78	244	183	122	
	L/360	29	22	14	36	27	18	45	34	22	62	46	31	34	26	17	42	32	21	52	39	26	72	54	36	
16	Strength	50	38	25	90	67	45	121	91	60	185	139	92	58	43	29	102	77	51	138	104	69	215	161	107	
	L/360	24	18	12	30	22	15	37	28	18	51	38	25	28	21	14	35	26	17	43	32	21	59	44	29	
17	Strength	44	33	22	79	59	39	107	80	53	164	123	82	51	38	25	91	68	45	122	92	61	190	142	95	
	L/360	20	15	10	25	19	12	31	23	15	42	31	21	23	17	11	29	22	14	36	27	18	49	37	24	
18	Strength	40	30		71	53	35	96	72	48	146	110	73	45	34	22	81	60	40	109	82	54	169	127	84	
	L/360	17	12		21	16	10	26	19	13	35	26	17	20	15	10	24	18	12	30	23	15	41	31	20	
19	Strength	36	27		63	47		86	64	43	131	98	65	41	30		72	54	36	98	73	49	152	114	76	
	L/360	14	11		18	13		22	16	11	30	22	15	17	12		21	15	10	26	19	13	35	26	17	
20	Strength	32			57	43		77	58		119	89	59	37	27		65	49		88	66	44	137	103	68	
	L/360	12			15	11		19	14		26	19	13	14	10		18	13		22	16	11	30	22	15	
21	Strength	29			52	39		70	52		107	80	53	33			59	44		80	60		124	93	62	
	L/360	10			13	10		16	12		22	16	11	12			15	11		19	14		26	19	13	
22	Strength				47			64	48		98	73		30			54	40		73	55		113	85	56	
	L/360				11			14	10		19	14		10			13	10		16	12		22	17	11	
23	Strength				43			58			89	67					49			67	50		104	78	52	
	L/360				10			12			17	12					11			14	11		20	15	10	
24	Strength							54			82	61					45			61			95	71		
	L/360							11			15	11					10			12			17	13		
25	Strength										76	57								56			88	66		
	L/360										13	10								11			15	11		
26	Strength										70									52			81	61		
	L/360										11									10			13	10		
27	Strength										65												75			
	L/360										10												12			
28	Strength																						70			
	L/360																						11			
29	Strength																						65			
	L/360																						10			
30	Strength																									
	L/360																									

**NOTES:**

\* Web stiffeners required at ends of members.

1) Values greater than 500 psf and less than 10 psf are not shown.

2) For other deflection limits such as L/480, multiply the L/360 uniform specified loads by the following factor:

Deflection limit	Factor
L/480	360/480 = 0.75











FLOOR JOIST LOAD TABLE

Uniformly Distributed Single Span Loads (psf) with  $K_{\phi} = 0$

Strength - Factored Loads L/360 - Specified Loads

Table with columns: Section, Design Criteria, Spacing (in.), and Strength/L/360 values for various joist sections (1000S250-54 to 1000S300-97) across 32 different span lengths.

NOTES:

\* Web stiffeners required at ends of members.

- 1) Values greater than 500 psf and less than 10 psf are not shown.
2) For other deflection limits such as L/480, multiply the L/360 uniform specified loads by the following factor:
Deflection limit Factor
L/480 360/480 = 0.75

Bailey Metal Products, Doss Metal Products, DCM Metal Corp., EB Metal Inc., Imperial Building Products, Manugypse, Groupe UP, Trebor Building Products Ltd.





## Header Load Tables

### Table Notes

- 1 Values are for unpunched members and are given in pounds per linear foot.
- 2 Headers are made from two "boxed" or "back-to-back" C-section members.
- 3 Factored moment, shear and web crippling resistances are based on twice the resistance of a single member. The moment of inertia for deflection is based on twice the value of a single member.
- 4 Web crippling check is based on 1" of bearing at end supports.
- 5 Members are assumed to be adequately braced for bending.
- 6 Header loads are for simply supported members subjected to uniform bending loads only.



Back-to-Back Header



Boxed Header







## UNIFORM DISTRIBUTED HEADER LOADS (PLF)

Strength - Factored Loads

L/360 - Specified Loads

Section	Design Criteria	F <sub>y</sub> (ksi)	Span (ft)																
			4	5	6	7	8	9	10	11	12	13	14	15	16	17	18	19	20
1000S162-54	Strength	50	2093e	1675e	1395e	1196e	1046e	930e	805e	665e	559e	476e	410e	357e	314e	278e	248e	223e	201e
	L/360		12514	6407	3707	2335	1564	1098	800	601	463	364	291	237	195	163	137	116	100
1000S162-68	Strength	50	4217e	3374e	2811e	2295e	1757e	1388e	1124e	929e	780e	665e	573e	499e	439e	389e	347e	311e	281e
	L/360		16022	8203	4747	2989	2002	1406	1025	770	593	466	373	303	250	208	175	149	128
1000S162-97	Strength	50	11553e	7394e	5135e	3772e	2888e	2282e	1848e	1527e	1283e	1093e	943e	821e	722e	639e	570e	512e	462e
	L/360		22828	11687	6763	4259	2853	2004	1460	1097	845	664	532	432	356	297	250	213	182
1000S200-54	Strength	50	2093e	1675e	1395e	1196e	1046e	930e	837e	761e	645e	550e	474e	413e	363e	321e	286e	257e	232e
	L/360		14317	7330	4242	2671	1789	1256	916	688	530	417	333	271	223	186	157	133	114
1000S200-68	Strength	50	4217e	3374e	2811e	2410e	2010e	1588e	1286e	1063e	893e	761e	656e	571e	502e	445e	397e	356e	321e
	L/360		18276	9357	5415	3410	2284	1604	1169	878	676	532	426	346	285	238	200	170	146
1000S200-97	Strength	50	12436e	8365e	5809e	4268e	3267e	2581e	2091e	1728e	1452e	1237e	1067e	929e	816e	723e	645e	579e	522e
	L/360		26015	13320	7708	4854	3251	2283	1665	1250	963	757	606	493	406	338	285	242	208
1000S250-54	Strength	50	2093e	1675e	1395e	1196e	1046e	930e	837e	761e	680e	580e	500e	435e	382e	339e	302e	271e	245e
	L/360		16377	8385	4852	3055	2047	1437	1048	787	606	477	381	310	255	213	179	152	131
1000S250-68	Strength	50	4217e	3374e	2811e	2410e	2108e	1677e	1359e	1123e	943e	804e	693e	604e	530e	470e	419e	376e	339e
	L/360		20902	10702	6193	3900	2612	1835	1337	1005	774	608	487	396	326	272	229	195	167
1000S250-97	Strength	50	12436e	8883e	6169e	4532e	3470e	2741e	2220e	1835e	1542e	1314e	1133e	987e	867e	768e	685e	615e	555e
	L/360		29367	15036	8701	5479	3670	2578	1879	1412	1087	855	684	556	458	382	322	274	234
1000S300-54	Strength	50	2093e	1675e	1395e	1196e	1046e	930e	837e	761e	697e	597e	515e	449e	394e	349e	311e	279e	252e
	L/360		17180	8796	5090	3205	2147	1508	1099	826	636	500	400	325	268	223	188	160	137
1000S300-68	Strength	50	4217e	3374e	2811e	2410e	2108e	1733e	1403e	1160e	974e	830e	716e	623e	548e	485e	433e	388e	350e
	L/360		22342	11439	6620	4168	2792	1961	1429	1074	827	650	521	423	349	291	245	208	178
1000S300-97	Strength	50	12436e	9229e	6409e	4709e	3605e	2848e	2307e	1906e	1602e	1365e	1177e	1025e	901e	798e	712e	639e	576e
	L/360		32128	16449	9519	5994	4016	2820	2056	1544	1189	935	749	609	502	418	352	299	257

NOTE: "e" web stiffeners required at ends.

## UNIFORM DISTRIBUTED HEADER LOADS (PLF)

### Strength - Factored Loads

### L/360 - Specified Loads

Section	Design Criteria	F <sub>y</sub> (ksi)	Span (ft)																
			4	5	6	7	8	9	10	11	12	13	14	15	16	17	18	19	20
1200S162-68	Strength	50	3493e	2794e	2328e	1996e	1746e	1552e	1319e	1090e	916e	780e	673e	586e	515e	456e	407e	365e	329e
	L/360		24535	12561	7269	4577	3066	2153	1570	1179	908	714	572	465	383	319	269	228	196
1200S162-97	Strength	50	10271e	8217e	6172e	4535e	3472e	2743e	2222e	1836e	1543e	1314e	1133e	987e	868e	768e	685e	615e	555e
	L/360		35772	18315	10599	6674	4471	3140	2289	1720	1324	1042	834	678	558	465	392	333	286
1200S200-68	Strength	50	3493e	2794e	2328e	1996e	1746e	1552e	1397e	1262e	1060e	903e	779e	678e	596e	528e	471e	423e	381e
	L/360		27834	14251	8247	5193	3479	2443	1781	1338	1030	810	649	527	434	362	305	259	222
1200S200-97	Strength	50	10271e	8217e	6847e	5168e	3957e	3126e	2532e	2093e	1758e	1498e	1292e	1125e	989e	876e	781e	701e	633e
	L/360		40422	20696	11976	7542	5052	3548	2587	1943	1497	1177	942	766	631	526	443	377	323
1200S250-68	Strength	50	3493e	2794e	2328e	1996e	1746e	1552e	1397e	1270e	1130e	962e	830e	723e	635e	563e	502e	450e	406e
	L/360		30747	15742	9110	5737	3843	2699	1967	1478	1138	895	717	583	480	400	337	286	245
1200S250-97	Strength	50	10271e	8217e	6847e	5514e	4221e	3335e	2701e	2233e	1876e	1598e	1378e	1200e	1055e	934e	833e	748e	675e
	L/360		45269	23177	13413	8446	5658	3974	2897	2176	1676	1318	1055	858	707	589	496	422	362
1200S300-68	Strength	50	3493e	2794e	2328e	1996e	1746e	1552e	1397e	1270e	1164e	1000e	862e	751e	660e	585e	521e	468e	422e
	L/360		34576	17703	10244	6451	4322	3035	2212	1662	1280	1007	806	655	540	450	379	322	276
1200S300-97	Strength	50	10271e	8217e	6847e	5744e	4397e	3474e	2814e	2326e	1954e	1665e	1436e	1250e	1099e	973e	868e	779e	703e
	L/360		49728	25460	14734	9278	6216	4365	3182	2391	1841	1448	1159	942	777	647	545	464	397

NOTE: "e" web stiffeners required at ends.

## UNIFORM DISTRIBUTED HEADER LOADS (PLF)

### Strength - Factored Loads

### L/360 - Specified Loads


Section	Design Criteria	F <sub>y</sub> (ksi)	Span (ft)																
			4	5	6	7	8	9	10	11	12	13	14	15	16	17	18	19	20
1400S162-68	Strength	50	2981e	2384e	1987e	1703e	1490e	1324e	1192e	1084e	993e	879e	758e	660e	580e	514e	459e	411e	371e
	L/360		35103	17972	10400	6549	4387	3081	2246	1687	1300	1022	818	665	548	457	385	327	280
1400S162-97	Strength	50	8748e	6999e	5832e	4999e	3990e	3153e	2554e	2110e	1773e	1511e	1303e	1135e	997e	883e	788e	707e	638e
	L/360		51894	26569	15376	9682	6486	4555	3321	2495	1922	1511	1210	984	810	676	569	484	415
1400S200-68	Strength	50	2981e	2384e	1987e	1703e	1490e	1324e	1192e	1084e	993e	917e	851e	772e	678e	601e	536e	481e	434e
	L/360		39661	20306	11751	7400	4957	3481	2538	1907	1468	1155	925	752	619	516	435	370	317
1400S200-97	Strength	50	8748e	6999e	5832e	4999e	4374e	3621e	2933e	2424e	2037e	1735e	1496e	1303e	1145e	1015e	905e	812e	733e
	L/360		58294	29846	17272	10877	7286	5117	3730	2803	2159	1698	1359	1105	910	759	639	543	466
1400S250-68	Strength	50	2981e	2384e	1987e	1703e	1490e	1324e	1192e	1084e	993e	917e	851e	794e	730e	647e	577e	518e	467e
	L/360		43602	22324	12919	8135	5450	3827	2790	2096	1614	1270	1016	826	681	567	478	406	348
1400S250-97	Strength	50	8748e	6999e	5832e	4999e	4374e	3888e	3151e	2604e	2188e	1864e	1608e	1400e	1231e	1090e	972e	873e	787e
	L/360		64926	33242	19237	12114	8115	5699	4155	3121	2404	1891	1514	1231	1014	845	712	605	519
1400S300-68	Strength	50	2981e	2384e	1987e	1703e	1490e	1324e	1192e	1084e	993e	917e	851e	794e	745e	677e	604e	542e	489e
	L/360		46013	23558	13633	8585	5751	4039	2944	2212	1704	1340	1073	872	718	599	504	429	368
1400S300-97	Strength	50	8748e	6999e	5832e	4999e	4374e	3888e	3301e	2728e	2292e	1953e	1684e	1467e	1289e	1142e	1018e	914e	825e
	L/360		70147	35915	20784	13088	8768	6158	4489	3372	2598	2043	1636	1330	1096	913	769	654	561

NOTE: "e" web stiffeners required at ends.

## Web Crippling Data

### Table Notes

- 1 The factored web crippling data is based on Section G5 of S136-16.
- 2 For single web members, the coefficients and resistance factors are based on Table G5-2. If  $N/h > 2$ , then  $N$  can not be greater than  $2h$ . If  $N/t > 210$ , then  $N$  can not be greater than  $210t$ .
- 3 For back-to-back members, the coefficients and resistance factors are based on Table G5-1. If  $N/h > 1$ , then  $N$  can not be greater than  $h$ . If  $N/t > 210$ , then  $N$  can not be greater than  $210t$ .
- 4 Coefficients and resistance factors are based on members "Fastened to Support", except for back-to-back members under two-flange loading, the coefficients and resistance factors "Unfastened to Support" are used.
- 5 For back-to-back members, the distance between web connectors and flange shall be kept to a minimum.
- 6 Calculations are based on unperforated webs. Resistance reductions for end and interior one flange loading near punchouts can be calculated based on Section G6 of S136-16.

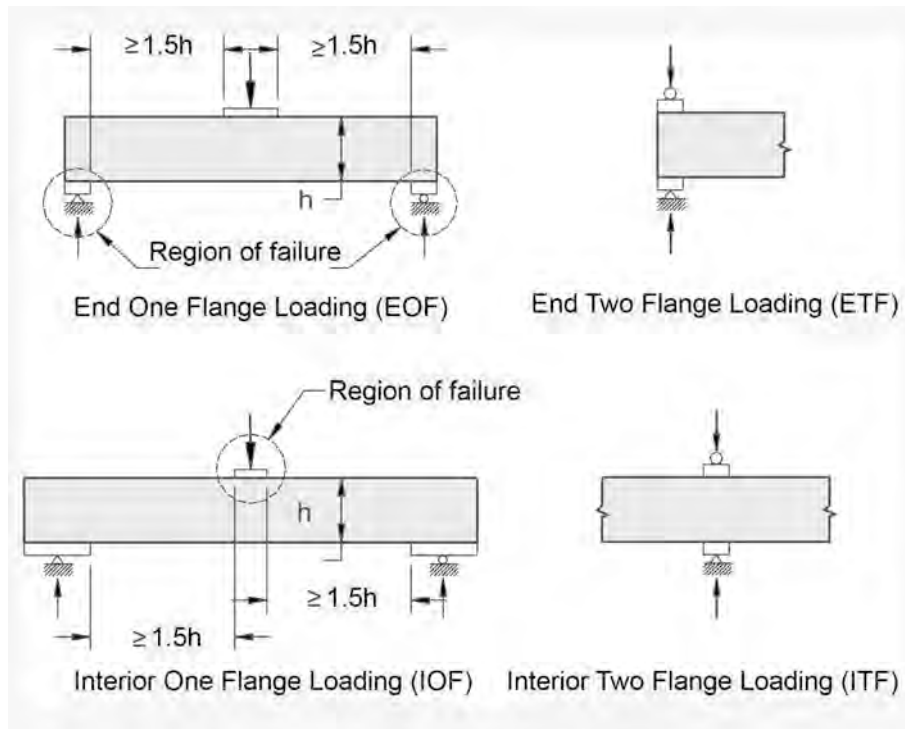

**FACTORED WEB CRIPPLING DATA FOR SINGLE WEB MEMBERS (Imperial)**

Section Depth (in.)	Designation Thickness (mil)	Base Design Thickness (in.)	F <sub>y</sub> (ksi)	h/t	FACTORED WEB CRIPPLING DATA (lb)							
					EOF		IOF		ETF		ITF	
					P <sub>eo1</sub>	P <sub>eo2</sub>	P <sub>io1</sub>	P <sub>io2</sub>	P <sub>et1</sub>	P <sub>et2</sub>	P <sub>it1</sub>	P <sub>it2</sub>
3.625	33	0.0346	33	98.3	75.2	26.3	244	34.1	103	12.3	349	28.0
	43	0.0451	33	75.2	137	48.0	453	63.5	198	23.8	644	51.5
	54	0.0566	50	59.0	337	118	1105	155	513	61.6	1606	129
	68	0.0713	50	45.8	546	191	1770	248	871	105	2644	212
	97	0.1017	50	30.6	1143	400	3649	511	1927	231	5639	451
4.00	33	0.0346	33	109	74.2	26.0	242	33.9	97.6	11.7	341	27.3
	43	0.0451	33	83.5	136	47.5	451	63.1	191	22.9	631	50.5
	54	0.0566	50	65.7	334	117	1100	154	497	59.6	1579	126
	68	0.0713	50	51.1	542	190	1763	247	847	102	2604	208
	97	0.1017	50	34.3	1135	397	3637	509	1886	226	5571	446
6.00	33	0.0346	33	167	69.6	24.4	235	33.0	74.3	8.90	302	24.2
	43	0.0451	33	128	128	44.9	440	61.6	155	18.6	572	45.7
	54	0.0566	50	101	318	111	1076	151	421	50.5	1452	116
	68	0.0713	50	79.2	519	182	1730	242	739	88.7	2423	194
	97	0.1017	50	54.0	1097	384	3579	501	1698	204	5256	421
8.00	43	0.0451	33	172	122	42.8	431	60.4	126	15.1	522	41.8
	54	0.0566	50	136	305	107	1057	148	357	42.9	1345	108
	68	0.0713	50	107	501	175	1702	238	649	77.8	2272	182
	97	0.1017	50	73.7	1065	373	3532	494	1543	185	4996	400
10.0	54	0.0566	50	172	294	103	1040	146	302	36.2	1252	100
	68	0.0713	50	135	485	170	1678	235	570	68.4	2140	171
	97	0.1017	50	93.3	1037	363	3490	489	1407	169	4769	382
12.0	68	0.0713	50	163	470	165	1656	232	499	59.8	2020	162
	97	0.1017	50	113	1012	354	3453	483	1285	154	4564	365
14.0	68	0.0713	50	191	457	160	1636	229	433	52.0	1911	153
	97	0.1017	50	133	989	346	3418	479	1173	141	4377	350

**NOTES:**

1. Factored end one flange web crippling resistance (EOF),  $P_{reo} = P_{eo1} + P_{eo2}[N/t]^{1/2}$
2. Factored interior one flange web crippling resistance (IOF),  $P_{rio} = P_{io1} + P_{io2}[N/t]^{1/2}$
3. Factored end two flange web crippling resistance (ETF),  $P_{ret} = P_{et1} + P_{et2}[N/t]^{1/2}$
4. Factored interior two flange web crippling resistance (ITF),  $P_{rit} = P_{it1} + P_{it2}[N/t]^{1/2}$

**FACTORED WEB CRIPPLING DATA FOR BACK TO BACK WEB MEMBERS (Imperial)**

Section Depth (in.)	Designation Thickness (mil)	Base Design Thickness (in.)	F <sub>y</sub> (ksi)	h/t	FACTORED WEB CRIPPLING DATA (lb)							
					EOF		IOF		ETF		ITF	
					P <sub>eo1</sub>	P <sub>eo2</sub>	P <sub>io1</sub>	P <sub>io2</sub>	P <sub>et1</sub>	P <sub>et2</sub>	P <sub>it1</sub>	P <sub>it2</sub>
<b>3.625</b>	33	0.0346	33	98.3	372	104	899	98.9	384	30.7	1019	81.5
	43	0.0451	33	75.2	658	184	1609	177	723	57.9	1951	156
	54	0.0566	50	59.0	1580	443	3870	426	1836	147	4964	397
	68	0.0713	50	45.8	2510	703	6147	676	3067	245	8293	663
	97	0.1017	50	30.6	5113	1432	12522	1377	6664	533	18014	1441
<b>4.00</b>	33	0.0346	33	109	372	104	898	98.8	371	29.6	983	78.7
	43	0.0451	33	83.5	658	184	1608	177	703	56.2	1895	152
	54	0.0566	50	65.7	1580	442	3868	426	1792	143	4843	388
	68	0.0713	50	51.1	2509	703	6145	676	3004	240	8121	650
	97	0.1017	50	34.3	5112	1431	12517	1377	6553	524	17715	1417
<b>6.00</b>	33	0.0346	33	167	371	104	896	98.6	308	24.6	816	65.3
	43	0.0451	33	128	656	184	1605	177	606	48.5	1636	131
	54	0.0566	50	101	1577	441	3861	425	1585	127	4286	343
	68	0.0713	50	79.2	2505	701	6134	675	2710	217	7325	586
	97	0.1017	50	54.0	5104	1429	12499	1375	6043	483	16337	1307
<b>8.00</b>	43	0.0451	33	172	655	183	1602	176	526	42.1	1419	114
	54	0.0566	50	136	1574	441	3854	424	1413	113	3819	306
	68	0.0713	50	107	2501	700	6125	674	2465	197	6663	533
	97	0.1017	50	73.7	5098	1427	12483	1373	5620	450	15194	1216
<b>10.0</b>	54	0.0566	50	172	1572	440	3849	423	1262	101	3411	273
	68	0.0713	50	135	2498	699	6117	673	2250	180	6082	487
	97	0.1017	50	93.3	5092	1426	12470	1372	5251	420	14197	1136
<b>12.0</b>	68	0.0713	50	163	2495	699	6110	672	2056	165	5559	445
	97	0.1017	50	113	5087	1424	12457	1370	4920	394	13300	1064
<b>14.0</b>	68	0.0713	50	191	2492	698	6103	671	1879	150	5080	406
	97	0.1017	50	133	5083	1423	12446	1369	4616	369	12478	998


**NOTES:**

1. Factored end one flange web crippling resistance (EOF),  $P_{reo} = P_{eo1} + P_{eo2}[N/t]^{1/2}$
2. Factored interior one flange web crippling resistance (IOF),  $P_{rio} = P_{io1} + P_{io2}[N/t]^{1/2}$
3. Factored end two flange web crippling resistance (ETF),  $P_{ret} = P_{et1} + P_{et2}[N/t]^{1/2}$
4. Factored interior two flange web crippling resistance (ITF),  $P_{rit} = P_{it1} + P_{it2}[N/t]^{1/2}$

## S-Section Ceiling Span Tables

### Table Notes

- 1 Values are for simple span conditions.
- 2 For "Unbraced" case, the factored moment resistance is based on Sections F2 and F3 of S136-16 with the unbraced length assumed to be the listed span.
- 3 For "Midspan" braced case, the factored moment resistance is based on Sections F2 and F3 of S136-16 with the unbraced length assumed to be half of the listed span.
- 4 Web crippling check is based on 1" of bearing at end supports.
- 5 Web crippling and shear capacity have not been reduced for punchouts. If web punchouts occur near supports, members must be checked for reduced shear and web crippling in accordance with S136-16.

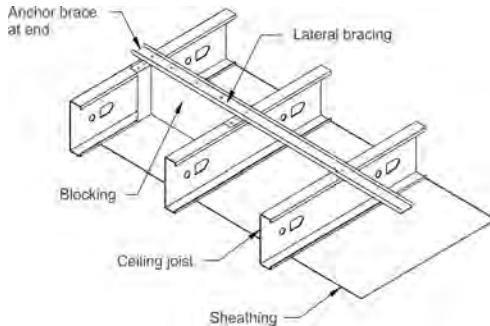

### LIMITING CEILING SPANS (ft) - L/240

Specified dead load		4 psf						6 psf						13 psf					
Stud Designation	F <sub>y</sub> (ksi)	Lateral Support of Compression Flange Unsupported			Midspan			Lateral Support of Compression Flange Unsupported			Midspan			Lateral Support of Compression Flange Unsupported			Midspan		
		Joist Spacing (in.) o.c.			Joist Spacing (in.) o.c.			Joist Spacing (in.) o.c.			Joist Spacing (in.) o.c.			Joist Spacing (in.) o.c.			Joist Spacing (in.) o.c.		
		12	16	24	12	16	24	12	16	24	12	16	24	12	16	24	12	16	24
162S125-18	33	7' 11"	7' 4"	6' 7"	8' 3"	7' 5"	6' 5"	7' 1"	6' 7"	5' 9"	7' 2"	6' 5"	5' 7"	5' 7"	5' 1"	4' 5"	5' 6"	5' 0"	4' 4"
162S125-33	33	10' 0"	9' 2"	8' 2"	10' 3"	9' 4"	8' 1"	8' 11"	8' 2"	7' 1"	8' 11"	8' 1"	7' 1"	6' 11"	6' 3"	5' 6"	6' 11"	6' 3"	5' 6"
250S125-18	33	8' 11"	8' 3"	7' 5"	11' 6"	10' 5"	9' 0"	8' 0"	7' 5"	6' 8"	10' 0"	9' 0"	7' 10"	6' 6"	6' 1"	5' 5" e	7' 7"	6' 11" e	5' 11" e
250S125-33	33	11' 0"	10' 2"	9' 0"	14' 3"	12' 11"	11' 3"	9' 10"	9' 0"	8' 1"	12' 5"	11' 3"	9' 10"	7' 10"	7' 3"	6' 6"	9' 7"	8' 8"	7' 7"
250S125-43	33	12' 5"	11' 5"	10' 1"	15' 6"	14' 0"	12' 3"	11' 0"	10' 1"	8' 11"	13' 6"	12' 3"	10' 9"	8' 9"	8' 0"	7' 2"	10' 5"	9' 6"	8' 3"
362S125-18	33	10' 0"	9' 3"	8' 4"	13' 4"	12' 3"	10' 8"	9' 0"	8' 4"	7' 6"	11' 9"	10' 8"	9' 2" e	7' 4"	6' 10" e	6' 2" e	8' 11" e	7' 11" e	6' 7" e
362S125-33	33	12' 1"	11' 2"	10' 0"	16' 11"	15' 7"	13' 11"	10' 9"	10' 0"	8' 11"	15' 1"	13' 11"	12' 6"	8' 9"	8' 1"	7' 3"	12' 2"	11' 2"	9' 7"
362S125-43	33	13' 6"	12' 4"	11' 0"	18' 8"	17' 2"	15' 4"	11' 11"	11' 0"	9' 9"	16' 8"	15' 4"	13' 9"	9' 7"	8' 10"	7' 10"	13' 5"	12' 4"	10' 10"
362S162-33	33	15' 6"	14' 4"	12' 10"	20' 9"	18' 10"	16' 6"	13' 10"	12' 10"	11' 6"	18' 2"	16' 6"	14' 5"	11' 3"	10' 5"	9' 5"	14' 0"	12' 9"	11' 4"
362S162-43	33	17' 1"	15' 9"	14' 0"	22' 7"	20' 6"	17' 11"	15' 2"	14' 0"	12' 6"	19' 9"	17' 11"	15' 8"	12' 3"	11' 4"	10' 2"	15' 3"	13' 10"	12' 1"
400S125-18	33	10' 3"	9' 6"	8' 7"	13' 9"	12' 7"	11' 1"	9' 3"	8' 7"	7' 9"	12' 2"	11' 1"	9' 7" e	7' 7"	7' 0" e	6' 4" e	9' 3" e	8' 3" e	6' 11" e
400S125-33	33	12' 5"	11' 5"	10' 3"	17' 5"	16' 1"	14' 4"	11' 1"	10' 3"	9' 2"	15' 6"	14' 4"	12' 10"	9' 0"	8' 4"	7' 5" e	12' 6"	11' 6"	10' 10"
400S125-43	33	13' 9"	12' 8"	11' 3"	19' 2"	17' 8"	15' 9"	12' 3"	11' 3"	10' 0"	17' 1"	15' 9"	14' 1"	9' 10"	9' 1"	8' 1"	13' 9"	12' 8"	11' 2"
400S162-33	33	15' 10"	14' 8"	13' 2"	22' 5"	20' 4"	17' 9"	14' 3"	13' 2"	11' 10"	19' 7"	17' 9"	15' 6"	11' 7"	10' 9"	9' 8"	15' 1"	13' 9"	12' 0"
400S162-43	33	17' 6"	16' 1"	14' 4"	24' 5"	22' 2"	19' 4"	15' 7"	14' 4"	12' 10"	21' 4"	19' 4"	16' 11"	12' 7"	11' 7"	10' 5"	16' 6"	14' 11"	13' 1"
600S125-33	33	13' 10"	12' 9"	11' 6"	19' 10"	18' 5"	16' 6"	12' 5"	11' 6"	10' 4"	17' 10"	16' 6"	14' 10"	10' 1"	9' 4"	8' 5"	14' 6"	13' 5"	12' 0"
600S125-43	33	15' 2"	14' 0"	12' 6"	21' 6"	19' 10"	17' 10"	13' 6"	12' 6"	11' 2"	19' 3"	17' 10"	16' 0"	10' 11"	10' 1"	9' 1"	15' 8"	14' 6"	13' 1"
600S162-33	33	17' 8"	16' 5"	14' 9"	25' 6"	23' 8"	21' 4"	15' 11"	14' 9"	13' 3"	23' 0"	21' 4"	19' 3"	13' 0"	12' 1"	10' 10"	18' 10"	17' 6"	15' 7" e
600S162-43	33	19' 4"	17' 10"	16' 0"	27' 6"	25' 6"	22' 11"	17' 3"	16' 0"	14' 4"	24' 9"	22' 11"	20' 8"	14' 0"	13' 0"	11' 8"	20' 3"	18' 9"	16' 10"


NOTE: "e" indicates that web stiffeners are required at ends.

### LIMITING CEILING SPANS (ft) - L/360

Specified dead load		4 psf						6 psf						13 psf					
Stud Designation	F <sub>y</sub> (ksi)	Lateral Support of Compression Flange Unsupported			Midspan			Lateral Support of Compression Flange Unsupported			Midspan			Lateral Support of Compression Flange Unsupported			Midspan		
		Joist Spacing (in.) o.c.			Joist Spacing (in.) o.c.			Joist Spacing (in.) o.c.			Joist Spacing (in.) o.c.			Joist Spacing (in.) o.c.			Joist Spacing (in.) o.c.		
		12	16	24	12	16	24	12	16	24	12	16	24	12	16	24	12	16	24
162S125-18	33	7' 5"	6' 8"	5' 10"	7' 2"	6' 6"	5' 8"	6' 5"	5' 10"	5' 0"	6' 3"	5' 8"	4' 11"	4' 11"	4' 5"	3' 10"	4' 9"	4' 4"	3' 9"
162S125-33	33	9' 0"	8' 2"	7' 1"	9' 0"	8' 1"	7' 1"	7' 10"	7' 1"	6' 3"	7' 10"	7' 1"	6' 2"	6' 0"	5' 6"	4' 9"	6' 0"	5' 6"	4' 9"
250S125-18	33	8' 11"	8' 3"	7' 5"	10' 1"	9' 1"	7' 10"	8' 0"	7' 5"	6' 8"	8' 9"	7' 10"	6' 10"	6' 6"	6' 1"	5' 4" e	6' 8"	6' 0"	5' 3" e
250S125-33	33	11' 0"	10' 2"	9' 0"	12' 5"	11' 3"	9' 10"	9' 10"	9' 0"	8' 1"	10' 10"	9' 10"	8' 7"	7' 10"	7' 3"	6' 6"	8' 4"	7' 7"	6' 7"
250S125-43	33	12' 5"	11' 5"	10' 1"	13' 6"	12' 3"	10' 9"	11' 0"	10' 1"	8' 11"	11' 9"	10' 9"	9' 4"	8' 9"	8' 0"	7' 2"	9' 1"	8' 3"	7' 3"
362S125-18	33	10' 0"	9' 3"	8' 4"	13' 4"	12' 3"	10' 7"	9' 0"	8' 4"	7' 6"	11' 8"	10' 7"	9' 2" e	7' 4"	6' 10" e	6' 2" e	8' 11" e	7' 11" e	6' 7" e
362S125-33	33	12' 1"	11' 2"	10' 0"	16' 7"	15' 1"	13' 2"	10' 9"	10' 0"	8' 11"	14' 6"	13' 2"	11' 6"	8' 9"	8' 1"	7' 3"	11' 2"	10' 1"	8' 10"
362S125-43	33	13' 6"	12' 4"	11' 0"	18' 0"	16' 4"	14' 4"	11' 11"	11' 0"	9' 9"	15' 9"	14' 4"	12' 6"	9' 7"	8' 10"	7' 10"	12' 2"	11' 0"	9' 8"
362S162-33	33	15' 6"	14' 4"	12' 10"	18' 2"	16' 6"	14' 5"	13' 10"	12' 10"	11' 6"	15' 10"	14' 5"	12' 7"	11' 3"	10' 5"	9' 5"	12' 3"	11' 1"	9' 8"
362S162-43	33	17' 1"	15' 9"	14' 0"	19' 9"	17' 11"	15' 8"	15' 2"	14' 0"	12' 6"	17' 3"	15' 8"	13' 8"	12' 3"	11' 4"	10' 2"	13' 4"	12' 1"	10' 7"
400S125-18	33	10' 3"	9' 6"	8' 7"	13' 9"	12' 7"	11' 1"	9' 3"	8' 7"	7' 9"	12' 2"	11' 1"	9' 7" e	7' 7"	7' 0" e	6' 4" e	9' 3" e	8' 3" e	6' 11" e
400S125-33	33	12' 5"	11' 5"	10' 3"	17' 5"	16' 1"	14' 3"	11' 1"	10' 3"	9' 2"	15' 6"	14' 3"	12' 5"	9' 0"	8' 4"	7' 5" e	12' 1"	10' 11"	9' 6"
400S125-43	33	13' 9"	12' 8"	11' 3"	19' 2"	17' 8"	15' 5"	12' 3"	11' 3"	10' 0"	17' 0"	15' 5"	13' 6"	9' 10"	9' 1"	8' 1"	13' 2"	11' 11"	10' 5"
400S162-33	33	15' 10"	14' 8"	13' 2"	19' 7"	17' 9"	15' 6"	14' 3"	13' 2"	11' 10"	17' 1"	15' 6"	13' 7"	11' 7"	10' 9"	9' 8"	13' 2"	12' 0"	10' 6"
400S162-43	33	17' 6"	16' 1"	14' 4"	21' 4"	19' 4"	16' 11"	15' 7"	14' 4"	12' 10"	18' 7"	16' 11"	14' 9"	12' 7"	11' 7"	10' 5"	14' 4"	13' 1"	11' 5"
600S125-33	33	13' 10"	12' 9"	11' 6"	19' 10"	18' 5"	16' 6"	12' 5"	11' 6"	10' 4"	17' 10"	16' 6"	14' 10"	10' 1"	9' 4"	8' 5"	14' 6"	13' 5"	12' 0"
600S125-43	33	15' 2"	14' 0"	12' 6"	21' 6"	19' 10"	17' 10"	13' 6"	12' 6"	11' 2"	19' 3"	17' 10"	16' 0"	10' 11"	10' 1"	9' 1"	15' 8"	14' 6"	13' 1"
600S162-33	33	17' 8"	16' 5"	14' 9"	25' 6"	23' 8"	21' 4"	15' 11"	14' 9"	13' 3"	23' 0"	21' 4"	18' 8"	13' 0"	12' 1"	10' 10"	18' 2"	16' 6"	14' 5" e
600S162-43	33	19' 4"	17' 10"	16' 0"	27' 6"	25' 6"	22' 11"	17' 3"	16' 0"	14' 4"	24' 9"	22' 11"	20' 4"	14' 0"	13' 0"	11' 8"	19' 9"	18' 0"	15' 8"

NOTE: "e" indicates that web stiffeners are required at ends.

## U-Channel Section Properties

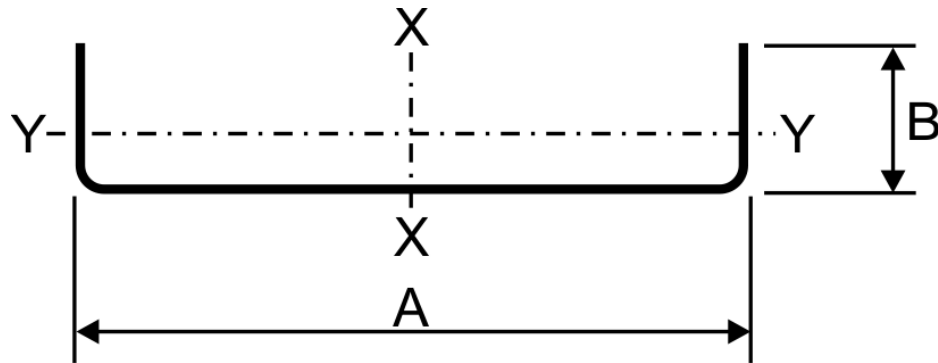

Note: Inside bend radius taken as 3/32"

Section Designation	Base Design Thickness (in.)	Depth A (in.)	Flange B (in.)	F <sub>y</sub> (ksi)	GROSS							EFFECTIVE		
					Weight (lb/ft)	Area (in. <sup>2</sup> )	I <sub>x</sub> (in. <sup>4</sup> )	r <sub>x</sub> (in.)	I <sub>y</sub> (in. <sup>4</sup> )	r <sub>y</sub> (in.)	V <sub>rg</sub> (kip)	I <sub>xd</sub> (in. <sup>4</sup> )	S <sub>xe</sub> (in. <sup>3</sup> )	M <sub>rx</sub> (k-in.)
75U50-54	0.0566	0.75	0.50	33	0.296	0.0871	0.00726	0.289	0.00211	0.156	0.419	0.00726	0.0194	0.687
75U50-54	0.0566	0.75	0.50	50	0.296	0.0871	0.00726	0.289	0.00211	0.156	0.634	0.00726	0.0194	1.02
150U50-43	0.0451	1.50	0.50	33	0.357	0.105	0.0324	0.555	0.00226	0.147	0.905	0.0324	0.0431	1.49
150U50-43	0.0451	1.50	0.50	50	0.357	0.105	0.0324	0.555	0.00226	0.147	1.37	0.0324	0.0431	2.21
150U50-54	0.0566	1.50	0.50	33	0.441	0.130	0.0390	0.549	0.00272	0.145	1.09	0.0390	0.0520	1.85
150U50-54	0.0566	1.50	0.50	50	0.441	0.130	0.0390	0.549	0.00272	0.145	1.65	0.0390	0.0520	2.73
150U75-54	0.0566	1.50	0.75	33	0.537	0.158	0.0537	0.583	0.00865	0.234	1.09	0.0537	0.0716	2.41
150U75-54	0.0566	1.50	0.75	50	0.537	0.158	0.0537	0.583	0.00865	0.234	1.65	0.0537	0.0705	3.17
200U50-54	0.0566	2.00	0.50	33	0.158	0.537	0.0796	0.710	0.0029	0.137	1.54	0.0796	0.0796	2.83
250U50-54	0.0566	2.50	0.50	33	0.186	0.634	0.140	0.867	0.00310	0.129	1.99	0.140	0.112	3.98

NOTE: Cold work of forming is applied when applicable.

## U-Channel Ceiling Span Tables

### Table Notes

- 1 Multiple span indicates two or more equal spans continuous over interior supports.
- 2 Compression flanges assumed unbraced.
- 3 Web crippling based on 3/4" bearing at end and interior supports.

### Limiting Ceiling Spans of U-Channels (ft) - L/240

Specified dead loads			4 psf					6 psf					13 psf					15 psf				
Section Designation	F <sub>y</sub> (ksi)	Span Type	Spacing (in.) o.c.					Spacing (in.) o.c.					Spacing (in.) o.c.					Spacing (in.) o.c.				
			24	36	48	60	72	24	36	48	60	72	24	36	48	60	72	24	36	48	60	72
75U050-54	33	Single	3' 10"	3' 4"	3' 1"	2' 10"	2' 8"	3' 4"	2' 11"	2' 8"	2' 6"	2' 4"	2' 7"	2' 3"	2' 1"	1' 11"	1' 9"	2' 6"	2' 2"	1' 11"	1' 10"	1' 8"
	33	Multiple	4' 9"	4' 2"	3' 9"	3' 6"	3' 4"	4' 2"	3' 8"	3' 4"	3' 1"	2' 11"	3' 3"	2' 10"	2' 6"	2' 4"	2' 2"	3' 1"	2' 8"	2' 5"	2' 2"	2' 0"
150U050-54	33	Single	5' 11"	5' 2"	4' 8"	4' 4"	4' 1"	5' 2"	4' 6"	4' 1"	3' 9"	3' 7"	4' 0"	3' 6"	3' 2"	2' 11"	2' 9"	3' 9"	3' 4"	3' 0"	2' 10"	2' 8"
	33	Multiple	7' 6"	6' 7"	6' 0"	5' 7"	5' 3"	6' 7"	5' 9"	5' 3"	4' 10"	4' 7"	5' 1"	4' 5"	4' 0"	3' 9"	3' 6"	4' 10"	4' 3"	3' 10"	3' 7"	3' 3"
200U050-54	33	Single	6' 2"	5' 5"	4' 11"	4' 7"	4' 4"	5' 5"	4' 9"	4' 4"	4' 0"	3' 9"	4' 2"	3' 8"	3' 4"	3' 1"	2' 11"	4' 0"	3' 6"	3' 2"	3' 0"	2' 10"
	33	Multiple	7' 11"	6' 11"	6' 3"	5' 10"	5' 6"	6' 11"	6' 0"	5' 6"	5' 1"	4' 10"	5' 4"	4' 8"	4' 3"	4' 0"	3' 9"	5' 1"	4' 6"	4' 1"	3' 9"	3' 7"
250U050-54	33	Single	6' 5"	5' 7"	5' 1"	4' 9"	4' 6"	5' 7"	4' 11"	4' 6"	4' 2"	3' 11"	4' 4"	3' 10"	3' 6"	3' 3"	3' 1"	4' 2"	3' 8"	3' 4"	3' 1"	2' 11"
	33	Multiple	8' 2"	7' 2"	6' 6"	6' 1"	5' 9"	7' 2"	6' 3"	5' 9"	5' 4"	5' 0"	5' 7"	4' 10"	4' 5"	4' 2"	3' 11"	5' 4"	4' 8"	4' 3"	3' 11"	3' 9"

### Limiting Ceiling Spans of U-Channels (ft) - L/360


Specified dead loads			4 psf					6 psf					13 psf					15 psf				
Section Designation	F <sub>y</sub> (ksi)	Span Type	Spacing (in.) o.c.					Spacing (in.) o.c.					Spacing (in.) o.c.					Spacing (in.) o.c.				
			24	36	48	60	72	24	36	48	60	72	24	36	48	60	72	24	36	48	60	72
75U050-54	33	Single	3' 4"	2' 11"	2' 8"	2' 6"	2' 4"	2' 11"	2' 7"	2' 4"	2' 2"	2' 0"	2' 3"	2' 0"	1' 9"	1' 8"	1' 7"	2' 2"	1' 11"	1' 8"	1' 7"	1' 6"
	33	Multiple	4' 2"	3' 8"	3' 4"	3' 1"	2' 11"	3' 8"	3' 2"	2' 11"	2' 8"	2' 6"	2' 10"	2' 5"	2' 3"	2' 1"	1' 11"	2' 8"	2' 4"	2' 1"	2' 0"	1' 10"
150U050-54	33	Single	5' 11"	5' 2"	4' 8"	4' 4"	4' 1"	5' 2"	4' 6"	4' 1"	3' 9"	3' 7"	4' 0"	3' 6"	3' 2"	2' 11"	2' 9"	3' 9"	3' 4"	3' 0"	2' 9"	2' 8"
	33	Multiple	7' 4"	6' 5"	5' 10"	5' 5"	5' 1"	6' 5"	5' 7"	5' 1"	4' 9"	4' 5"	4' 11"	4' 4"	3' 11"	3' 8"	3' 5"	4' 9"	4' 1"	3' 9"	3' 6"	3' 3"
200U050-54	33	Single	6' 2"	5' 5"	4' 11"	4' 7"	4' 4"	5' 5"	4' 9"	4' 4"	4' 0"	3' 9"	4' 2"	3' 8"	3' 4"	3' 1"	2' 11"	4' 0"	3' 6"	3' 2"	3' 0"	2' 10"
	33	Multiple	7' 11"	6' 11"	6' 3"	5' 10"	5' 6"	6' 11"	6' 0"	5' 6"	5' 1"	4' 10"	5' 4"	4' 8"	4' 3"	4' 0"	3' 9"	5' 1"	4' 6"	4' 1"	3' 9"	3' 7"
250U050-54	33	Single	6' 5"	5' 7"	5' 1"	4' 9"	4' 6"	5' 7"	4' 11"	4' 6"	4' 2"	3' 11"	4' 4"	3' 10"	3' 6"	3' 3"	3' 1"	4' 2"	3' 8"	3' 4"	3' 1"	2' 11"
	33	Multiple	8' 2"	7' 2"	6' 6"	6' 1"	5' 9"	7' 2"	6' 3"	5' 9"	5' 4"	5' 0"	5' 7"	4' 10"	4' 5"	4' 2"	3' 11"	5' 4"	4' 8"	4' 3"	3' 11"	3' 9"



## Furring Channel Section Properties

### Table Notes

- 1 If present, hems and offsets in flanges are ignored.
- 2 Effective properties are the minimum for positive and negative bending.

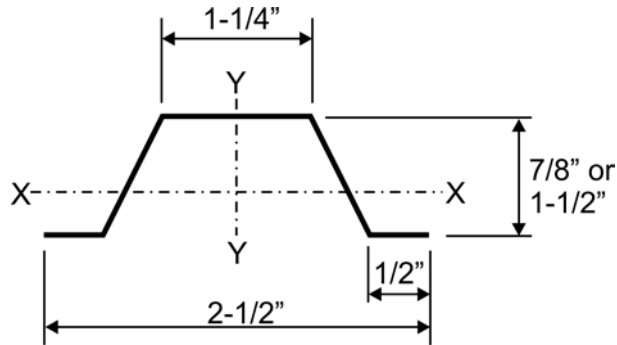

Section Designation	F <sub>y</sub> (ksi)	Base Design Thickness (in.)	Gross						Effective		
			Weight (lb/ft)	Area (in. <sup>2</sup> )	I <sub>x</sub> (in. <sup>4</sup> )	r <sub>x</sub> (in.)	I <sub>y</sub> (in. <sup>4</sup> )	r <sub>y</sub> (in.)	I <sub>xd</sub> (in. <sup>4</sup> )	S <sub>xe</sub> (in. <sup>3</sup> )	M <sub>rx</sub> (k-in.)
087F125-18	33	0.0188	0.245	0.0721	0.00913	0.356	0.0360	0.707	0.00888	0.0162	0.482
087F125-27	33	0.0283	0.366	0.108	0.0133	0.352	0.0535	0.705	0.0133	0.0275	0.816
087F125-30	33	0.0312	0.402	0.118	0.0146	0.351	0.0587	0.705	0.0146	0.0310	0.919
087F125-33	33	0.0346	0.444	0.131	0.0160	0.350	0.0648	0.704	0.0160	0.0343	1.02
087F125-43	33	0.0451	0.573	0.168	0.0201	0.345	0.0832	0.703	0.0201	0.0432	1.28
150F125-18	33	0.0188	0.323	0.0950	0.0315	0.576	0.0466	0.700	0.0308	0.0346	1.03
150F125-27	33	0.0283	0.483	0.142	0.0464	0.572	0.0692	0.698	0.0464	0.0573	1.70
150F125-30	33	0.0312	0.532	0.156	0.0509	0.571	0.0760	0.697	0.0509	0.0644	1.91
150F125-33	33	0.0346	0.588	0.173	0.0560	0.569	0.0838	0.696	0.0560	0.0712	2.11
150F125-43	33	0.0451	0.760	0.224	0.0713	0.565	0.108	0.694	0.0713	0.0907	2.69

## Furring Channel Ceiling Span Tables

### Table Notes

- 1 Single spans are the minimum span based on moment, shear, web crippling, or deflection.
- 2 Multiple spans are for two or more equal continuous spans with span length measured from support to support.
- 3 Web crippling check is based on a bearing length of 1" at end and interior supports.
- 4 Multiple spans are the minimum span based on moment, shear, web crippling, combined bending and shear, combined bending and web crippling, or deflection.

### Limiting Ceiling Spans of Furring Channels (ft) - L/240

Specified dead loads			4 psf			6 psf			13 psf		
Section Designation	F <sub>y</sub> (ksi)	Span Type	Spacing (in.) o.c.			Spacing (in.) o.c.			Spacing (in.) o.c.		
			12	16	24	12	16	24	12	16	24
087F125-18	33	Single	5' 3"	4' 9"	4' 2"	4' 7"	4' 2"	3' 7"	3' 6"	3' 2"	2' 9"
	33	Multiple	6' 5"	5' 10"	5' 1"	5' 8"	5' 1"	4' 6"	4' 4"	3' 10"	3' 1"
087F125-27	33	Single	6' 0"	5' 5"	4' 9"	5' 3"	4' 9"	4' 2"	4' 0"	3' 8"	3' 2"
	33	Multiple	7' 5"	6' 9"	5' 10"	6' 6"	5' 10"	5' 1"	5' 0"	4' 6"	3' 11"
087F125-30	33	Single	6' 2"	5' 7"	4' 11"	5' 4"	4' 11"	4' 3"	4' 2"	3' 9"	3' 3"
	33	Multiple	7' 7"	6' 11"	6' 0"	6' 8"	6' 0"	5' 3"	5' 2"	4' 8"	4' 1"
087F125-33	33	Single	6' 4"	5' 9"	5' 0"	5' 6"	5' 0"	4' 5"	4' 3"	3' 11"	3' 5"
	33	Multiple	7' 10"	7' 2"	6' 3"	6' 10"	6' 3"	5' 5"	5' 3"	4' 10"	4' 2"
087F125-43	33	Single	6' 10"	6' 3"	5' 5"	6' 0"	5' 5"	4' 9"	4' 7"	4' 2"	3' 8"
	33	Multiple	8' 6"	7' 9"	6' 9"	7' 5"	6' 9"	5' 10"	5' 9"	5' 2"	4' 6"
150F125-18	33	Single	7' 11"	7' 2"	6' 3"	6' 11"	6' 3"	5' 6"	5' 4"	4' 10"	4' 3"
	33	Multiple	9' 9"	8' 11"	7' 9"	8' 7"	7' 9"	6' 9"	6' 6"	5' 7"	4' 7"
150F125-27	33	Single	9' 1"	8' 3"	7' 2"	7' 11"	7' 2"	6' 3"	6' 1"	5' 7"	4' 10"
	33	Multiple	11' 3"	10' 2"	8' 11"	9' 10"	8' 11"	7' 9"	7' 7"	6' 11"	5' 10"
150F125-30	33	Single	9' 4"	8' 6"	7' 5"	8' 2"	7' 5"	6' 6"	6' 4"	5' 9"	5' 0"
	33	Multiple	11' 7"	10' 6"	9' 2"	10' 1"	9' 2"	8' 0"	7' 10"	7' 1"	6' 2"
150F125-33	33	Single	9' 8"	8' 9"	7' 8"	8' 5"	7' 8"	6' 8"	6' 6"	5' 11"	5' 2"
	33	Multiple	12' 0"	10' 10"	9' 6"	10' 5"	9' 6"	8' 3"	8' 1"	7' 4"	6' 5"
150F125-43	33	Single	10' 6"	9' 6"	8' 4"	9' 2"	8' 4"	7' 3"	7' 1"	6' 5"	5' 7"
	33	Multiple	13' 0"	11' 9"	10' 3"	11' 4"	10' 3"	9' 0"	8' 9"	7' 11"	6' 11"

### Limiting Ceiling Spans of Furring Channels (ft) - L/360

Specified dead loads			4 psf			6 psf			13 psf		
Section Designation	F <sub>y</sub> (ksi)	Span Type	Spacing (in.) o.c.			Spacing (in.) o.c.			Spacing (in.) o.c.		
			12	16	24	12	16	24	12	16	24
087F125-18	33	Single	4' 7"	4' 2"	3' 7"	4' 0"	3' 7"	3' 2"	3' 1"	2' 9"	2' 5"
	33	Multiple	5' 8"	5' 1"	4' 6"	4' 11"	4' 6"	3' 11"	3' 9"	3' 5"	3' 0"
087F125-27	33	Single	5' 3"	4' 9"	4' 2"	4' 7"	4' 2"	3' 7"	3' 6"	3' 2"	2' 9"
	33	Multiple	6' 6"	5' 10"	5' 1"	5' 8"	5' 1"	4' 6"	4' 4"	3' 11"	3' 5"
087F125-30	33	Single	5' 4"	4' 11"	4' 3"	4' 8"	4' 3"	3' 9"	3' 7"	3' 3"	2' 10"
	33	Multiple	6' 8"	6' 0"	5' 3"	5' 10"	5' 3"	4' 7"	4' 6"	4' 1"	3' 6"
087F125-33	33	Single	5' 6"	5' 0"	4' 5"	4' 10"	4' 5"	3' 10"	3' 9"	3' 5"	2' 11"
	33	Multiple	6' 10"	6' 3"	5' 5"	6' 0"	5' 5"	4' 9"	4' 7"	4' 2"	3' 8"
087F125-43	33	Single	6' 0"	5' 5"	4' 9"	5' 3"	4' 9"	4' 2"	4' 0"	3' 8"	3' 2"
	33	Multiple	7' 5"	6' 9"	5' 10"	6' 6"	5' 10"	5' 1"	5' 0"	4' 6"	3' 11"
150F125-18	33	Single	6' 11"	6' 3"	5' 6"	6' 0"	5' 6"	4' 9"	4' 8"	4' 3"	3' 8"
	33	Multiple	8' 7"	7' 9"	6' 9"	7' 6"	6' 9"	5' 11"	5' 9"	5' 3"	4' 7"
150F125-27	33	Single	7' 11"	7' 2"	6' 3"	6' 11"	6' 3"	5' 6"	5' 4"	4' 10"	4' 3"
	33	Multiple	9' 10"	8' 11"	7' 9"	8' 7"	7' 9"	6' 9"	6' 7"	6' 0"	5' 3"
150F125-30	33	Single	8' 2"	7' 5"	6' 6"	7' 2"	6' 6"	5' 8"	5' 6"	5' 0"	4' 4"
	33	Multiple	10' 1"	9' 2"	8' 0"	8' 10"	8' 0"	7' 0"	6' 10"	6' 2"	5' 5"
150F125-33	33	Single	8' 5"	7' 8"	6' 8"	7' 4"	6' 8"	5' 10"	5' 8"	5' 2"	4' 6"
	33	Multiple	10' 5"	9' 6"	8' 3"	9' 1"	8' 3"	7' 3"	7' 0"	6' 5"	5' 7"
150F125-43	33	Single	9' 2"	8' 4"	7' 3"	8' 0"	7' 3"	6' 4"	6' 2"	5' 7"	4' 11"
	33	Multiple	11' 4"	10' 3"	9' 0"	9' 11"	9' 0"	7' 10"	7' 8"	6' 11"	6' 1"